

UL 746C

ISBN 0-7629-0721-5

Polymeric Materials – Use in Electrical Equipment Evaluations

Underwriters Laboratories Inc. (UL)
333 Pfingsten Road
Northbrook, IL 60062-2096

UL Standard for Safety for Polymeric Material – Use in Electrical Equipment Evaluations, UL 746C

Fifth Edition, Dated November 29, 2001

Announcement Bulletin(s): This Standard contains the announcement bulletin(s) dated March 20, 2001. The announcement bulletin is located at the end of the Standard (after the adoption bulletin(s)).

The following table lists the future effective dates with the corresponding item.

Future Effective Dates	References
June 1, 2004	Paragraphs 3.3, 3.4, 3.21, 3.22, 3.25, 3.26, Sections 4, 5, 6, 7, Section 8 Title, Paragraphs 8.1.1, 8.1.2, 8.1.3, 8.1.4, 8.1.5, 8.1.6, 8.2, 8.2.1, 8.2.2, Section 9, Paragraphs 10.1, 14.1.1, Subsection 14.3 Title, Paragraphs 31.1, 33.1 and A.2. Tables 8.1, 8.2, and A.1. Figures 2.1 and 8.1

As indicated on the title page (page 1), this UL Standard for Safety is an American National Standard. Attention is directed to the note on the title page of this Standard outlining the procedures to be followed to retain the approved text of this ANSI/UL Standard.

As indicated on the title page (page1), this UL Standard for Safety has been adopted by the Department of Defense.

The master for this Standard at UL's Northbrook Office is the official document insofar as it relates to a UL service and the compliance of a product with respect to the requirements for that product and service, or if there are questions regarding the accuracy of this Standard.

UL's Standards for Safety are copyrighted by UL. Neither a printed copy of a Standard, nor the distribution diskette for a Standard-on-Diskette and the file for the Standard on the distribution diskette should be altered in any way. All of UL's Standards and all copyrights, ownerships, and rights regarding those Standards shall remain the sole and exclusive property of UL.

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form by any means, electronic, mechanical photocopying, recording, or otherwise without prior permission of UL.

Revisions of UL Standards for Safety are issued from time to time. A UL Standard for Safety is current only if it incorporates the most recently adopted revisions.

UL provides this Standard "as is" without warranty of any kind, either expressed or implied, including but not limited to, the implied warranties of merchantability or fitness for any purpose.

In no event will UL be liable for any special, incidental, consequential, indirect or similar damages, including loss of profits, lost savings, loss of data, or any other damages arising out of the use of or the inability to use this Standard, even if UL or an authorized UL representative has been advised of the possibility of such damage. In no event shall UL's liability for any damage ever exceed the price paid for this Standard, regardless of the form of the claim.

UL will attempt to answer support requests concerning electronic versions of its Standards. However, this support service is offered on a reasonable efforts basis only, and UL may not be able to resolve every support request. UL supports the electronic versions of its Standards only if they are used under the conditions and operating systems for which it is intended. UL's support policies may change from time-to-time without notification.

UL reserves the right to change the format, presentation, file types and formats, delivery methods and formats, and the like of both its printed and electronic Standards without prior notice.

Purchasers of the electronic versions of UL's Standards for Safety agree to defend, indemnify, and hold UL harmless from and against any loss, expense, liability, damage, claim, or judgement (including reasonable attorney's fees) resulting from any error or deviation introduced while purchaser is storing an electronic Standard on the purchaser's computer system.

If a single-user version electronic Standard was purchased, one copy of this Standard may be stored on the hard disk of a single personal computer, or on a single LAN file-server or the permanent storage device of a multiple-user computer in such a manner that this Standard may only be accessed by one user at a time and for which there is no possibility of multiple concurrent access.

If a multiple-user version electronic Standard was purchased, one copy of the Standard may be stored on a single LAN file-server, or on the permanent storage device of a multiple-user computer, or on an Intranet server. The number of concurrent users shall not exceed the number of users authorized.

Electronic Standards are intended for on-line use, such as for viewing the requirements of a Standard, conducting a word search, and the like. Only one copy of the Standard may be printed from each single-user version of an electronic Standard. Only one copy of the Standard may be printed for each authorized user of a multiple-user version of an electronic Standard. Because of differences in the computer/software/printer setup used by UL and those of electronic Standards purchasers, the printed copy obtained by a purchaser may not look exactly like the on-line screen view or the printed Standard.

An employee of an organization purchasing a UL Standard can make a copy of the page or pages being viewed for their own fair and/or practical internal use.

The requirements in this Standard are now in effect, except for those paragraphs, sections, tables, figures, and/or other elements of the Standard having future effective dates as indicated in the note following the affected item. The prior text for requirements that have been revised and that have a future effective date are located after the Standard, and are preceded by a "SUPERSEDED REQUIREMENTS" notice.

New product submittals made prior to a specified future effective date will be judged under all of the requirements in this Standard including those requirements with a specified future effective date, unless the applicant specifically requests that the product be judged under the current requirements. However, if the applicant elects this option, it should be noted that compliance with all the requirements in this Standard will be required as a condition of continued Recognition, and Follow-Up Services after the effective date, and understanding of this should be signified in writing.

Copyright © 2001 Underwriters Laboratories Inc.

This Standard consists of pages dated as shown in the following checklist:

Page	Date
1-110	November 29, 2001
A1-A4.....	November 29, 2001
SR1-SR24.....	November 29, 2001

No Text on This Page

NOVEMBER 29, 2001

1

UL 746C

**Standard for Polymeric Materials – Use in Electrical Equipment
Evaluations**

The first edition was titled Test for Polymeric Enclosures of Portable Electrical Appliances and numbered UL 746.51.

First Edition – June, 1973
Second Edition – March, 1978
Third Edition – May, 1989
Fourth Edition – December, 1995

Fifth Edition

November 29, 2001

An effective date included as a note immediately following certain requirements is one established by Underwriters Laboratories Inc.

The Department of Defense (DoD) has adopted UL 746C on November 3, 1988. The publication of revised pages or a new edition of this Standard will not invalidate the DoD adoption.

Revisions of this Standard will be made by issuing revised or additional pages bearing their date of issue. A UL Standard is current only if it incorporates the most recently adopted revisions, all of which are itemized on the transmittal notice that accompanies the latest set of revised requirements.

ISBN 0-7629-0721-5

COPYRIGHT © 1973, 2001 UNDERWRITERS LABORATORIES INC.

No Text on This Page

CONTENTS

FOREWORD	8
-----------------------	---

INTRODUCTION

1 Scope	9
2 General	9
3 Glossary	11

ENCLOSURES

4 General	15
5 Portable Unattended Household Equipment – Alternate Path	16
5.1 General	16
5.2 Electrical connections	17
5.3 Materials adjacent to connections	18
5.4 Wire, tubing, sleeving and tape	18
6 Portable Appliances	19
7 Fixed or Stationary Equipment	21

ELECTRICAL INSULATION

8 Material Property Considerations	22
8.1 General	22
8.2 Evaluation of Materials Not Meeting Preselection Test Performance Levels in Table 8.1	23
9 Internal Barriers	29

PERFORMANCE CRITERIA

10 General	30
------------------	----

ELECTRICAL

11 Comparative Tracking Index (CTI)	30
12 Dielectric Strength	31
13 High Current Arc Resistance to Ignition (HAI)	31
14 Hot-Wire Ignition (HWI) – Abnormal Overload Test or Glow-Wire End-Product Test	32
14.1 General	32
14.2 Abnormal overload test	33
14.3 Glow-wire end-product test (GWEPT)	33
15 Inclined Plane Tracking	33
16 Volume Resistivity	34

FLAMMABILITY

17 Flammability – 12 mm Flame	34
18 Flammability – 3/4-Inch Flame	35
19 Flammability – 127 mm (5 Inch) Flame	35
20 Enclosure Flammability – 746-5VS	35
20.1 Test criteria	35
21 Enclosure Flammability – Large Surface Area Considerations	36

22 Flame-Retardant Coatings	36
22.1 General	36
22.2 Test criteria	37

MECHANICAL

23 Crushing Resistance	37
24 Resistance to Impact	38

DIMENSIONAL CHANGE OF POLYMERIC PARTS

25 Creep	38
----------------	----

PERMANENCE

26 Permanence	39
26.1 General	39
26.2 Vicat softening point	39
26.3 Heat deflection temperature	39
26.4 Ball pressure temperature	39
27 Ultraviolet Light Exposure	40
28 Water Exposure and Immersion	41
28.1 General	41
28.2 Dimensional change	41

SPECIAL END-USE CONSIDERATIONS

29 Abnormal Operation	42
30 Severe Conditions	42

THERMAL

31 Mold Stress-Relief Distortion	42
32 Input to Motor	43
33 Strain-Relief Test after Mold Stress-Relief Distortion	43
34 Temperature Considerations— General	43
35 Functional-Use Temperature Indices	44
36 Generic Thermal Indices	45
37 Relative Thermal Index	47
38 Relative Thermal Capability	48
39 Relative Thermal Capability (Alternate)	49
40 Temperature Excursions Beyond the Maximum Use Temperature	52

SPECIALIZED APPLICATIONS

41 General – Adhesives	53
42 Function Analysis	53
43 Program of Investigation	53
43.1 End-product evaluation	53
43.2 Effect of environmental conditions	53
44 Coil Forms	54
45 Conformal Coatings	54

METALLIZED PARTS

46 General	55
47 Ductile Coatings	55
48 Brittle Coatings	56

TEST PERFORMANCE

49 General	56
49.1 Details	56
49.2 Voltmeters	56
49.3 Cheesecloth indicators	57
49.4 Supply-circuit voltage and frequency	57
50 End-Product Arc Resistance Test	57
51 Abnormal Overload Test	58
52 Flammability – 12 mm Flame Test	60
53 Flammability – 3/4 Inch Flame Test	61
54 Flammability – 127 mm (5 inch) Flame Test	62
55 Enclosure Flammability – 746-5VS Test	64
55.1 Apparatus	64
55.2 Plaque conditioning	65
56 Flame-Retardant Coatings Test	66
56.1 Specimen conditioning	66
56.2 Test methods	68
56.3 Other considerations	68
57 Crushing Resistance Test	69
58 Resistance to Impact Test	69
59 Ultraviolet Light Exposure Test	73
59.1 Apparatus	73
59.2 Method	73
60 Water Exposure and Immersion Test	80
61 Abnormal Operation Test	81
62 Severe Conditions Test	81
63 Mold Stress-Relief Distortion Test	82
64 Ball Pressure Test on End-Product	82
65 Input to Motors Test	83
66 Relative Thermal Capability	83
67 Relative Thermal Capability (Alternate)	84
68 Temperature Excursions Beyond the Maximum Use Temperature	84
69 Temperature Considerations – Illustrative Example	86
70 Temperature Considerations – Illustrative Example (Alternate RTC)	88
71 Adhesives – Specialized Applications	91
71.1 General	91
71.2 As-received test	91
71.3 Effect of temperature	91
71.4 Effect of humidity	93
71.5 Effect of cold	93
71.6 Effect of cyclic conditions	93
71.7 Other test considerations	94

COIL FORMS

72	Conformal Coating Test	94
72.1	General	94
72.2	Sample conditioning	98
73	Tape Adhesion Test	99
73.1	General	99
73.2	Samples	101
73.3	Coating Thickness Measurement	101
73.4	Sample Preparation	101
73.5	Conditioning	101
73.6	Results	102
74	Leakage Current Test	102
75	Glow-Wire End-Product Test	105
75.1	General	105
75.2	Significance	105
75.3	Apparatus	105
75.4	Specimens	106
75.5	Conditioning	106
75.6	Procedure	106

MARKING

76	General	109
----	---------------	-----

APPENDIX A Guidelines for Evaluation of Substitute Polymeric Materials

A	Alternate Enclosure Material Considerations	A1
---	---	----

No Text on This Page

FOREWORD

A. This Standard contains basic requirements for products covered by Underwriters Laboratories Inc. (UL) under its Follow-Up Service for this category within the limitations given below and in the Scope section of this Standard. These requirements are based upon sound engineering principles, research, records of tests and field experience, and an appreciation of the problems of manufacture, installation, and use derived from consultation with and information obtained from manufacturers, users, inspection authorities, and others having specialized experience. They are subject to revision as further experience and investigation may show is necessary or desirable.

B. The observance of the requirements of this Standard by a manufacturer is one of the conditions of the continued coverage of the manufacturer's product.

C. A product which complies with the text of this Standard will not necessarily be judged to comply with the Standard if, when examined and tested, it is found to have other features which impair the level of safety contemplated by these requirements.

D. A product that contains features, characteristics, components, materials, or systems new or different from those covered by the requirements in this standard, and that involves a risk of fire or of electric shock or injury to persons shall be evaluated using appropriate additional component and end-product requirements to maintain the level of safety as originally anticipated by the intent of this standard. A product whose features, characteristics, components, materials, or systems conflict with specific requirements or provisions of this standard does not comply with this standard. Revision of requirements shall be proposed and adopted in conformance with the methods employed for development, revision, and implementation of this standard.

E. UL, in performing its functions in accordance with its objectives, does not assume or undertake to discharge any responsibility of the manufacturer or any other party. The opinions and findings of UL represent its professional judgment given with due consideration to the necessary limitations of practical operation and state of the art at the time the Standard is processed. UL shall not be responsible to anyone for the use of or reliance upon this Standard by anyone. UL shall not incur any obligation or liability for damages, including consequential damages, arising out of or in connection with the use, interpretation of, or reliance upon this Standard.

F. Many tests required by the Standards of UL are inherently hazardous and adequate safeguards for personnel and property shall be employed in conducting such tests.

INTRODUCTION

1 Scope

1.1 These requirements cover parts made of polymeric materials that are used in electrical equipment and describe the various test procedures and their use in the testing of such parts and equipment.

1.2 These requirements do not cover the specific insulating systems that are covered by the requirements contained in the Standard for Systems of Insulating Materials, General, UL 1446.

1.3 Test procedures are provided herein for the evaluation of polymeric materials in specific applications. These test procedures include references to data obtained from small-scale property tests conducted under standard conditions as well as other practical means of evaluation.

2 General

2.1 If a value for measurement is followed by a value in other units, the use of either value can be expected to provide equivalent results in the application of such requirements. Each of the requirements is stated in SI units as well as in U.S. customary units. Equivalent, although not necessarily exactly identical results, are to be expected from applying a requirement in SI units or U.S. customary units. Equipment calibrated in metric units is to be used when a requirement is applied in metric terms.

2.2 Any undated reference to a code or standard appearing in the requirements of this standard shall be interpreted as referring to the latest edition of that code or standard.


2.3 For reference purposes, Figure 2.1 describes the procedure to be followed in the evaluation of parts made of polymeric materials and covered by the requirements in this standard.

2.4 The Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94, covers flammability of polymeric materials used for parts in devices and appliances. The Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A, contains short-term test procedures to be used for the evaluation of materials used for parts intended for specific applications in electrical end-products. The Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B, contains long-term test procedures to be used for the evaluation of materials used for parts intended for specific applications in end-products. The Standard for Polymeric Materials – Fabricated Parts, UL 746D, contains requirements for traceability and performance of parts molded and fabricated from polymeric materials.

2.5 Requirements for materials that have been modified to match the requirements of a specific application, including the use of recycled and regrind materials, the use of additives and colorants, and the blending of two or more materials, are described in the Standard for Polymeric Materials – Fabricated Parts, UL 746D.

Figure 2.1
UL 746C guide for polymeric evaluations

Revised Figure 2.1 effective June 1, 2004

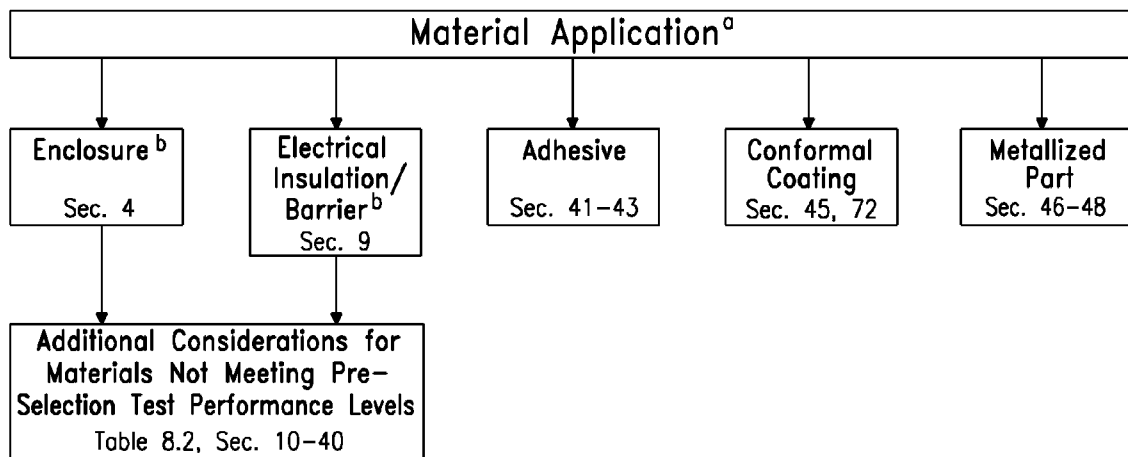

^a More than one application may apply to the material under investigation.

^b For alternate material substitution see Appendix A.

S4304A

3 Glossary

3.1 For the purposes of this standard the following definitions apply:

3.2 **ACCESSIBLE PART** – A part so located that it can be contacted by a person, either directly or by means of a probe or a tool, or that is not recessed the required distance behind an opening.

3.3 *Deleted effective June 1, 2004*

3.4 **ATTENDED EQUIPMENT** – Equipment intended for use where operator presence is required for the equipment to function but is not necessarily required for the equipment to operate. Operator absence is effectively limited to short durations due to one or more characteristics of the equipment such as production of excessive noise or vibration. Examples may include hand-held drills, electric knives, can openers, hand-held hair dryers, blenders, and vacuum cleaners.

Revised 3.4 effective June 1, 2004

3.5 **BRANCH CIRCUIT** – A branch circuit is that portion of the building wiring system beyond the final overcurrent device on the power- distribution panel protecting the circuit to the field-wiring terminals of permanently connected equipment or to the receptacle outlet for cord-connected appliances.

3.6 **COMPARATIVE TRACKING INDEX** – Comparative tracking index (CTI) is determined by the method described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A, Recommended Method for Determining the Comparative Tracking Index of Solid Insulating Materials Under Moist Conditions.

CTI range – tracking index (Volts)	Assigned PLC
$600 \leq TI$	0
$400 \leq TI < 600$	1
$250 \leq TI < 400$	2
$175 \leq TI < 250$	3
$100 \leq TI < 175$	4
$0 \leq TI < 100$	5

3.7 **CONFORMAL COATING** – A protective covering applied on a printed wiring board to increase the dielectric voltage-withstand capability between conductors and to protect against environmental conditions.

3.8 **CORD-CONNECTED UNIT** – An appliance or product intended for connection to the branch-circuit power line by means of a power supply cord.

3.9 **COUNTER-SUPPORTED APPLIANCE** – An appliance that is physically supported by a counter, table or bench during the performance of its intended function.

3.10 **DECORATIVE PART** – A part used for ornamental purposes only and not as an enclosure or insulation of electrically live parts.

3.11 **ENCLOSURE** – That part of the product that:

- a) Renders inaccessible all or any parts of the equipment that may otherwise present a risk of electric shock and/or

b) Retards propagation of flame initiated by electrical disturbances occurring within.

3.12 FIELD-WIRING TERMINAL – Any terminal where a power supply or other wire can be connected by an installer in the field.

3.13 FIXED EQUIPMENT – Any equipment or appliance that is intended to be permanently connected electrically to the wiring system.

3.14 FLAMMABILITY CLASSIFICATION – The flammability classification of a material is determined by tests described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94.

3.15 GLOW WIRE RESISTANCE TO IGNITION – Glow wire resistance to ignition performance is expressed as the number of seconds required to ignite a specimen by an electrically heated bar operating at a specified temperature. This test is described in the Standard for Polymeric Materials– Short Term Property Evaluations, UL 746A.

3.16 GROUND – Earth ground, unless otherwise specified.

3.17 HAND-SUPPORTED APPLIANCE – An appliance that is physically supported by any part of the body of the user during the performance of its intended functions.

3.18 HIGH-CURRENT ARC RESISTANCE TO IGNITION – High-Current arc resistance to ignition (HAI) performance is expressed as the number of arc-rupture exposures (standardized as to electrode type and shape and electrical circuit) that are necessary to ignite a material when they are applied at a standard rate on the surface of the material. This test is described in the Standard for Polymeric Materials – Short Term Property Evaluation, UL 746A.

HAI range – mean number of arcs to cause ignition (NA)	Assigned PLC
$120 \leq NA$	0
$60 \leq NA < 120$	1
$30 \leq NA < 60$	2
$15 \leq NA < 30$	3
$0 \leq NA < 15$	4

3.19 HOT-WIRE RESISTANCE TO IGNITION – Hot-wire resistance to ignition (HWI) performance is expressed as the mean number of seconds needed to ignite standard specimens that are wrapped with resistance wire that dissipates a specified level of electrical energy. The test is described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

HWI range – mean ignition time (sec.)	Assigned PLC
$120 \leq IT <$	0
$60 \leq IT < 120$	1
$30 \leq IT < 60$	2
$15 \leq IT < 30$	3
$7 \leq IT < 15$	4
$0 \leq IT < 7$	5

3.20 HOUSEHOLD APPLIANCE – An appliance intended for use in the home.

3.21 IEC Glow Wire Ignitability Temperature (GWIT) – in accordance with IEC 60695-2-1/3, is expressed as the temperature in degrees C which is 25°C hotter than the maximum temperature of the tip of the glow-wire which does not cause ignition of the material.

Added 3.21 effective June 1, 2004

3.22 IEC Glow Wire Flammability Temperature (GWFT) – in accordance with IEC 60695-2-1/2, is expressed as the highest temperature (in degrees C) at which flaming or glowing of the material extinguishes within 30 seconds after removal of the glow-wire and without ignition of the specified indicator by burning drips or particles.

Added 3.22 effective June 1, 2004

3.23 INSULATED LIVE PART – An electrically live part that is provided with complete protection against electric shock and does not rely upon other parts for insulation.

3.24 INSULATION, FUNCTIONAL – The insulation necessary for the proper functioning of the product and for basic protection against electric shock.

3.25 INTERMITTENT OPERATION EQUIPMENT – Operation in a series of specified cycles each composed of a period of operation under NORMAL LOAD, followed by a rest period with the equipment switched off or running idle.

Added 3.25 effective June 1, 2004

3.26 LEVEL OF ATTENDANCE – The level of operator attendance is determined by whether or not operator presence is normally required or essential in order for the equipment to perform its intended task or purpose. Consideration should be given to whether the equipment has to be kept switched on by hand or foot, or equipment, which is continuously loaded by hand under normal use. The end-product standard should be referenced when determining the applicable level.

Added 3.26 effective June 1, 2004

3.27 LIVE PARTS – Denotes metal or other conductive parts that, during intended use, has an electrical potential difference with respect to earth ground or any other conductive part.

3.28 NON-HAZARDOUS ENERGY CIRCUIT – A circuit that is not considered to have a risk of electric shock or fire.

3.29 PERFORMANCE LEVEL CATEGORY – An integer that defines a range of test values for a given electrical/mechanical property test.

3.30 PORTABLE APPLIANCE – An appliance that is easily carried or conveyed by hand, and is provided with a power-supply cord for connection to the supply circuit.

3.31 POWER-SUPPLY CORD – The flexible electrically insulated cord provided to connect the product to the supply circuit.

3.32 PRIMARY CIRCUITS – The wiring and components that are conductively connected to the supply circuit.

3.33 PRINTED-WIRING BOARD – The finished combination of a pattern of conductive paths either on or within multilayer sheets of insulating material.

3.34 RISK OF ELECTRIC SHOCK – A risk of electric shock is considered to exist at any part if,

- a) The potential between the part and earth ground or any other accessible part is more than 42.4 V peak, and
- b) The continuous current flow through a 1500 ohm resistor connected across the potential exceeds 0.5 mA.

3.35 RISK OF FIRE – A risk of fire is considered to exist at any two points in a circuit where;

- a) The open circuit voltage is more than 42.4 V peak and the energy available to the circuit under any condition of load including short circuit, results in a current of 8 A or more after 1 minute of operation, or
- b) A power of more than 15 watts can be delivered into an external resistor connected between the two points.

3.36 SAME BASIC COMPOSITION – Materials that are of the identical generic material type having equivalent percentage and type of fillers, additives, resins and reinforcements.

3.37 SECONDARY CIRCUIT – A secondary circuit is a circuit supplied from a secondary winding of an isolating transformer.

3.38 STATIONARY EQUIPMENT – Any equipment or appliance that is intended to be fastened in place or located in a dedicated space, and is provided with a power-supply cord for connection to the supply circuit.

3.39 SUPPLY CIRCUIT – The branch circuit supplying electrical energy to the product.

3.40 UNINSULATED LIVE PART – A part involving the risks of fire or electric shock that is bare or has insulation that is not acceptable for the operating conditions (electrical potential, temperature, and the like) involved.

3.41 USER SERVICING – The replacing, cleaning, or adjusting done by the user.

3.42 VULCANIZED FIBER – A term used in this standard to denote a material normally used as electrical insulation. Vulcanized fiber is made by combining layers of chemically gelled paper. The zinc chloride used in gelling the paper is subsequently removed by a water leaching treatment, and the resultant product, after being dried and finished by calendering, is a dense material of partially regenerated cellulose where the fibrous structure is retained in varying degrees, depending upon the grade of fiber. Cellulose fiberboard, pressboard, fullerboard, or cardboard are not acceptable as the equivalent of fiber. Fishpaper is a designation commonly used in the trade to refer to thin sheets of electrical grade vulcanized fiber.

ENCLOSURES

4 General

4.1 Equipment having an enclosure, or parts of the enclosure, comprised of polymeric material shall comply with the applicable requirements in Table 4.1.

Revised 4.1 effective June 1, 2004

4.2 The requirements in this section, do not cover the additional considerations that must be given to enclosure materials exposed to oils, acids, solvents, cleaning agents, and the like in use. The performance of the material shall not be adversely affected by such environments (if encountered in the end-use application) as determined by applicable tests as detailed in the end-product standard or the Standard for Polymeric Materials – Short Term Property Evaluation, UL 746A.

Revised 4.2 effective June 1, 2004

4.3 If a metal sub-enclosure houses all insulated or uninsulated live parts that involve a risk of fire, then the overall polymeric outer enclosure may be classed either 5VA, 5VB, V-O, V-1, V-2, or HB.

Exception: A V-0 material may be substituted for the metal sub-enclosure for portable equipment described in Path II of Table 4.1.

Revised 4.3 effective June 1, 2004

4.4 Decorative parts are not required to be made of a material classed 5VA, 5VB, V-0, V-1, V-2, or HB, providing the part does not occupy a volume greater than 2 cubic centimeters (0.122 cubic inch), does not have any dimension greater than 3 cm (1.18 inch), and is located so it cannot propagate flame from one area to another or bridge between a possible source of ignition and other ignitable parts.

Added 4.4 effective June 1, 2004

4.5 The use of a flame-retardant coating applied to the inside of a polymeric enclosure is not acceptable unless the coating/material interface is found to be acceptable by separate investigation (see Flame-Retardant Coatings, Section 22).

Added 4.5 effective June 1, 2004

Table 4.1
Enclosure Requirements

Revised Table 4.1 effective June 1, 2004

Path	I	II	III
Application Area	Portable Attended Household Equipment	All other Portable Equipment ^k	All other Equipment
Applicable requirements shown below			
Minimum Flammability Rating	HB^{a,d}	V^{b,d}	5VA^{c,d}
Material Properties per Table 8.1	Yes	Yes	Yes
Impact Test per Section 24	Yes	Yes	Yes
Crush Resistance per 23.1	No	No	Yes
Abnormal Operations Test per 29.1	Yes	Yes	Yes
Severe Conditions Test per 30.1	Yes ^l	No ^l	Yes
Mold-Stress Relief Distortion per Section 31.1	Yes ^e	Yes ^e	Yes ^e
Input after Mold-Stress Relief per 32.1	Yes	No	Yes
Strain Relief Test per 33.1	Yes ^f	Yes ^f	Yes ^f
UV Resistance per 27.1	Yes ^g	Yes ^g	Yes ^g

Table 4.1 Continued on Next Page

Table 4.1 Continued

Path	I	II	III
Application Area	Portable Attended Household Equipment	All other Portable Equipment ^k	All other Equipment
Applicable requirements shown below			
Minimum Flammability Rating	HB ^{a,d}	V ^{b,d}	5VA ^{c,d}
Water Exposure and Immersion per Sec. 28	Yes ^h	Yes ^h	Yes ^h
Dimensional Stability per 28.2	Yes	Yes	Yes
Conduit Connections	No	No	Yes ⁱ
^a HB or has a GWIT and GWFT of 750°C, or the enclosure complies with the 12 mm or 20 mm end-product flame tests as described in Section 17 and 18 respectively. ^b V=V-0, V-1 or V-2 classed materials, or the enclosure complies with the 12 mm or 20 mm end-product flame tests as described in Section 17 and 18 respectively. Exception: A polymeric enclosure material classified HB may be used in portable unattended household equipment that complies with the criteria specified in Section 5. ^c 5VA or the enclosure complies with the 127 mm end-product flame tests as described in Section 19. ^d May require flame spread per Section 21. ^e Mold-Stress Relief. For HB enclosures use Section 63.2. For V, 5VA or enclosures that comply with the 12 mm or 20 mm end-product flame tests as described in Section 17 and 18 respectively use Section 63.1. ^f This test is only required if the strain-relief means is secured to the enclosure or is an integral part of the polymeric enclosure. ^g This test is only required if the equipment is intended for outdoor use and is constructed such that the enclosure's degradation from exposure to outdoor weather conditions or UV radiation could increase the risk of fire, electrical shock, or injury to persons. ^h This test is only required if the equipment is intended for outdoor use and is constructed such that the enclosure's degradation from exposure to water could increase the risk of fire, electrical shock, or injury to persons. ⁱ This test is required only if the equipment is permanently connected electrically to the wiring system. The continuity of the conduit system shall be a metal-to-metal contact. If the integrity of the polymeric enclosure is relied upon to provide for bonding between the parts of the conduit system at any location where conduit may be connected, the bonding shall be evaluated by the requirements contained in the Standard for Enclosures for Electrical Equipment, UL 50. If the polymeric enclosure is intended for connection to a rigid conduit system, it shall acceptably perform when tested using the pullout, torque and bending tests as described in the Standard for Industrial Control Equipment, UL 508. ^j This test is only required for materials that are rated HB. ^k Path II includes portable attended and unattended commercial equipment, and portable unattended household equipment.			

5 Portable Unattended Household Equipment – Alternate Path

Added Section 5 effective June 1, 2004

5.1 General

5.1.1 The basic flammability resistance requirement for polymeric enclosures of portable unattended household equipment is the use of a V-0, V-1 or V-2 rated material, or of a material that complies with the 12 mm or 20 mm end-product flame tests as described in Sections 17 and 18. Alternatively, the use of HB rated materials as the enclosure of portable unattended household equipment is acceptable if the requirements in this section are met.

5.1.2 In addition to the requirements outlined in Table 4.1, portable unattended household equipment employing HB rated enclosure material shall comply with the Severe Conditions Test per 30.1, Mold Stress Relief Distortion Test per Subsection 31.1 (utilizing conditioning guidelines as outlined in Subsection 63.2) and Input after Mold Stress Relief Test per Subsection 32.1.

5.1.3 All electrical connections within the polymeric enclosure of portable unattended household equipment employing HB rated enclosure material shall comply with Subsections 5.2, 5.3 and 5.4.

Exception No. 1: This requirement is not applicable to current-carrying connections that do not involve a risk of fire as defined by 3.35.

Exception No. 2: This requirement is not applicable to the following types of connections:

- a. welded connections,*
- b. soldered connections on printed circuit boards located in Class 2 circuitry, or*
- c. connections on small components that are mounted on printed circuit boards located in Class 2 circuitry.*

Exception No. 3: This requirement is not applicable to snap switches, lampholders with switching mechanisms, appliance inlets and outlets, receptacles, and special-use switches that have been found to be acceptable with respect to resistance to ignition, resistance to arcing, or overload and endurance testing in compliance with the following standards:

UL 20, the Standard for Snap Switches;

UL 496, the Standard for Edison-Base Lampholders;

UL 498, the Standard for Receptacles and Attachment Plugs;

UL 1054, the Standard for Special-Use Switches;

All electrical connections, as identified in 5.2.1, to these devices shall comply with Subsections 5.2, 5.3 and 5.4.

5.2 Electrical connections

5.2.1 All electrical connections, such as wire nuts, splicing wire connectors, quick-connect terminals, terminal connectors, multi-pin and other forms of wire connectors and the like, shall comply with the following standards:

- a) UL 310, the Standard for Electrical Quick-Connect Terminals;
- b) UL 486A, the Standard for Wire Connectors and Soldering Lugs for Use with Copper Conductors;
- c) UL 486C, the Standard for Splicing Wire Connectors;
- d) UL 486E, the Standard for Equipment Wiring Terminals for Use with Aluminum and/or Copper Conductors; or
- e) UL 1977, the Standard for Component Connectors for Use in Data, Signal, Control and Power Applications.

5.2.2 Polymeric materials used on connectors shall be rated V-0 or V-1 and shall be so identified.

Exception: A polymeric material that complies with either items (a), (b), or (c) of 5.3.1.

5.3 Materials adjacent to connections

5.3.1 All polymeric materials located within 3 mm of electrical connections shall comply with the following requirements as applicable:

- a) A minimum V-0, V-1, VTM-0, or VTM-1 flammability classification for the polymeric material in accordance with UL 94, the Standard for Tests for Flammability of Plastic Materials in Devices and Appliances,
- b) A minimum SC-0, SC-1, SCTC-0, or SCTC-1 flammability classification for the polymeric material in accordance with UL 1694, the Standard for Tests for Flammability of Small Polymeric Component Materials, or
- c) A minimum Glow Wire Ignitability Temperature (GWIT) and a Glow Wire Flammability Temperature (GWFT) of 750°C for the polymeric material in accordance with IEC 60695-2-1/3 and IEC 60695-2-1/2, respectively, or the part complies with the Glow Wire End Product Test (GWEPT) as described in Section 75.

5.4 Wire, tubing, sleeving and tape

5.4.1 Components such as wire, tubing, sleeving, or tape that are located within 3 mm of a connection shall comply with the following requirements as applicable:

- a) A VW-1 rating for wire evaluated in accordance with UL 1581, the Standard for Electrical Wires, Cables and Flexible Cords,
- b) A VW-1 rating for tubing and sleeving evaluated in accordance with UL 224, the Standard for Extruded Insulating Tubing, or UL 1441, the Standard for Coated Electrical Sleeving, or
- c) Flame-retardant insulating tape shall be evaluated in accordance with UL 510, the Standard for Polyvinyl Chloride, Polyethylene and Rubber Insulating Tape.

6 Portable Appliances

Section 6 deleted effective June 1, 2004. Applicable requirements for Portable Appliances moved to Section 4

6.1 *Deleted effective June 1, 2004*

6.2 *Deleted effective June 1, 2004*

6.3 *Deleted effective June 1, 2004*

6.4 *Deleted effective June 1, 2004*

6.5 *Deleted effective June 1, 2004*

6.6 *Deleted effective June 1, 2004*

Figure 6.1
Enclosure requirements for portable appliances

Figure 6.1 deleted effective June 1, 2004

6.7 Deleted effective June 1, 2004

6.8 Deleted effective June 1, 2004

6.9 Deleted effective June 1, 2004

6.10 Deleted effective June 1, 2004

6.11 Deleted effective June 1, 2004

7 Fixed or Stationary Equipment

Section 7 deleted effective June 1, 2004. Applicable requirements for Fixed or Stationary Equipment moved to Section 4

7.1 Deleted effective June 1, 2004

7.2 Deleted effective June 1, 2004

7.3 Deleted effective June 1, 2004

7.4 Deleted effective June 1, 2004

7.5 Deleted effective June 1, 2004

7.6 Deleted effective June 1, 2004

7.7 Deleted effective June 1, 2004

7.8 Deleted effective June 1, 2004

7.9 Deleted effective June 1, 2004

Figure 7.1 Enclosure requirements for fixed or stationary equipment

Figure 7.1 deleted effective June 1, 2004

7.10 Deleted effective June 1, 2004

7.11 Deleted effective June 1, 2004

ELECTRICAL INSULATION

8 Material Property Considerations

Revised Title effective June 1, 2004

8.1 General

8.1.1 Mechanical and electrical properties of materials are to be judged with respect to the particular "end use" application. The requirements in this section establish general minimum requirements for applications where the polymeric material is relied upon to reduce the risks of fire and electric shock.

Revised 8.1.1 effective June 1, 2004

8.1.2 These requirements do not cover the additional considerations that must be given to applications employing large masses of polymeric materials. Whether or not such materials protect against electric shock or injury to persons, consideration is to be given to the likelihood of ignition of the material by sources inside the product or by sources outside the product. See Section 21 for Flame Spread requirements to be applied to large mass applications.

Revised 8.1.2 effective June 1, 2004

8.1.3 These requirements supplement the requirements for enclosures in Section 4.

Revised 8.1.3 effective June 1, 2004

8.1.4 Figure 8.1 is to be used as a guide to determine the applicable material-property requirements. First, the construction features found in the end product are to be matched to the Figurative examples given in Figure 8.1. By referring back to Table 8.1, it can be determined which minimum property values are required for each of the typical constructions (Figurative examples).

Exception: End product tests may be used instead of pre-selection tests to determine if the material is acceptable in the application, as indicated in Table 8.2.

Note – As an example of using Table 8.1 and Figure 8.1, a polymeric material used in an application that most closely matches figurative example No. 7 of Figure 8.1, would be evaluated with respect to the mold-stress relief, resistance to creep, and maximum-use temperature properties indicated in Table 8.1.

Revised 8.1.4 effective June 1, 2004

8.1.5 Deleted effective June 1, 2004

8.1.6 To determine a polymeric material's performance profile, certain tests are to be performed according to the methods contained in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A and the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B. These tests, general engineering considerations, and minimum performance levels are tabulated in Table 8.1. Specific applications may require different limits than are shown in the general case. Refer to 8.2 for considerations to be used in determining the acceptability of an insulating material that does not meet with the requirements tabulated in Table 8.1.

Revised 8.1.6 effective June 1, 2004

8.1.7 In establishing acceptable performance levels, consideration has been given to the service experience and to property values of presently available materials. Minimum performance characteristics have been grouped into four distinct levels based upon a material's flammability classification. The basis for the grouping is a relationship developed between resistance to ignition and persistence or rate of burning.

8.1.8 Nonrigid foamed materials – having a tensile or flexural modulus less than 0.69 gigapascals (100,000 lbf/in²), and a density less than 0.5 gram per cubic centimeter (31.3 lb/ft³) – are generally not considered acceptable for the direct or indirect support of live parts.

8.2 Evaluation of Materials Not Meeting Preselection Test Performance Levels in Table 8.1

Revised 8.2 effective June 1, 2004

8.2.1 Some materials may have performance characteristics less than the minimum required for the construction type (Figurative example) in Table 8.1. In such cases, the application can be considered in the context of the complete end product construction and special tests conducted to determine if the lower value can be accepted without increasing the likelihood of risk for the particular end-product.

Revised 8.2.1 effective June 1, 2004


8.2.2 Table 8.2 indicates which end-product tests, or other considerations such as increased thicknesses or spacings, may be used as alternatives to the requirements in Table 8.1.

Revised 8.2.2 effective June 1, 2004

Figure 8.1
Figurative examples for Table 8.1


Revised Figure 8.1 effective June 1, 2004

1.

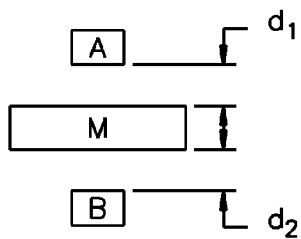


$d_1 + d_2 < S_a$
WHERE d_1, d_2 = THROUGH AIR SPACING
 S_a = APPLICABLE THROUGH AIR
SPACING REQUIREMENT

2.




$d < 12.7\text{mm}$
WHERE d = OVER SURFACE SPACING

3.

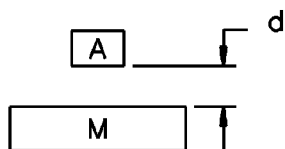

$0 \leq d < 0.8\text{mm}$
WHERE d = THROUGH AIR SPACING






4.

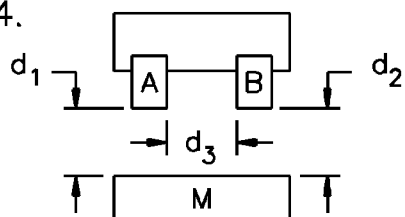

$d_1, d_2 < 0.8\text{mm}$
 $d_3 < 12.7\text{mm}$
WHERE d_1, d_2 = THROUGH AIR SPACINGS
 d_3 = OVER SURFACE SPACING

S3463B-1

Figure 8.1 (Cont.)
Figurative examples for Table 8.1

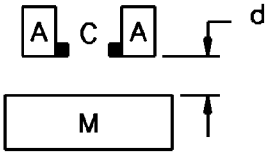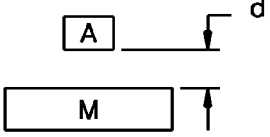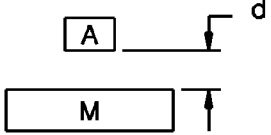5.  $d < 12.7\text{mm}$
WHERE d = THROUGH AIR SPACING
C = ELECTRICAL CONTACTS, e.g.
SWITCH CONTACTS,
RELAY CONTACTS,
BRUSH/COMMUTATOR CONTACTS
6.  $0.8\text{mm} \leq d < 12.7\text{mm}$
WHERE d = THROUGH AIR SPACING
7.  D = ACCEPTABLE INSULATING MATERIAL
IN CONTACT WITH "A" AND MOUNTED
ON "M" BY SCREWS
8.  $d \geq 12.7\text{mm}$
9.  $0 \leq d \leq 3\text{mm}$
WHERE d = THROUGH AIR SPACING

A = UNINSULATED LIVE PART

B = (1) UNINSULATED LIVE PART HAVING DIFFERENCE IN POTENTIAL FROM A, OR
(2) DEAD METAL PART THAT MAY BE GROUNDED IN SERVICE OR IS EXPOSED TO CONTACT.

M = POLYMERIC MATERIAL UNDER CONSIDERATION

Note: (1) ALL SPACINGS ASSUMED TO BE RELIABLY MAINTAINED.
(2) UNLESS SHOWN IN CONTACT WITH "M", ALL LIVE PARTS ARE SUPPORTED BY STRUCTURES NOT DEPENDENT ON "M".

S3463B-3

Table 8.1
Material property considerations

Revised Table 8.1 effective June 1, 2004

Property	Test	Method	Units of PLC	Recommended levels related to flammability classification ^a				Applications ^b	Figurative examples from Fig. 8.1
				V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB		
ELECTRIC STRENGTH	Volume – resistivity (Sec.16)	UL 746A	Min Ohm-cm (dry)	50 x 10 ⁶	50 x 10 ⁶	50 x 10 ⁶	50 x 10 ⁶	Material serves as insulation between uninsulated live parts of opposite polarity or between uninsulated live parts and (1) dead metal parts that may be grounded in service or (2) any surface exposed to contact	(1), (2), (3), (8)
			Min Ohm-cm (after 90% humidity)	10 x 10 ⁶	10 x 10 ⁶	10 x 10 ⁶	10 x 10 ⁶		
	Dielectric strength (Sec.12)	UL 746A	Min V (rms) (both dry & after 90% humidity)	5000	5000	5000	5000	Same as above	(1), (2), (3), (8)
TRACKING RESISTANCE	Comparative tracking index (CTI) (Sec.11)	UL 746A	Max ^c PLC					Material surface is in contact with or in close proximity (less than 1/32 inch (0.8mm)) to (a) uninsulated live parts of opposite polarity, or (b) uninsulated live parts and either (1) dead metal parts that may be grounded in service, or (2) any surface exposed to contact Higher CTI values are required where a greater degree of contamination is involved, as follows: Indoor equipment exposed to relatively clean environment	(2), (3), (4)
				4	4	4	4		
				3	3	3	3		
	CTI	UL 746A	Max ^c PLC	2	2	2	2	Outdoor and indoor equipment exposed to moderate contaminate environments Outdoor and indoor equipment exposed to severe contaminate environments	
	Inclined-plane tracking (Sec. 15)	UL 746A	Min time (min) to track 25.4 mm at 2.5 kV excitation	60	60	60	60	Same as above for CTI except that the application voltage range is 601 V-5 kV	(2), (3), (4), (8)
				300	300	300	300	Same as above for CTI except that application voltage range 5,001 V-35 kV	(2), (3), (4), (8)

Table 8.1 Continued on Next Page

Table 8.1 Continued

Property	Test	Method	Units of PLC	Recommended levels related to flammability classification ^a				Applications ^b	Figurative examples from Fig. 8.1
				V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB		
PERMANENCE	Dimensional change after water exposure (28.2.1)	UL 746A	Max percent change	2	2	2	2	Same as Volume Resistivity above but also includes applications where the material maintains the relative positioning of live parts and the parts could be subjected to high humidity or moisture	(1), (2), (3), (4), (7), (8)
DISTORTION UNDER LOAD	Heat deflection temperature under load or Vicat softening point or Ball pressure temperature (Sec. 31)	UL 746A	Min °C at 66 psi	10°C (18°F) greater than the use temperature but not less than 90°C 25°C greater than the use temperature but not less than 105°C (221°F) Greater than the use temperature by the difference between 40°C and the ambient, but not less than 95°C				All applications except decorative parts	(1), (2), (3), (4), (5), (6), (7), (8)
DIMENSIONAL CHANGE DUE TO EXTERNAL STRESSES	Resistance to Creep (Sec. 25)	UL 746C		Resistance to creep should be evaluated in the specific application				All applications with mechanical stresses due to external sources	(1), (2), (3), (4), (5), (6), (7), (8)
RESISTANCE TO ELECTRICAL IGNITION SOURCES	High current arc resistance to ignition (HAI) (Sec. 13)	UL 746A	Max PLC ^d	3	2	2	1	Material is in contact with or in close proximity to uninsulated live parts 0.8 mm (1/32 inch) for nonarcing parts or 12.7 mm (1/2 inch) for arcing parts	(1), (2), (3), (4), (5), (8)
	Hot wire ignition HWI (Sec. 14)	UL 746A	Max PLC ^e	4	3	2	2	Material is in contact with or close proximity to uninsulated live parts [less than 0.8 mm (1/32 inch)]	(2), (3), (4), (8)
MECHANICAL	Tensile or flexural strength; tensile, Izod, or Charpy impact (Sec. 24)	UL 746A	MPa KJ/m ² or J/m notch	Mechanical strength is judged in the application				Material maintains the relative positioning of live parts or encloses live parts	(2), (4), (7), (8)
MAXIMUM USE TEMPERATURE	Relative thermal index (RTI) (Sec. 38 – 40)	UL 746A	Minimum °C	The maximum operating temperature of the part shall not exceed materials' temperature limit determined by the method, indicated in Table 34.1 (See Sections 34 – 40)				All applications except decorative parts	(1), (2), (3), (4), (5), (6), (7), (8)

Table 8.1 Continued on Next Page

Table 8.1 Continued

Property	Test	Method	Units of PLC	Recommended levels related to flammability classification ^a				Applications ^b	Figurative examples from Fig. 8.1														
				V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB																
GLOW WIRE	Glow Wire Ignitability Temperature (GWIT) and Glow Wire Flammability Temperature (GWFT) Sec. 5	UL 746A	Min °C	N/A	N/A	750 ^f	750 ^f	Material is spaced 3 mm or less from electrical connections in circuitry that involve a risk of fire; see note f	(2), (3), (4), (5), (6), (7), (8), (9)														
^a Materials classed as 5VA and 5VB only by the Vertical Burning Test described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94, or a material when flame tested as used in the equipment, complies with the requirements in Flammability - 12 mm flame, Section 17, Flammability - 3/4-inch flame, Section 18, or Flammability - 127 mm (5 inch) flame, Section 19, shall be considered with respect to the recommended performance levels of a material classed as V-1.																							
^b Materials located in nonhazardous-energy circuitry, as defined in the appropriate end-product standard, shall only be considered with respect to their flammability, distortion under load and mold stress relief, mechanical and maximum use temperature properties except the resistance to electrical ignition sources property may also be considered if the material is located less than 12.7 (1/2 inch) from arcing parts or sources of ignition.																							
^c <table><tr><th>CT1 Range – Tracking Index (Volts)</th><th>Assigned PLC</th></tr><tr><td>600 ≤ TI</td><td>0</td></tr><tr><td>400 ≤ TI < 600</td><td>1</td></tr><tr><td>250 ≤ TI < 400</td><td>2</td></tr><tr><td>175 ≤ TI < 250</td><td>3</td></tr><tr><td>100 ≤ TI < 175</td><td>4</td></tr><tr><td>0 ≤ TI < 100</td><td>5</td></tr></table>										CT1 Range – Tracking Index (Volts)	Assigned PLC	600 ≤ TI	0	400 ≤ TI < 600	1	250 ≤ TI < 400	2	175 ≤ TI < 250	3	100 ≤ TI < 175	4	0 ≤ TI < 100	5
CT1 Range – Tracking Index (Volts)	Assigned PLC																						
600 ≤ TI	0																						
400 ≤ TI < 600	1																						
250 ≤ TI < 400	2																						
175 ≤ TI < 250	3																						
100 ≤ TI < 175	4																						
0 ≤ TI < 100	5																						
^d During the HAI test, the electrodes are to be positioned as indicated in 13.2. <table><tr><th>HAI Range – mean number of arcs to cause ignition</th><th>Assigned PLC</th></tr><tr><td>120 ≤ NA</td><td>0</td></tr><tr><td>60 ≤ NA < 120</td><td>1</td></tr><tr><td>30 ≤ NA < 60</td><td>2</td></tr><tr><td>15 ≤ NA < 30</td><td>3</td></tr><tr><td>0 ≤ NA < 15</td><td>4</td></tr></table>										HAI Range – mean number of arcs to cause ignition	Assigned PLC	120 ≤ NA	0	60 ≤ NA < 120	1	30 ≤ NA < 60	2	15 ≤ NA < 30	3	0 ≤ NA < 15	4		
HAI Range – mean number of arcs to cause ignition	Assigned PLC																						
120 ≤ NA	0																						
60 ≤ NA < 120	1																						
30 ≤ NA < 60	2																						
15 ≤ NA < 30	3																						
0 ≤ NA < 15	4																						
^e <table><tr><th>HWI Range – mean ignition time</th><th>Assigned PLC</th></tr><tr><td>120 ≤ IT</td><td>0</td></tr><tr><td>60 ≤ IT < 120</td><td>1</td></tr><tr><td>30 ≤ IT < 60</td><td>2</td></tr><tr><td>15 ≤ IT < 30</td><td>3</td></tr><tr><td>7 ≤ IT < 15</td><td>4</td></tr><tr><td>0 ≤ IT < 7</td><td>5</td></tr></table>										HWI Range – mean ignition time	Assigned PLC	120 ≤ IT	0	60 ≤ IT < 120	1	30 ≤ IT < 60	2	15 ≤ IT < 30	3	7 ≤ IT < 15	4	0 ≤ IT < 7	5
HWI Range – mean ignition time	Assigned PLC																						
120 ≤ IT	0																						
60 ≤ IT < 120	1																						
30 ≤ IT < 60	2																						
15 ≤ IT < 30	3																						
7 ≤ IT < 15	4																						
0 ≤ IT < 7	5																						
^f Glow Wire Ignitability Temperature (GWIT) and Glow Wire Flammability Temperature (GWFT) requirements apply only to portable household equipment in accordance with Path II of Table 4.1, or components intended for use in these enclosures.																							

Table 8.2
Additional considerations for materials not meeting pre-selection test performance levels

Revised Table 8.2 effective June 1, 2004

Test		Additional end product considerations
1.	Volume resistivity	Conduct end product leakage current test – see 16.1
2.	Dielectric strength	Use thicker material section – see 12.1
3.	Comparative tracking index (CTI)	Increase spacings
4.	Inclined Plane tracking	Increase spacings
5.	Permanence	Conduct end product conditioning test – see 28.2
6.	Distortion under load	Conduct end product mold stress-relief distortion test where stress is internal (i.e., results from molding or fabrication process) – see 31.1
7.	High current arc ignition (HAI)	Conduct end product arc resistance test – see 13.3 and 13.4
8.	Hot wire ignition (HWI)	Conduct end product abnormal overload test, or end-product Glow-Wire Test – see Hot-Wire Ignition (HWI) – Abnormal Overload Test, Section 14
9.	Maximum Use Temperature	Conduct end product thermal aging test – see Relative Thermal Index, Section 37, Relative Thermal Capability, Section 38, and Temperature Excursions Beyond the Maximum Use Temperature, Section 40

9 Internal Barriers

9.1 A barrier or liner employed where spacings are unacceptable between uninsulated live parts of opposite polarity or between uninsulated live parts and accessible metal parts, shall comply with all of the following:

- a) The barrier or liner shall be of insulating material that complies with Table 8.1.
- b) The minimum thickness of the barrier or liner shall be at least 0.71 mm, except that 0.33 mm is acceptable where used in conjunction with an air space of at least one-half of the required clearance.

Exception No. 1: The thickness of the barrier may be less than that specified in 9.1(b) providing that the results of a separate investigation indicate acceptable performance. Resin bonded mica 0.15 mm thick is considered to meet this thickness requirement when its use is limited to applications where it is protected from mechanical abuse or movement. Polyethylene terephthalate (PETE) film 0.18 mm thick, or greater, is considered to meet the thickness requirement.

c) The barrier or liner shall be equivalent to vulcanized fiber in mechanical strength (tensile strength, tear resistance, puncture strength, Cold Flow, and the like) if likely to be subject to mechanical damage. See the Standard for Polymeric Materials – Industrial Laminates, Filament Wound Tubing, Vulcanized Fibre, and Materials used in Printed Wiring Boards, UL 746E, Vulcanized Fibre, Section 9, for specific performance indexing data on vulcanized fiber.

Revised 9.1 effective June 1, 2004

9.2 A material, that is used as a physical barrier against contact with parts that can cause injury to persons during intended operation and user servicing, or to restrict access to circuitry where there is an increased risk of electric shock, shall comply with the requirements in Table 8.1.

Revised 9.2 effective June 1, 2004

Table 9.1
Material requirements for internal barriers

Table 9.1 deleted effective June 1, 2004

9.3 *Deleted effective June 1, 2004*

PERFORMANCE CRITERIA

10 General

10.1 Sections 10– 40 indicate the test methods and minimum performance levels specified in Table 4.1 and Table 8.1. Some materials may not comply with all of the general properties required for the application. In such cases, the application must be further considered to determine if the material's characteristics are not acceptable, or if a reduced value can be accepted without increasing the likelihood of risk for the particular end-product.

Revised 10.1 effective January 1, 2004

10.2 Many of the sections make reference to one or more performance tests on the end-product that can be used to determine the acceptability of a material where performance does not meet the minimum requirements.

ELECTRICAL

11 Comparative Tracking Index (CTI)

11.1 A risk of fire or electric shock may develop within electrical equipment as a result of electrical tracking of insulating material that is exposed to various contaminating environments and surface conditions. The comparative tracking index provides a comparison of the performance of insulating materials under wet and contaminated conditions.

11.2 Comparative tracking index (CTI) is determined by the method described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A, Recommended Method for Determining the Comparative Tracking Index of Solid Insulating Materials Under Moist Conditions. The comparative tracking voltage is an index and is not directly related to the suitable operating voltage in actual service.

11.3 The comparative tracking index provides an indication of the relative track resistance of the material at voltages up to 600V. The incline plane tracking test described in Inclined Plane Tracking, Section 15 should be used to evaluate the track resistance of materials at voltages that are greater than 600V.

11.4 As indicated in Table 8.1, an insulating material that is in contact with or close proximity to less than 0.8 mm (1/32 inch) uninsulated live parts or such parts and dead metal parts that may be grounded in service or any surface exposed to contact, shall have a maximum CTI PLC of 4 for indoor equipment in a relatively clean environment; a maximum CTI PLC of 3 is required for most outdoor and indoor equipment that may be exposed to moderate contaminate environments; a maximum CTI PLC of 2 is required for equipment that is likely to be subjected to severe contaminate environments.

Exception: In lieu of demonstrating compliance through the use of a pre-selection test, The Proof Tracking Test, described in IEC 112, can be conducted on a portion of the product enclosure to determine compliance with the specified Proof Tracking Index (PTI) specified in the end-product standard.

11.5 The values specified in Table 8.1 are for reference, higher or lower values may be required in specific end-product equipment.

12 Dielectric Strength

12.1 If an enclosure of polymeric material is depended upon to serve as electrical insulation, it shall have a dielectric strength in the use thickness at 50 – 60 Hz of at least 5000 V, rms, both after conditioning for 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 \pm 5 percent relative humidity and after conditioning for 96 hours to moist air having a relative humidity of 90 \pm 5 percent at a temperature of $35.0 \pm 2.0^{\circ}\text{C}$ ($95.0 \pm 3.6^{\circ}\text{F}$).

13 High Current Arc Resistance to Ignition (HAI)

13.1 A polymeric material shall resist ignition to the levels shown in Table 8.1 when tested in accordance with the High Current Arc Resistance to Ignition Test described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

Exception: The high current arc resistance-to-ignition test need not be conducted for non-hazardous energy circuits.

13.2 During the test the electrodes are to be positioned as follows:

- a) If the live parts are located less than 0.8 mm (1/32 inch) from the polymeric material, then the electrodes are to be positioned on the surface of the material, or
- b) If the source of an arc for an arcing live part is located at least 0.8 mm (1/32 inch) but less than 12.7 mm (1/2 inch) from the material, the electrodes are to be positioned above the surface of the material at a distance equal to the minimum distance between the arc source and the material used in the application.

13.3 A material that does not comply with 13.1 may be evaluated by using the power (current, voltage, and power factor) of the circuit in the end product by conducting a short-circuit test using the procedures described in 50.1 (Arcing Test).

13.4 There shall be no ignition;

- a) Within 15 arcs for materials classed V-0,
- b) Within 30 arcs for materials classed V-1 and V-2, or
- c) Within 60 arcs for materials classed HB.

In addition, there shall not be a permanent carbon conductor path judged by application of a dielectric voltage-withstand potential between the live part and the adjacent part of different potential indicated in 50.1, as required in the end-product standard but not less than 1000 volts, 60 hertz for 1 minute.

13.5 The end-product tests described in 50.1 may show that the shape, over-surface distance, thickness, heat sinks, and the like, provide more ignition resistance than occurred as a result of testing plastic specimens using the method described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

14 Hot-Wire Ignition (HWI) – Abnormal Overload Test or Glow-Wire End-Product Test

14.1 General

14.1.1 Materials that do not comply with the minimum hot-wire ignition levels shown in Table 8.1 or may be evaluated by an abnormal overload test or the glow-wire end-product test. The abnormal overload test passes abnormal currents through current-carrying members as described in 14.2. Over-current values and times are shown in Table 51.1 as a function of the circuit over-current device rating. The glow-wire end-product test subjects the end-product to an electrically heated wire. Glow-wire test temperatures are shown in Table 75.1 and are determined by end-product use.

Exception No. 1: The abnormal overload test or the glow-wire end-product test need not be conducted if the electrically live parts are spaced 0.8 mm (1/32 inch) or more from the material.

Exception No. 2: The abnormal overload test or the glow-wire end-product test need not be conducted for non-hazardous energy circuits.

Revised 14.1.1 effective June 1, 2004

14.2 Abnormal overload test

14.2.1 A polymeric material shall be capable of withstanding the temperatures that are generated during or as a result of the abnormal overload test described in 51.1 and 51.2 without ignition.

14.2.2 If there is no overcurrent protective device as part of the equipment or it cannot be relied upon, evaluation shall be based upon the available energy to the end-product using percentages of the intended branch-circuit overcurrent device, but not less than a 30 A normal-acting protective device.

14.2.3 If the overcurrent protective device is part of the equipment, it shall be relied upon only if the protector is not user-serviceable unless substitution of a higher-rated protector value is prevented by keying, other constructional features, or if there is a permanent marking limitation.

14.3 Glow-wire end-product test (GWEPT)

Revised Title of 14.3 effective June 1, 2004

14.3.1 A polymeric material shall be capable of withstanding the effects of an electrically heated wire as described in 75.1.1 – 75.6.2. The specimen is considered to have satisfactorily withstood the glow-wire end-product test if either:

- a) There is no ignition, or
- b) All flaming and glowing of the specimen, the parts surrounding the specimen, and (if a material was used other than the tissue paper/pinewood board) the flaming particle indicator, ceases within 30 ± 1 s after removal of the glow-wire. The results are not acceptable if the specimen, the parts surrounding the specimen, or the flaming particle indicator are completely consumed.

15 Inclined Plane Tracking

15.1 The inclined plane tracking test described in the Standard for Polymeric Materials – Short Term Property Evaluations, (UL 746A), provides an indication of the relative track resistance of the material at voltages that are greater than 600 V, but less than 35 kV.

15.2 As indicated in Table 8.1, an insulating material that is in contact with or close proximity to uninsulated live parts or such parts and dead metal parts that may be grounded in service or any surface exposed to contact, shall not track beyond one inch in less than 300 minutes using the time-to-track method. For materials subjected to voltage stresses between 5,001 V and 35 kV.

Exception: A minimum 60 minute time-to-track time is required for materials subjected to voltage stresses between 601 V and 5 kV.

16 Volume Resistivity

16.1 The volume resistivity of the polymeric material shall not be less than:

- a) 50 megohm-centimeters after conditioning for 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 ± 5 percent relative humidity.
- b) 10 megohm-centimeters immediately after exposure for 96 hours to moist air having a relative humidity of 90 ± 5 percent at a temperature of $35.0 \pm 2.0^{\circ}\text{C}$ ($95.0 \pm 3.6^{\circ}\text{F}$).

Exception: A material that exhibits a low value of volume resistivity may be considered acceptable, provided that the equipment complies with the leakage-current requirements in 16.3.

16.2 The volume resistivity is to be determined in accordance with the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

16.3 The leakage current of a cord-connected appliance rated for a nominal 120 V supply when tested in accordance with 74.1 – 74.5 shall not be more than:

- a) 0.5 mA for an ungrounded (two-wire) portable, stationary, or fixed appliance,
- b) 0.5 mA for a grounded (three-wire) portable appliance, and
- c) 0.75 mA for a grounded (three-wire) stationary or fixed appliance employing a standard attachment plug rated 20 A or less.

16.4 Leakage current refers to all currents, including capacitively coupled currents, which may be conveyed between exposed conductive surfaces of an appliance and ground or other exposed conductive surfaces of an appliance.

FLAMMABILITY

17 Flammability – 12 mm Flame

17.1 When equipment is tested as described in 52.1 – 52.6, the material shall not flame for more than 1 minute after two 30-second applications of a test flame, with an interval of 1 minute between applications of the flame. The results are not acceptable if the sample is completely consumed.

Exception: Parts that are molded from materials that are classed as 5VA, 5VB, V-0, V-1, or V-2 by the vertical burning test described in UL 94, need not be subjected to the flammability test described in 52.1 – 52.6.

18 Flammability – 3/4-Inch Flame

18.1 When equipment is tested as described in 53.1 – 53.5, the material shall not flame for more than 1 minute after two 30-second applications of a test flame, with an interval of 1 minute between applications of the flame. The results are not acceptable if the sample is completely consumed.

Exception: Parts that are molded from materials that are classed as 5VA, 5VB, V-0, V-1, or V-2 by the vertical burning test described in UL 94, need not be subjected to the flammability test described in 53.1 – 53.5.

19 Flammability – 127 mm (5 Inch) Flame

19.1 Except as indicated in the Exception to 54.1, when equipment is tested as described in 54.1 – 54.5, all of the following results shall be obtained:

- a) The material shall not continue to burn for more than 1 minute after the fifth 5-second application of the test flame, with an interval of 5 seconds between applications of the flame,
- b) Flaming drops or flaming or glowing particles that ignite surgical cotton 305 mm (12 inch) below the test specimen shall not be emitted by the test sample at any time during the test, and
- c) The material shall not be destroyed in the area of the test flame to such an extent that the integrity of the part is affected with regard to containment of fire.

Exception: Parts that are molded from materials that are classed as 5VA by the five inch burning test described in UL 94, need not be subjected to the flammability tests described in 54.1 – 54.5.

20 Enclosure Flammability – 746-5VS

20.1 Test criteria

20.1.1 When tested as described in 55.1.1 – 55.2.7, coated materials shall:

- a) Not have any plaques which burn with flaming or glowing combustion, or both, for more than 5 seconds after removal of the flame.
- b) Not have any plaques which drip flaming particles that ignite the dry absorbent surgical cotton located 305 mm (12 inch) below the test plaque.
- c) Not have any plaques that exhibit burn through.

20.1.2 If only one plaque from a set of five fails to comply with the requirements, another set of five plaques is to be tested. All plaques from this second set shall comply with the requirements in order for the material in that thickness to be considered acceptable.

21 Enclosure Flammability – Large Surface Area Considerations

21.1 A polymeric material enclosure or part outside of the enclosure having in any single unbroken section, a projected surface area greater than 0.93 m² (10 ft²) or a single linear dimension greater than 1.83 m (6 ft) shall have a maximum flame-spread rating of 200 as determined by the requirements for tests for surface burning characteristics of building materials, UL 723, or the radiant-panel test in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94, may be used optionally to determine the flame spread characteristics of the material, in noncritical applications.

Exception No. 1: If the projected surface area is broken with a minimum 305 mm (12 inch) fire separation, or the polymeric material is used for the enclosure of equipment not permanently affixed to a power supply source, then the radiant panel test described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94, shall be used to determine the flame spread characteristics of the material. The material shall have a maximum flame spread index of 200 as determined by the radiant panel test.

Exception No. 2: These requirements are not applicable to detachable parts such as vacuum cleaner hoses or wands nor is it applicable to the power-supply cord whether detachable or nondetachable.

22 Flame-Retardant Coatings

22.1 General

22.1.1 The requirements in Section 22 and the test method in Section 56 cover flame-retardant coatings that are employed on enclosures of polymeric materials in order to comply with the 20 mm, 127 mm, or 746–5 VS Flammability Tests in Sections 18, 19, and 20, respectively.

22.1.2 The coating/enclosure material combination may be considered equivalent to a material possessing the applicable minimum flammability classification providing:

- a) The basic polymeric enclosure material is classified at least HB by the test method described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94,
- b) Samples of the base material with the flame-retardant coating properly applied are found to comply, both before and after conditioning, with the minimum flammability classification required for the end-product application,
- c) Additional coatings applied to the enclosure for coloring, finish, and the like do not adversely affect the complete enclosure with respect to its flammability classification,
- d) The addition of the flame-retardant coating does not adversely affect the insulating characteristics of the enclosure (this characteristic may not be a factor in all equipment designs) and
- e) An acceptable process-control program is to be established by the manufacturer at the location where the flame-retardant coating is applied to the enclosure material.

22.1.3 In all cases, the flame-retardant coating shall comply with the requirements of Sections 22 and 56 and the base enclosure material shall be acceptable for the temperatures that are encountered in the end product.

22.1.4 The tests in 22.2 apply to the coating/material interface when it is exposed to a maximum use temperature of 60°C (140°F). When the maximum use temperature exceeds 60°C (140°F), the acceptability of the coating/material interface is to be determined by a long-term thermal aging study of the critical properties. These properties include flammability, adhesion, flexural strength and izod impact. Refer to the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B, for thermal-aging test procedures.

22.2 Test criteria

22.2.1 After completing the conditioning described in 56.1.1.1, 56.1.2.1 and 56.1.3.1, the flammability classification shall be the same or better than that of the unconditioned samples.

22.2.2 After completing the conditioning described in 56.1.1.2, 56.1.2.1 and 56.1.3.1, the specimens shall not exhibit any evidence of flaking, cracking or blistering of the coating after the test described in 56.2.3.

22.2.3 After completing the conditioning described in 56.1.1.3, the izod impact and/or flexural strength properties shall not be reduced by more than 50 percent from the as-received (unconditioned) value.

22.2.4 The surface resistivity of the specimens shall be at least 1 megohm after the test described in 56.1.2.2 and 56.2.4. If the resistivity is not essentially the same for each of the conditionings, the conditioning described in 56.1.2.2(b) shall be continued for a longer period of time to demonstrate that the asymptotic resistivity is at least 1 megohm.

MECHANICAL

23 Crushing Resistance

23.1 Equipment that is not easily moved from one place to another during intended use, shall withstand a 1 minute application of the crushing force described in 57.1 without resulting in any of the following:

- a) Reduction of spacings below the minimum acceptable values.
- b) Making bare live parts or internal wiring accessible to contact.
- c) Such breakage, cracking, rupture, and the like as to produce an adverse effect on the insulation.
- d) Producing any other condition that would increase the likelihood of electric shock or fire, or both, during use of the equipment.

24 Resistance to Impact

24.1 The equipment shall withstand the impact described in 58.1 or 58.3 (whichever is applicable) without occurrence of any of the following:

- a) Making uninsulated live parts accessible to contact (use the accessibility probe of the product standard for this evaluation);
- b) Producing a condition that might affect the mechanical performance of the equipment; or
- c) Producing a condition that would increase the likelihood of an electric shock.

24.2 With reference to 24.1(b), cracking or denting of the enclosure is not to affect the function of any safety controls or constructional features such as thermostats, overload protective devices, waterseals, or strain relief. Cracking or denting of the enclosure is not to result in exposure of moving parts capable of causing injury to persons.

24.3 With reference to 24.1(c), the equipment is to comply with the dielectric voltage-withstand requirements applicable to the equipment after being subjected to the impact.

DIMENSIONAL CHANGE OF POLYMERIC PARTS

25 Creep

25.1 Creep is defined as the dimensional change with time of a material under load. If a constant load is applied to a polymeric material, the initial dimensional change is predictable from the stress-strain modulus but, with time, the dimensional change continues to increase slowly until a point is reached at which the elongation suddenly again increases or rupture occurs. From experience, these effects are considered not to apply to rigid thermoset materials.

25.2 Creep can occur when a polymeric part is under any type of long-time loading (for example, bending, compressive, or tensile loading, leaf or coil springs, or gravity).

25.3 Where the end-product application is such that the creep is self-relieving, 300 hours at normal operating temperature, and with maximum loading, determines the effect of plastic flow. Creep is to be considered self-relieving if the stress is eliminated due to the change in dimension of the polymeric part.

25.4 Where the end-product application is such that the creep is not self-relieving, such as when the external force is provided by gravity, 1,000 hours at normal operating temperature, and with maximum loading, determines the effect of plastic flow.

25.5 As a result of the above, there is to be no warpage or distortion that:

- a) interferes with normal operation or servicing,
- b) results in accessibility of live parts,
- c) reduces electrical spacings below the level necessary to comply with the applicable requirements pertaining to dielectric strength and leakage current,
- d) for outdoor-use products, exposes internal components to the effects of weathering or water, and

e) results in an unacceptable reduction of the pressure involved in metal-to-metal joints relied upon for safety including joints providing a bonding path and joints serving as current carrying parts.

25.6 Manufacturer's data concerning the creep characteristics of material can be used for creep analysis. In applying such data, consideration is to be given to the similarity of the test method to the end application. The more nearly alike the environmental conditions, the geometry of the parts, and the stresses of both the test and the end application, the more valid a prediction can be made based on the test data.

PERMANENCE

26 Permanence

26.1 General

26.1.1 The tests indicated in 26.2.1 – 26.4.1 may be used as a relative measure of a material's ability to withstand relief of molding stresses while under the influence of elevated temperature. In applications where the distortion temperature is less than the values indicated in the applicable table, the results may be judged on the basis of the results of the mold stress-relief distortion test referred to in 31.1.

26.2 Vicat softening point

26.2.1 The vicat softening point shall be at least 25°C (45°F) greater than the use temperature but not less than 105°C (221°F) when tested in accordance with the Standard for Polymeric Materials – Short Term Property Evaluations (UL 746A).

26.3 Heat deflection temperature

26.3.1 The heat deflection temperature shall be at least 10°C (18°F) greater than the use temperature but not less than 90°C (194°F) when tested in accordance with the Standard for Polymeric Materials – Short Term Property Evaluations (UL 746A).

26.4 Ball pressure temperature

26.4.1 The ball pressure temperature shall be at least equal to 40°C (72°F) greater than the use temperature minus the ambient temperature, but not less than 95°C (203°F), when tested in accordance with the Standard for Polymeric Materials– Short Term Property Evaluations (UL 746A).

27 Ultraviolet Light Exposure

27.1 A polymeric material used for the enclosure of electrical equipment that will be exposed to an UV weathering source shall be acceptably resistant to degradation when exposed to the test described in 59.1.1 – 59.2.11.

27.2 Table 27.1 summarizes the minimum property retention limitations after UV conditioning. The flammability classification of base samples of the material in the thinnest part thickness, and any color under consideration, shall not be reduced as a result of 720 hours of twin enclosed carbon-arc (ASTM G151 and G153) or 1000 hours of xenon-arc (ASTM G151 and G155), weatherometer conditioning. The average physical property values after UV conditioning shall not be less than 70 percent of the unconditioned value when the standardized small-scale physical tests indicated in Table 27.1 are performed. See 59.2.3.

Exception No. 1: Where it is not practical to conduct the Tensile, Izod, or Charpy impact test using the standard specimens, the procedure of 59.2.7 – 59.2.11 and the impact equipment of Figures 59.1 and 59.2 may be used on representative sections of the equipment's enclosure.

Exception No. 2: If the impact value for an enclosure material that has been tested in accordance with the requirements in this section has exhibited less than 70 percent retention but at least 25 percent retention of the impact property, it is considered acceptable provided that all of the following results are obtained:

a) The unconditioned equipment complies with the resistance to impact requirement levels shown in Table 27.2, and

b) The specimens exposed to the 720 hour twin enclosed carbon-arc or 1000 hour xenon-arc UV conditioning have retained at least 80 percent of the 360 hour twin enclosed carbon-arc or 500 hour xenon-arc UV conditioning impact level. As an alternative, this UV conditioning may be conducted for a longer period of time in 360 hour (carbon-arc) or 500 hour (xenon-arc) increments providing the final exposure impact level is not less than 80 percent of the previous increment's impact level.

Table 26.1
Minimum property retention limitations after ultraviolet light and water immersion conditioning

Property	Ultra-violet light ^a	Water immersion ^b
Flammability Classification	Unchanged	Unchanged
Tensile or Flexural Strength ^c	70 Percent	50 Percent
Tensile, Izod or Charpy Impact ^c	70 Percent	50 Percent
^a 720 hours twin enclosed carbon-arc or 1000 hours xenon-arc exposure. See 59.1.1 – 59.2.11. ^b 7 days at 70°C. See 60.1. ^c For functional support, the test methods are tensile strength and flexural strength. For Impact Resistance the test methods are Tensile, Izod, or Charpy impact. See Table 59.1.		

Table 26.2
Unconditioned ball-impact requirements for equipment exposed to UV radiation^a

Percent retention of property after UV conditioning ^b	Impact level for ball-impact test on unconditioned specimens foot-pounds (joules)
70 or more	5.0 (6.8)
50 – 69	10.0 (13.6)
25 – 49	20.0 (27.2)
Less than 25	Not acceptable
^a For other than easily moved hand held and counter supported equipment. ^b 720 hours twin enclosed carbon-arc or 1000 hours xenon-arc exposure or after the final exposure if longer exposures are conducted as described in 27.2.	

28 Water Exposure and Immersion

28.1 General

28.1.1 A polymeric material used for the enclosure of electrical equipment intended for outdoor installation shall not be appreciably degraded because of exposure to water. The acceptability of the material's resistance to such degradation may be judged by the procedure described in 28.1.2, 60.1 and 60.2.

28.1.2 Table 27.1 summarizes the minimum property retention limitations after exposure to water. The flammability classification of base samples of the material in the thinnest part thickness, and any color under consideration shall not be reduced as a result of the 7 day at 70°C (158°F) conditioning described in 60.1. The average physical-property values after the water exposure and immersion conditioning shall not be less than 50 percent of the original (non-water conditioned) value when the standardized small-scale physical test in Table 27.1 are performed.

28.2 Dimensional change

28.2.1 If a material exhibits a dimensional change greater than 2.0 percent after immersion for 168 hours in distilled water, as described in the Standard for Polymeric Materials— Short Term Property Evaluations (UL 746A), end-product tests are to be performed to determine if the change in dimension created by the service environment might cause:

- a) A reduction of spacings leading to excessive leakage currents,
- b) A dielectric breakdown after such exposure, or
- c) Warpage or swelling that might impair the acceptable operation of the equipment.

SPECIAL END-USE CONSIDERATIONS

29 Abnormal Operation

29.1 When tested as described in 61.1, there shall not be ignition of the material, exposure to live parts, nor glowing or flaming of the combustible material that the equipment is placed on or is draped. Warping, shrinkage, expansion, or cracking of the material is not objectionable provided that there is no ignition of the combustible material indicators in proximity to the enclosure.

30 Severe Conditions

30.1 The no-load current input to the equipment that has completed the procedures described in 62.1 without burning out electrically shall not be greater than 150 percent of the no-load current input of the equipment, measured on an unconditioned sample.

30.2 Burnout of the equipment during the conditioning described in 62.1 shall not result in:

- a) Flaming of the enclosure that persists for more than 1 minute, or
- b) Ignition of the white tissue paper or cheesecloth indicators in proximity to the enclosure.

THERMAL

31 Mold Stress-Relief Distortion

31.1 Conditioning of the equipment as described in 63.1 or 63.2, whichever is applicable according to Table 4.1, shall not cause softening of the material as determined by handling immediately after the conditioning, nor shall there be shrinkage, warpage, or other distortion as judged after cooling to room temperature, that results in any of the following:

- a) Reduction of spacings between uninsulated live parts of opposite polarity, uninsulated live parts and accessible dead or grounded metal, uninsulated live parts and the enclosure below the minimum acceptable values.
- b) Making uninsulated live parts or internal wiring accessible to contact, or defeating the integrity of the enclosure so that acceptable mechanical protection is not afforded to internal parts of the equipment.
- c) Causing a condition that results in the equipment not complying with the power-supply-cord strain-relief requirements, if applicable.
- d) Causing interference with the intended operation or servicing of the equipment.

Exception: The conditioning described in 63.1 and 63.2 is not required for rigid thermosetting materials or for low-pressure foamed molded parts.

Revised 31.1 effective June 1, 2004

32 Input to Motor

32.1 After being conditioned as described in 63.2 and when operated at no-load and rated voltage, as indicated in 65.1, the equipment shall have an input current no more than 150 percent of the no-load current measured during the applicable input test conducted on an unconditioned sample.

33 Strain-Relief Test after Mold Stress-Relief Distortion

33.1 After the test samples have cooled to room temperature following the oven conditioning described in 63.1 or 63.2 (whichever is applicable according to Table 4.1), the sample shall be subjected to the strain-relief test and shall comply with the requirements applicable to the equipment.

Revised 33.1 effective June 1, 2004

34 Temperature Considerations— General

34.1 It has been shown that material properties are a continuous function of temperature and time. At relatively low temperatures the tendency for degradation is reduced while at elevated temperatures, there is a more rapid degradation. A single temperature rating can not be assigned to a material, since such a rating would be a function of: the generic material type, additives, and fillers; the properties required and levels of stress encountered in the application; the duty cycle and the effect of part failure with regard to increasing the risk of electrical shock, fire or injury to persons.

34.2 Table 34.1 and Sections 35 – 38 describe different approaches for assigning temperature limits to materials based upon the knowledge of the material and its application. Any of these methods may be employed to assign a temperature limit to the material. Temperature Considerations – Illustrative Example, Section 69, contains an illustrative example that describes how temperature considerations are applied.

34.3 Temperature Excursions Beyond the Maximum Use Temperature, Section 40, describes a procedure for determining an equivalent temperature where temperature excursions above the material's temperature limit are encountered or where the material may be exposed to cyclic temperatures during intended operation.

Table 34.1
Methods of material temperature limit considerations

Section	Methods of temperature limits	Synopsis of method
35	Functional-use thermal index	This is the most general approach for assigning material temperature limits. It does not require any information on the material formulation. The temperature limit is determined by the function that the material serves in specific applications.
36	Generic thermal index	Maximum temperature limits based upon the material's generic type (chemical structure, fillers, additives, etc.); no knowledge of the material's end-use function is required.

Table 34.1 Continued on Next Page

Table 34.1 Continued

Section	Methods of temperature limits	Synopsis of method
37	Relative thermal index	Material temperature limits based upon a relative comparison of long term critical material property retention with those of a control material having an acceptable field service history under various conditions and applications. Basic knowledge of the material's end use function is required.
38	Relative thermal capability	Material temperature limit based upon the material's use in a specific application where required material property stress levels are identified and controlled. This is the most specific approach for assigning material temperature limits. It requires knowledge of long term thermal aging properties (see Relative Thermal Index, Section 37) before this procedure may be used.

35 Functional-Use Temperature Indices

35.1 Table 35.1 presents a list of maximum temperature limits that have been assigned to materials regardless of generic type when used in applications that perform a specific function.

35.2 The functional-use temperature index is independent of thickness and pigmentation.

35.3 A polymeric material having a maximum operating temperature that does not exceed the value tabulated in Table 35.1 is acceptable if tests on finished parts, before and after mold-stress conditioning (refer to the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A) with regard to electrical and physical properties and a 7 day conditioning at 70°C (158°F) or 10°C (18°F) higher than the maximum use temperature whichever is higher, for flammability properties, demonstrate compliance with the requirements for the application in equipment. If the requirements after conditioning are the same as the requirements as-received and the test results are acceptable, the as-received tests can be waived.

Exception No. 1: The mold-stress conditioning is not required for rigid thermosetting materials and low-pressure foamed molded parts.

Exception No. 2: Flammability conditioning is not required if both of the following conditions are met:

- a) The material does not exhibit a reduction in its flame-resistance properties as a result of long-term thermal aging (refer to the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B).*
- b) The thermal-aging program used for such determination included specimens having a thickness equal to or less than the wall thickness of the finished part.*

35.4 A polymeric material having a maximum use operating temperature in excess of the value shown in Table 35.1, shall be considered acceptable if it complies with the requirements for Generic Thermal Indices (Section 36), Relative Thermal Indices, (Section 37), or Relative Thermal Capability (Section 38).

Table 35.1
Maximum temperature limits of polymeric material based upon its functional end-use application

Application Area	Temperature limits of polymeric material°C (°F)	
	Enclosure	Other Parts ^a
Portable, attended, intermittent-duty household equipment	80 (176)	65 (149)
All other portable equipment	65 (149)	65 (149)
All other equipment	50 (122)	50 (122)

^a Decorative parts are exempt from these temperature limits.

36 Generic Thermal Indices

36.1 Table 36.1 presents a list of materials, that have been assigned a generic thermal index based upon acceptable service experience, the chemical structure of the material, and a knowledge of the performance of the material in tests of insulating systems and electrical equipment. The assigned generic thermal index is applicable to each member of the generic material group.

36.2 Except for materials specified in Table 36.1, the generic thermal index of a material is to be considered 50°C (122°F).

36.3 Except for materials specified in Table 36.1, the generic thermal index of a material is independent of thickness and pigmentation.

36.4 A polymeric material having a maximum use operating temperature that exceeds the values shown in Table 36.1, shall be considered acceptable if it complies with the requirements for Functional-Use Temperature Indices (Section 35), Relative Thermal Indices (Section 37), or Relative Thermal Capability (Section 38).

Table 36.1
Relative thermal indices based upon past field-test performance and chemical structure^a

Material	ISO Designation	Generic thermal index, °C
Polyamide (Type 6, 11, 12, 66, 610, or 612 nylon) ^b	(PA)	65
Polycarbonate ^b	(PC)	80
Polyethylene terephthalate – molding resin ^b	(PETP)	75
film (0.25 mm, 0.010 inch)	(PETP)	105
Polybutylene (polytetramethylene) terephthalate ^b	(PBTP)	75
Polyphenylene oxide ^j	(PPE – PS)	65
Polypropylene ^{b,h}	(PP)	65
Polyetherimide ^g	–	105
Polyphenylene Sulfide	(PPS)	130
Polymide film (0.25 mm, 0.010 inch max)	(PI)	130
Molded phenolic ^c	(PF)	150
Molded melamine ^{c,d} and molded melamine/phenolic ^{c,d} – specific gravity <1.55		130

Table 36.1 Continued on Next Page

Table 36.1 Continued

Material	ISO Designation	Generic thermal index, °C
specific gravity ≥ 1.55		150
Polytetrafluoroethylene	(PTFE)	180
Polychlorotrifluoroethylene	(PCTFE)	150
Fluorinated ethylene propylene	(FEP)	150
Urea Formaldehyde ^c	(UF)	100
Acrylonitrile– butadiene – styrene ^b	(ABS)	60
Silicone – molding resin ^{c,d}		150
Silicone rubber –		
molding resin	(SIR)	150
Room-temperature vulcanizing or heat-cured paste	(RTV)	105
Epoxy –	(EP)	
molding resin ^{c,d}		130
powder coating materials		105
casting or potting resin ^{b,i}		90
Molded diallyl phthalate ^{c,d}		130
Molded unsaturated polyester ^{c,d}	(UP)	
alkyd (AMC), bulk (BMC),		
dough (DMC), sheet (SMC),		
thick (TMC), and pultrusion		
molding compounds	(electrical)	105 ^e
	(mechanical)	130
Liquid crystalline thermotropic aromatic polyester ^h	(LCP)	130
Ligno-cellulose laminate		60
Vulcanized fiber		90
Cold-molded phenolic, melamine or		
melamine-phenolic compounds ^d –		
specific gravity < 1.55		130
specific gravity ≥ 1.55		150
Cold-molded inorganic		200
(hydraulic-cement, etc.) compounds –		
Integrated mica, resin-bonded–		
epoxy, alkyd or		
polyester binder		130
phenolic binder		150
silicone binder		200

^a Generic thermal index is for homopolymer resins only unless a specific copolymer or blend is indicated. In the case of alloys, the lowest generic index of any component shall be assigned to the composite.

^b Includes glass-fiber reinforcement and/or talc, asbestos, mineral, calcium carbonate, and other inorganic fillers.

^c Includes only compounds molded by high-temperature and high-pressure processes such as injection, compression, pultrusion, and transfer molding and match-metal die molding; excludes compounds molded by open-mold or low-pressure molding processes such as hand lay-up spray-up, contact bag, filament winding, rotational molding, and powder coating (fluidized bed, electrostatic spray, hot dip, flow coating).

^d Includes materials having filler systems of fibrous (other than synthetic organic) types but excludes fiber reinforcement systems using resins that are applied in liquid form. Synthetic organic fillers are to be considered acceptable at temperatures not greater than 105°C.

^e Except 130°C generic thermal index if the material retains at least 50% of its unaged dielectric strength after a 504-hour exposure at 180°C in an air circulating oven. Specimens are to be tested in a dry, as molded, condition. Specimens that are removed from the oven are to be cooled over desiccant for at least 2 hours prior to testing.

Table 36.1 Continued on Next Page

Table 36.1 Continued

Material	ISO Designation	Generic thermal index, °C
^f Includes only wholly aromatic liquid crystalline thermotropic polyesters; wholly aromatic polyester/amides and wholly aromatic polyester/ethers; excluding amorphous, lyotropic and liquid crystalline aliphatic-aromatic polyesters which are aliphatic in the backbone chain or main chain, and substituted aromatic polyesters (except for methyl or aromatic). ^g Includes only polyetherimide molding resin. ^h Includes polypropylene copolymers containing not more than 25% ethylene comonomer, by weight. ⁱ Multi-part liquid epoxy materials incorporating acid anhydride or aromatic amine curing agents receive a 130°C generic thermal index. ^j Includes only those polyphenylene oxide materials in which the PPO component is not less than 30% of the total composition by weight and that have a Heat Deflection Temperature of at least 70°C at a load (fiber stress) of 1.80 M Pa (264 psi).		

37 Relative Thermal Index

37.1 The relative thermal index of a material is to be based upon an evaluation of long-term thermal-aging data obtained under a program described in the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B.

37.2 Essentially, the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B, procedure allows the thermal-aging characteristics of a material to be determined by measuring the changes in its properties to a predetermined level by aging at each of several elevated temperatures, plotting the logarithm of time at each temperature against the reciprocal of absolute temperature using the best-fit straight line by the least squares method of regression analysis. The time-temperature relationship may be expressed as:

$$\ln(t) = A + B/T$$

in which:

A is Constant (frequency factor)

B is Activation (Energy Constant)

T is Absolute temperature, °K (°C + 273.16) and

ln is Natural logarithm

37.3 A comparison of the thermal aging characteristics of the candidate material against those of a concurrently tested control material having proven field service, provides a means for estimating a relative thermal index level where the candidate material is expected to have an acceptable field service history. For each material, a number of relative thermal indices can be established, each index being related to a specific property, color, and thickness of the material.

37.4 A polymeric material having a use operating temperature higher than the applicable relative thermal index, shall be considered acceptable if it complies with the requirements for Functional Use Temperature Indices (Section 36) or Relative Thermal Capability (Section 38).

38 Relative Thermal Capability

38.1 The Relative Thermal Capability (RTC) of an organic insulating material relates to that maximum operating temperature at which the material can be expected to maintain critical properties and perform its intended mechanical or electrical function to the extent consistent with acceptable operation over the maximum expected life of the equipment. In general, the Relative Thermal Index (RTI) (see Section 37) may be used to represent the RTC provided consideration is given to the character of the critical (mechanical, electrical, impact) properties and minimum thickness of the material. A material may operate at a higher temperature than the RTI if the design of the equipment will allow a greater amount of thermal degradation. For such a material, it is necessary to define the following with respect to the critical property, using data obtained during a thermal endurance study in accordance with the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B:

- a) The resulting RTI from the UL 746B program.
- b) Life Equation Slope Parameter (B) as defined by 37.2.
- c) Excess performance factor (P) determined from the level of critical property in excess of the acceptable known value.
- d) Property – Time degradation characteristics for one or more aging temperatures, which can be used to determine that time (t_1) required for the property to degrade to a reduced fraction (f) of the unaged value, as well as normal end-of-life time (t_0).

38.2 The Relative Thermal Capability of a material cannot be measured by a superficial examination of material properties, as with a short term performance profile and long term relative thermal index. To determine the Relative Thermal Capability of a material, the level or value of the critical property of the material must be measured to determine the amount of degradation permissible in a specific end application.

38.3 An evaluation of the functional usage of the complete appliance or device is necessary in order to determine acceptable operating temperatures for materials used in appliances and equipment.

38.4 The thermal capability of a specific part is related to the thermal, mechanical, and electrical demands upon it in a particular application. Therefore, the results of a thermal capability evaluation for a given part and application cannot be extended to another end-use application even though the same material, and in some cases, the same part may be used.

38.5 The results of accelerated thermal aging studies, conducted in accordance with the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B, provide the basic information needed for the assessment of the thermal capability for a material used in a specific application.

38.6 The Relative Thermal Capability is calculated using the following equation:

$$RTC = [1 / (RTI + 273.16) - (\log F) / B]^{-1} - 273.16$$

in which:

F is the ratio t_1/t_0 determined at one or more aging temperatures,

t_0 is the normal end-of-life time based on 50 percent degradation, and

t^1 is calculated in terms of the reduced property percent, $f = 50 / P$.

P is the excess performance factor (see Relative Thermal Capability, Section 66).

38.7 Since the resulting RTC is based solely on projected long term effects resulting from slow chemical degradation reactions, it is essential to further determine that the RTC will not result in unacceptable performance with respect to any other short term-thermal effects, such as softening, warping, excessive weight loss indicating rapid decomposition, and the like. These effects are relatively easy to assess since by their very nature they will occur and can be measured in a short term time using standardized material tests. For the thermoplastics, the softening temperature limit can usually be determined by the results of either the Heat Deflection Under Load, Ball Pressure, or Vicat tests. For thermosets, Thermogravimetric Analysis or other equivalent analytical tests can usually determine the temperature of the onset of rapid decomposition.

38.8 If the resulting RTC calculated for one critical property (for example, mechanical with impact) results in an increased temperature limit above the RTI for another critical property (for example, mechanical without impact or electrical), then the latter property RTI must then be considered a limiting temperature which might in turn be considered as the basis for computing another RTC.

39 Relative Thermal Capability (Alternate)

39.1 The relative thermal capability of a material relates to its ability to perform the intended mechanical or electrical function in equipment when exposed to temperatures in excess of the relative thermal index, to the extent that short term thermal (softening) and long term exposure (thermal degradation) at the use temperature does not affect its functional usage. Evaluation of the relative thermal capability of the material used in a specific application requires the use of thermal aging on actual parts, using the procedures described in this section.

39.2 The thermal capability of a material cannot be measured by a simple examination of material properties. Rather, the thermal capability of a material may only be determined by analyzing measured changes in material property levels after exposure to elevated temperatures over a period of time, along with a thorough knowledge of the functional requirements for the material in the specific application.

39.3 An evaluation of the functional usage of the complete appliance or device is necessary in order to determine acceptable operating temperatures for materials used in appliances and equipment.

39.4 The thermal capability of a specific part is related to the thermal, mechanical, and electrical demands upon it in a particular application. Therefore, the results of a thermal capability evaluation for a given part and application cannot be extended to another end-use application even though the same material, and in some cases, the same part may be used.

39.5 The results of accelerated thermal aging studies, conducted in accordance with the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B, provide the basic information needed for the assessment of the thermal capability for a material used in a specific application.


39.6 Using the materials long term heat aging data from the most critical property required by the application, a relative thermal capability profile line can be generated having the same slope as the best fit material endurance profile line but displaced such that it passes through the point defined by the maximum use application temperature and the correlation factor. The example in Temperature Considerations – Illustrative Example (Alternate RTC), Section 70 (shown in Figure 39.1) graphically explains how the relative thermal capability profile line is constructed and used. Employing inverse temperature-logarithm hours graph paper, draw the relative thermal endurance profile of the material property under study and then generate the relative thermal capability profile by:

- a) Drawing a vertical line at the assigned relative thermal index of the material, (1) until it intersects the materials relative thermal endurance profile, (2). The value of the ordinate at this point of intersection is an estimate of the correlation factor, (A).
- b) Drawing a horizontal line at the point of intersection, (2), to the maximum part temperature point (3).
- c) Drawing a line parallel to the thermal endurance profile that passes through the maximum part temperature point, (3), determined in step B.

39.7 In order to be considered acceptable following the conditioning described in 62.1 and 62.2, the material shall not;

- a) Have its flammability classification changed below an acceptable level,
- b) Have a reduction in mechanical or electrical strength, or
- c) Become softened to a value where:
 - 1) The material cannot provide mechanical support of electrical conductors and parts, or
 - 2) There is a reduction of spacings between uninsulated live parts of opposite polarity, uninsulated live parts and accessible dead or grounded metal below the minimum acceptable values, or
 - 3) Uninsulated live parts or internal wiring are accessible to contact, or
 - 4) A condition is created that results in the equipment not complying with the power supply cord strain relief requirements, if applicable, or
 - 5) Interference with the operation or servicing of the equipment occurs.

Figure 39.1
Determination of the relative thermal capability

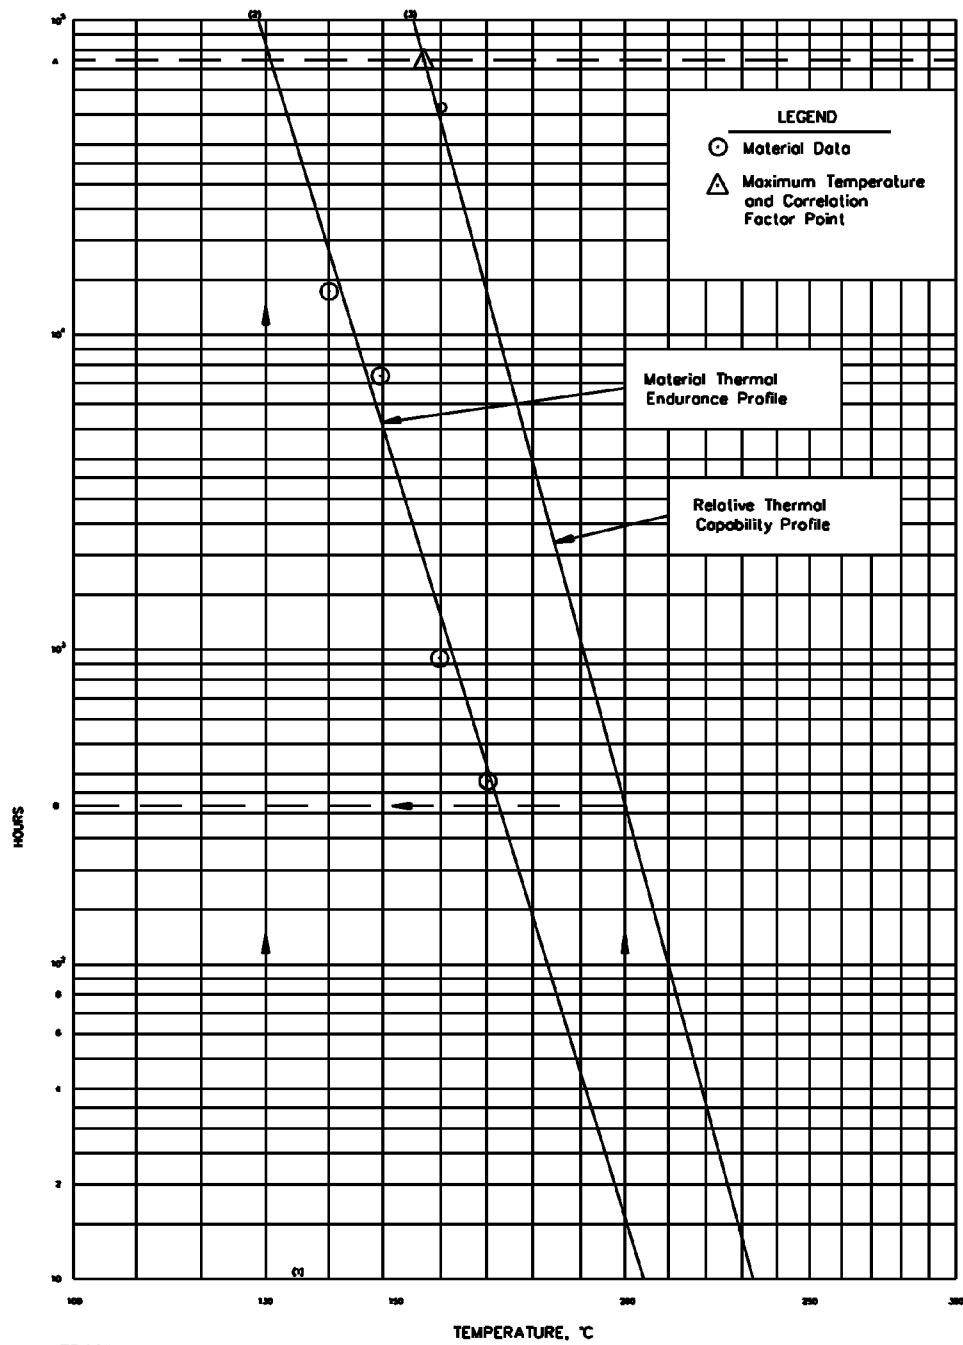

A= 73,969 hours
B= 330 hours

S2004

40 Temperature Excursions Beyond the Maximum Use Temperature

40.1 Electrical products and equipment may be subjected to cyclic or transient temperature peaks during or immediately after intended operation. Short term temperature excursions, above the limits established for the appropriate thermal indices, may be acceptable for specific applications and constructions provided that long term aging information is available for the material (see Relative Thermal Index, Section 37). It may be necessary to use the procedure described in Relative Thermal Capability, Section 38, in order to determine acceptability.

40.2 For example, a heating appliance employing an automatic resettable thermostat will generally experience the greatest temperature excursion during the first few cycles of operation. During subsequent operations, the thermostat will clear the circuit at lower peak temperatures due to an increase in the ambient air temperature.

40.3 For most applications, the product will experience exponential temperature rises and decays where the duration and time constants depend upon the geometry of the product, the thermal masses of the parts, and the magnitude of the heat source.

40.4 In such cases where the Time – Temperature profile is well defined, and can be approximated by a “step” function consisting of a series of (i) constant temperature exposures, each at temperature (T_i) for a fraction of the total cycle time (f_i), then an equivalent continuous use temperature (T_{eq}) can be defined as:

$$T_{eq} = -B / [\ln (\text{Sum on } i \text{ of } (f_i \times \text{Exp}(-B/5_i)))]$$

in which:

T_{eq} is the Equivalent continuous use temperature in °K.

B is the Activation energy constant of the Arrhenius relationship having the form $L = Ae^{B/T}$ (see Relative Thermal Index, Section 37).

$B = - E / R$, where:

E is the activation energy in electron volts

R is the Boltzmann constant, 8.62×10^{-5}

\ln is the Natural logarithm

$\text{Exp}(\)$ is the The number e ($=2.718284$) raised to the power of the exponent ().

The approximating step function shall be constructed to exceed the actual measured characteristic at all points as illustrated in the example indicated in Temperature Excursions Beyond the Maximum Use Temperature, Section 68.

SPECIALIZED APPLICATIONS

41 General – Adhesives

41.1 These requirements cover adhesives used to bond structural parts, where the adhesive is relied upon to maintain the proper functioning of the device with regard to the likelihood of electric shock, fire, and injury to persons.

41.2 These requirements do not cover adhesives used in the manufacture of printed-wiring boards that are covered by the Standard for Printed-Wiring Boards, UL 796.

41.3 Adhesive joints shall comply with the requirements indicated in Function Analysis, Section 42, Program of Investigation, Section 43, and Adhesives – Specialized Applications, Section 71.

42 Function Analysis

42.1 The properties required of the adhesive shall be based upon an analysis of the function or functions of the adhesive in the end-product equipment. Bond strength (or impact strength) shall be considered as a critical property and the evaluation test method shall be selected to relate as closely as possible to the end-product use.

43 Program of Investigation

43.1 End-product evaluation

43.1.1 The strength of an adhesive joint used to position critical parts in electrical equipment shall be capable of withstanding at least four times the maximum force in the as received condition that might be applied to the joint in the end application.

43.2 Effect of environmental conditions

43.2.1 The initial values of the critical properties shall be determined by tests representing as closely as possible actual use conditions. The effect of environmental conditions that might be experienced during normal and reasonably foreseeable abuse of the end product shall be determined. The same evaluation test method shall be used after exposure of the specimens to environmental conditions representative of such use. A critical property shall not be reduced more than 50 percent.

44 Coil Forms

44.1 Materials used in an insulation system shall be evaluated with respect to the Standard for Polymeric Materials – Coil Forms, UL 1692.

45 Conformal Coatings

45.1 This section and Conformal Coating Test, Section 72 cover requirements for conformal coatings used on printed-wiring boards in electrical equipment where electrical spacings are insufficient between uninsulated live parts of opposite polarity or between such parts and accessible dead metal parts. The coatings are used as a protective covering against environmental conditions and are also used instead of electrical spacings to increase the dielectric voltage withstand capability between lands (traces) on a printed-wiring board.

45.2 The printed-wiring board with conformal coating is to be evaluated in accordance with the Standard for Printed-Wiring Boards, UL 796, and is to comply with the requirements indicated in Conformal Coating Test, Section 72, relative to temperature, solder conditions, conductor size, and adhesion to the base material under the conditions encountered in the end-use application.

45.3 Testing is to be conducted on each type of industrial laminate material that is to be considered. Flammability tests are to be conducted in accordance with the Standard for Flammability of Plastic Materials for Use in Appliances and Devices, UL 94, for each type of industrial laminate to be considered. Unclad specimens are to be prepared that contain the minimum and maximum conformal coating thickness, inks and solder resists if employed. The coating shall not degrade the flammability classification of the base material.

Exception No. 1: Testing of ANSI FR-4 is considered representative of ANSI FR-5, G-10, G-11, CEM-1, and CEM-3 materials.

Exception No. 2: Testing of ANSI XXXPC is considered representative of ANSI X, XP, XPC, XX, XXP, XXX, and XXXP materials.

Exception No. 3: Testing of ANSI GPO-2 is considered representative of ANSI GPO-3 material.

Exception No. 4: Flammability tests are not required if the base industrial laminate material is classed HB.

METALLIZED PARTS

46 General

46.1 Ductile Coatings, Section 47, Brittle Coatings, Section 48, and Tape Adhesion Test, Section 73 describe requirements to evaluate metallized processes such as those for use in the fabrication of decorative parts or enclosures treated with a conductive surface coating intended for electromagnetic interference (EMI) suppression.

46.2 The purpose of these requirements is to evaluate the integrity of the bond between the substrate material and the metallized coating by means of bond strength testing (ductile coatings) or by tape adhesion tests (brittle coatings). The results of these adhesion tests can then be used to judge the acceptability of metallized processes in the end-product where loss of the bond strength might result in electric shock, fire, or both.

46.3 These requirements do not cover the additional considerations which must be given a metallized part used as a conducting or bonding member.

46.4 Ductile Coatings, Section 47 and Brittle Coatings, Section 48 describe the performance requirements for metallized parts. Section 47 describes the performance requirements for ductile coatings, such as those found on metallized parts using electroplated ductile copper. Sections 48 and 73 describe the performance requirements for brittle coatings, such as those found on electromagnetic interference (EMI) shields using vacuum-applied foil, arc- or flame-spray coatings, conductive paints, cathode sputtering, and the like.

47 Ductile Coatings

47.1 The process shall produce metallized parts that are free of wrinkles, pits, blisters, corrosion, and the like that could result in electric shock, fire, or injury to persons, and have a minimum average unconditioned bond strength between the metal surface and the plastic of 36 g/mm (2 lb/inch) of width. The bond strength is to be determined by tests on copper-plated plaques in accordance with the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A. Results obtained on 0.05 mm (0.002 inch) ductile copper can be considered representative of lesser thicknesses.

47.2 The process shall produce metallized parts that are capable of withstanding accelerated aging and environmental cycling conditions without a reduction in average bond strength less than 18 g/mm (1 lb/inch) of width. See items 73.5 (b), (c) and (d) for conditioning requirements.

47.3 If the contemplated end use of metallized parts is such that the temperatures to which these parts are to be subjected exceeds the lowest assigned RTI for the applicable critical material properties, the metallized plastic shall be investigated in accordance with the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B. The primary property for evaluating the thermal degradation shall be bond strength. A reduction of 50 percent of the original bond-strength property shall be considered the end-point criteria.

48 Brittle Coatings

48.1 The metallic coating process shall produce metallized parts that are free of wrinkles, pits, blisters, corrosion, and the like that can result in electric shock, fire, or injury to persons; and have acceptable cohesion and adhesion between the metallized coating and between the metallized coating and the substrate as received and after conditioning. The adhesion strength is to be determined by tests on the flat sections of the test specimens. The tape adhesion test shall be conducted in accordance with the Standard Methods for Measuring Adhesion by Tape Test, ASTM D 3359, Method A or B and Section 73.

48.2 If the contemplated end use of metallic coated parts is such that the temperatures to which these parts are to be subjected exceeds the lowest assigned RTI for the applicable critical material properties, the metallized plastic shall be investigated in accordance with the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B. The primary property for evaluating the thermal degradation shall be adhesion by means of the tape adhesion test. After aging, the coatings shall comply with the requirements in 48.1.

TEST PERFORMANCE

49 General

49.1 Details

49.1.1 Values of voltage and current are root-mean-square (rms) values, unless otherwise stated.

49.1.2 An appliance having both alternating-current and direct-current ratings is to be tested with the appliance connected to an alternating-current supply and again to a direct-current supply, unless it can be established that one test results in the maximum operating conditions.

49.2 Voltmeters

49.2.1 Unless otherwise indicated, voltage measurements shall be made with a voltmeter having a resistance of 2000 ohms per volt minimum for potentials of 1000 V or less and 20,000 ohms per volt minimum for potentials of more than 1000 V.

49.2.2 The open-circuit voltage measurement used in conjunction with a leakage- or shock-current determination is to be made with a measuring instrument that has an input impedance that does not significantly affect the circuit being measured. In general, a measuring instrument with a minimum input impedance of one megohm is to be used.

49.2.3 A lead, connector, or component that is accessible during intended operation or user-servicing is to be connected for intended operation and is to be arranged in any position likely after user-servicing.

49.3 Cheesecloth indicators

49.3.1 Cheesecloth used for tests shall be bleached cotton cheesecloth, running 26 – 28 m²/kg mass (14 – 15 yd²/lb mass) and having what is known to the trade as a count of 32 by 28.

49.3.2 Tests involving cheesecloth are to be conducted in a room free of drafts.

49.4 Supply-circuit voltage and frequency

49.4.1 All operational tests shall be conducted with the appliance connected to a supply circuit of rated frequency and voltage.

49.4.2 An appliance with one supply circuit frequency rating is to be tested at that frequency. An appliance with a dual frequency rating is to be tested at 60 Hz if 60 Hz is included in the rating and may also be tested at the second frequency if such testing is warranted.

49.4.3 An appliance that can be operated from alternate power supplies, such as dc adapters, car batteries, and the like, is to be tested with those supplies if such testing is considered necessary.

49.4.4 Unless otherwise specified in the individual test method, the standard atmospheric conditions surrounding the specimens or appliance prior to and during the test shall be between 15°C and 35°C (59°F and 95°F) and between 45 percent and 75 percent relative humidity.

50 End-Product Arc Resistance Test

50.1 The current for the arcing test is to be based upon the maximum normal load-current rating that the equipment draws and minimum power factor. The voltage used for the test is to be equal to the available voltage at the live part. The arc is to be established between the live part and any adjacent part where breakdown is likely to occur. The arc is to be used to attempt to ignite materials forming parts of the enclosure or to ignite materials located between the parts of different potential. The arc is to be established by means of a copper or stainless steel conductive probe. The conductive probe is to be used to create arc tracking or a carbon build-up across the surface of the insulating material at the rate of 40 arc separations per minute. (A rate of 30 arc separations per minute may be used if 40 arc separations per minute is not practical.)

51 Abnormal Overload Test

51.1 To determine whether a polymeric material complies with 14.2, separate samples of the equipment or representative sections of the equipment are to be loaded to each indicated overcurrent values for the corresponding test times indicated in Table 51.1. Except as indicated in 51.2, only one sample need be subjected to each of the specified overload tests.

51.2 If a current-carrying conductor within any of the samples of the equipment opens before the minimum test time tabulated in Table 51.1 has elapsed without resulting in ignition, then three samples are to be loaded to a lesser current value, as indicated in 51.6 (b) – (i), for the minimum test time tabulated in Table 51.1 corresponding to the largest overload value that does not result in a current-carrying conductor opening before the minimum test time, or 7 hours.

51.3 For the sequence of tests described in 51.6, if the abnormal overload test continues for 7 hours or the full test time indicated in Table 51.1 without a winding or an acceptable protective device opening, the remaining tests need not be conducted. For example, if the test described in 51.6(a) continues for 7 hours using 110 percent of the overcurrent protective device rating load (namely 33 A for a 30 A overcurrent protective device), 60 minutes using 135 percent of the overcurrent protective device rating load (namely 40.5 A), and 2 minutes using 200 percent of the overcurrent protective device rating load (namely 60 A) the tests described in (b) – (i) need not be conducted.

51.4 The overload current value indicated in 51.6 (b) – (h) is the lesser overload value tabulated in Table 51.1 that resulted in a current-carrying conductor opening before the minimum test time. The base test current value indicated in 51.6 (b) – (i) is the largest overload value tabulated in Table 51.1 that does not result in a current-carrying conductor opening before the minimum test time. If a current-carrying conductor opens before 7 hours within the sample loaded to 110 percent of the overcurrent protective device rating, then the base test current value shall be the rated current of the equipment.

Table 51.1
Abnormal overload test

Overcurrent protective device rating	110-percent current ^a	Minimum test time	
		135-percent current	200-percent current
0 – 30 amperes	7 hours	60 minutes	2 minutes
31 – 60	7	60	4
61 – 100	7	120	6
101 – 200	7	120	8
201 – 400	7	120	10
^a The test may be terminated when the temperatures have stabilized, indicating that ultimate results have already been achieved.			

51.5 For the purpose of illustration, consider the following two examples:

Example A:

Given the rated current of the equipment under evaluation is 10 A and the overcurrent protective device rating is 30 A, one sample of the equipment, designated sample 1, is then loaded to 33 amperes for 7 hours, another sample, designated sample 2, is loaded to 40.5 A for 60 minutes and a third sample, designated sample 3, is loaded to 60 A for 2 minutes.

If sample 1 continues for 7 hours and sample 2 continues for 60 minutes without a current-carrying conductor opening, but a current-carrying conductor in sample 3 opens before 2 minutes, then 3 samples of the equipment, designated samples 4, 5 and 6, are subjected to the abnormal overload test for 60 minutes loaded to the base test current (40.5 A) plus 75 percent of the difference between the overload current (60 A) and the base test current (40.5 A), namely 55 A.

Example B:

Given the same information as Example A above except in samples 1, 2 and 3 a current-carrying conductor opens before 7 hours, 60 minutes and 2 minutes respectively, then 3 samples of the equipment, designated samples 4, 5, and 6, are subjected to the abnormal overload test for 7 hours loaded to the base test current (rated current of 10 A) plus 75 percent of the difference between the overload current (33 A) and the base test current (10 A), namely 27.25 A.

51.6 Loading the equipment shall not result in ignition, undue distortion, or melting of the material being evaluated under any of the following conditions:

- a) Loading the equipment to the specified overload values per Table 51.1.
- b) Loading the equipment to a current equal to the base test current plus 75 percent of the difference between the overload current and the base test current.
- c) Loading the equipment to a current equal to the base test current plus 50 percent of the difference between the overload current and the base test current.
- d) Loading the equipment to a current equal to the base test current plus 25 percent of the difference between the overload current and the base test current.
- e) Loading the equipment to a current equal to the base test current plus 20 percent of the difference between the overload current and the base test current.
- f) Loading the equipment to a current equal to the base test current plus 15 percent of the difference between the overload current and the base test current.
- g) Loading the equipment to a current equal to the base test current plus 10 percent of the difference between the overload current and the base test current.
- h) Loading the equipment to a current equal to the base test current plus 5 percent of the difference between the overload current and the base test current.
- i) Loading the equipment to the base test current.

51.7 To determine whether a material complies with the requirement in 51.2, three samples of the complete equipment are to be subjected to each condition described in 51.6 (a) – (i).

51.8 For the loading conditions, a variable resistor is to be connected in series with the equipment. The tests described in 51.6 (a) – (i) are to be continued for the test times indicated in 51.6 and Table 51.1, unless a current-carrying conductor within the equipment or an acceptable protective device opens in a shorter time. In conducting the tests described in 51.6 (b) – (i), the variable resistance load is to be adjusted to the required value as quickly as possible and readjusted, if necessary, 1 minute after application of voltage to the equipment.

51.9 For equipment that is provided with a built-in, acceptable, protective device (as indicated in 14.2.3) the tests described in 51.6 (a) – (h) are to be concluded if the protective device opens the circuit. If the protective device is of the automatic recycling type, the test is to be continued for the full time indicated in Table 51.1.

51.10 Samples for the abnormal overload tests are to be prepared as follows:

- a) The complete equipment is to be placed on a white tissue paper covered softwood surface.
- b) The equipment is to be connected to a suitable supply circuit, that may use a low voltage current source, fused at not less than 30 A.

51.11 Each abnormal-overload test is to be continued until ignition of the material occurs, the circuit under test burns open, or until the test time indicated in 51.2 and Table 51.1 is achieved.

52 Flammability – 12 mm Flame Test

52.1 Three samples of the complete equipment or three test specimens of the part thereof shall be subjected to this test. Consideration is to be given to leaving in place components and other parts that might influence the performance. The test samples are to be conditioned in a full draft circulating air oven for 7 days at 10°C (18°F) greater than the maximum use temperature but not less than 70°C (158°F) in any case prior to testing, the samples are to be conditioned for a minimum of 4 hours at 23.0 ±2.0°C (73.4 ±3.6°F) and 50 ±5 percent relative humidity. The samples are then to be tested as described in 52.2 – 52.6.

Exception: The test may be conducted on only unconditioned test samples if both of the following conditions are met:

- a) The material does not exhibit a reduction in its flame-resistance properties as a result of long-term thermal aging.*
- b) The thermal-aging program used for such determination included specimens having a thickness equal to or less than the wall thickness of the polymeric part.*

52.2 Three samples of the part are to be subjected to the flame test described in 52.5. In the performance of the test, the equipment is to be supported in its intended operating position in a draft-free location. Consideration is to be given to leaving in place components and other parts that might influence the performance. The flame shall be applied to an inside surface of the sample at a location judged to be likely to become ignited because of its proximity to a source of ignition. For example, motor or transformer windings, brush holders, switch contacts, terminals, connections, and so forth are considered possible sources of ignition. If more than one part is near a source of ignition, each sample shall be tested with the flame applied to a different location.

Exception: The flame may be applied to the outside surface of an enclosure, if the equipment is of the encapsulated type or of such size that the flame cannot be applied inside.

52.3 With reference to 52.2, the sections most likely to be ignited should be considered as those adjacent to arcing parts, or other possible sources of ignition.

52.4 The burner to produce the flame consists of a tube at least 35 mm long having an inside diameter of 0.5 ± 0.1 mm and an outer diameter not exceeding 0.9 mm. The burner shall not have air ports. The gas supply shall be butane having a purity of at least 95 percent, and a heat content of approximately 122 MJ/m³.

52.5 With the axis of the burner in a vertical position, the gas supply is to be adjusted so that a 12 mm flame is produced. Two 30 second applications of the tip of the flame are to be made to each section of the equipment, selected as indicated in 52.3, with a 1 minute interval between the applications.

52.6 If one sample from a set of three does not comply with 17.1, an additional set of 3 samples shall be tested. All samples from the second set shall comply with 17.1 to be considered acceptable.

53 Flammability – 3/4 Inch Flame Test

53.1 Three samples of the complete equipment or three test specimens of the part thereof shall be subjected to this test. Consideration is to be given to leaving in place components and other parts that might influence the performance. The test samples are to be conditioned in a full draft circulating air oven for 7 days at $10 \pm 1^\circ\text{C}$ or $(18 \pm 2^\circ\text{F})$ greater than the maximum use temperature but not less than 70°C (158°F) in any case prior to testing, the samples are to be conditioned for a minimum of 4 hours at $23.0 \pm 2.0^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and 50 ± 5 percent relative humidity. The samples are then to be tested as described in 53.2 – 53.6.

Exception: The test may be conducted on only three unconditioned test samples if both of the following conditions are met:

- a) The material does not exhibit a reduction in its flame-resistance properties as a result of long-term thermal aging.*
- b) The thermal-aging program used for such determination included specimens having a thickness equal to or less than the wall thickness of the polymeric part.*

53.2 Three samples of the part are to be subjected to the flame test described in 53.5. In the performance of the test, the equipment is to be supported in its normal operating position in a draft-free location. Nonpolymeric portions of the part in contact with or fastened to the polymeric portions are not to be removed and, insofar as possible, the internal mechanism of the equipment is to be in place. The flame shall be applied to an inside surface of the sample at a location judged to be likely to become ignited because of its proximity to a source of ignition. For example, motor or transformer windings, brush holders, switch contacts, terminals, connections, and so forth are considered possible sources of ignition. If more than one part is near a source of ignition, each sample shall be tested with the flame applied to a different location.

Exception: The flame may be applied to the outside surface of an enclosure if the equipment is of the encapsulated type or of such size that the flame cannot be applied inside.

53.3 With reference to 53.2, the sections most likely to be ignited should be considered as those adjacent to coil windings, splices, open-type switches, or arcing parts.

53.4 A laboratory type burner having a tube with a length of 100 ± 10 mm (3.94 ± 0.39 inch) and an inside diameter of 9.5 ± 0.3 mm (0.374 ± 0.012 inch) is to be used. The barrel is not to be equipped with an end attachment, such as a stabilizer. The burner shall be in compliance with ASTM D5025, Specification for a Laboratory Burner Used for Small-Scale Burning Tests on Plastic Materials. Adjust the burner to produce a blue flame 20 ± 1 mm high ($3/4$ inch nominal). The flame is obtained by adjusting the gas supply and air ports of the burner until a 20 ± 1 mm ($3/4$ inch nominal) yellow-tipped blue flame is produced. Increase the air supply until the yellow tip just disappears. Measure the height of the flame again and readjust it if necessary. The test flame shall be calibrated in accordance with ASTM D 5207, Standard Practice for Calibration of 20 mm and 125 mm Test Flames for Small-Scale Burning Tests on Plastic Materials at least once a month and when the gas supply is changed, test equipment is replaced, or when data is questioned.

53.5 Two 30 second applications of the tip of the flame are to be made to each section of the equipment selected as indicated above, with 1 minute intervals between the applications. A supply of technical-grade methane gas (minimum 98 percent pure) is to be used with a regulator and meter for uniform gas flow. The methane gas supply to the burner shall be arranged as in Figure 53.1 and adjusted to produce a gas flow rate of 105 ml/min with a back pressure less than 10 mm of water. See ASTM D 5207. The flow meter shall be a rotameter calibrated in accordance with ASTM D 3195, Practice of Rotameter Calibration with correlation curves appropriate for the gas, or a mass flow meter with ± 2 percent accuracy.

Exception: Natural gas having a heat content of approximately 37 MJ/m^3 (1000 Btu/ft^3) at 23°C (73.4°F) has been found to provide similar results; however, technical grade methane shall be used in case of dispute.

53.6 If one sample from a set of three does not comply with 18.1, an additional set of three samples shall be tested. All samples from the second set shall comply with 18.1 to be considered acceptable.


54 Flammability – 127 mm (5 inch) Flame Test

54.1 Three samples of the complete equipment or three test specimens of the part thereof shall be subjected to this test. Consideration is to be given to leaving in place components and other parts that might influence the performance. The test samples are to be conditioned in a full draft circulating air oven for 7 days at 10°C (18°F) greater than the maximum use temperature but not less than 70°C (158°F) in any case. Prior to testing, the samples are to be conditioned for a minimum of 4 hours at $23.0 \pm 2.0^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and 50 ± 5 percent relative humidity. The flame shall be applied to an inside surface of the sample at a location judged to be likely to become ignited because of its proximity to a source of ignition. If more than one part is near a source of ignition, each sample shall be tested with the flame applied to a different location.

Exception: The test may be conducted on only three unconditioned test samples if both of the following conditions are met:

- a) The material used does not exhibit a reduction in its flame-resistance properties as a result of long-term thermal aging.*
- b) The thermal-aging program used for such determination included specimens having a thickness equal to or less than the wall thickness of the polymeric part.*

Figure 53.1
Burner supply arrangement

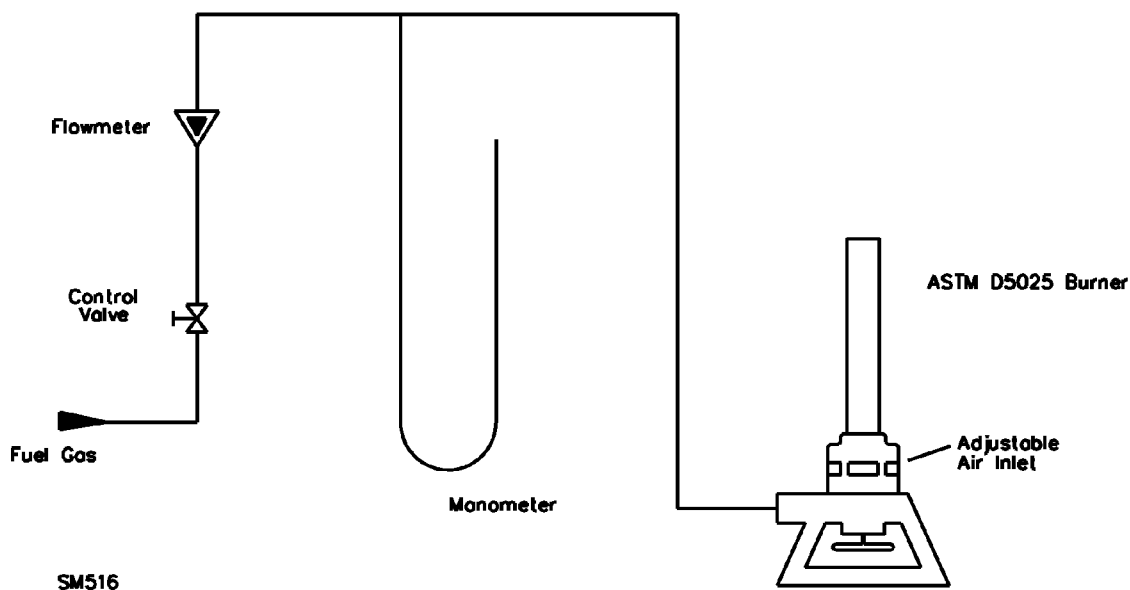

54.2 The three test samples are to result in the acceptable performance described in 19.1. If one sample does not comply, the test is to be repeated on a set of three new samples with the flame applied under the same conditions as for the unsuccessful sample. If all the new specimens comply with 19.1 the material is acceptable.

54.3 The laboratory burner, adjustment and calibration are to be identical to that described for the 3/4-inch flame test except:

- 1) The gas flow rate shall be 965 ml/min with a back pressure of 125 ± 25 mm water, and
- 2) The flame height shall be adjusted, with the burner vertical in a darkened room, to an overall height of approximately 125 ± 10 mm and the height of the inner blue cone to 40 ± 2 mm.

54.4 When a complete enclosure is used to conduct the flame test, the sample is to be mounted as intended in service, if it does not impair the flame testing, in a draft-free test chamber, enclosure, or laboratory hood. A layer of absorbant 100 percent cotton is to be located 305 mm (12 inch) below the point of application of the test flame. The 127 mm (5 inch) flame is to be applied to any portion of the interior of the part judged as likely to be ignited (by its proximity to live or arcing parts, coils, wiring, and the like) at an angle of approximately 20 degrees in so far as possible from the vertical so that the tip of the blue cone touches the specimen. The test flame is to be applied to three different locations on each of the three samples tested. A supply of technical-grade methane gas is to be used with a regulator and meter for uniform gas flow.

Exception No. 1: The flame may be applied to the outside of an enclosure if the equipment is of the encapsulated type or of such size that the flame cannot be applied inside.

Exception No. 2: Natural gas having a heat content of approximately 37 MJ/m³ (1000 Btu/ft³) at 23°C has been found to provide similar results and may be used.

54.5 The flame is to be applied for 5 seconds and removed for 5 seconds. The operation is to be repeated until the specimen has been subjected to five applications of the test flame.

55 Enclosure Flammability – 746-5VS Test

55.1 Apparatus

55.1.1 The apparatus employed is to consist of the following:

- a) A test chamber, enclosure, or laboratory hood free of induced or forced draft during tests.
- b) Laboratory Burner – A Bunsen or Tirrill burner having a tube with a length of 100 ± 10 mm (3.94 ± 0.39 inch) and an inside diameter of 9.5 ± 0.3 mm (0.374 ± 0.012 inch). The tube shall not be equipped with end attachments, such as a stabilizer.
- c) Ring Stand – A ring stand with clamps or the equivalent, adjustable for vertical positioning of specimens.
- d) Gas Supply – A supply of technical grade methane gas with regulator and meter for uniform gas flow. Natural gas having a heat content of approximately 37 MJ/m³ (1000 Btu/ft³) has been found to provide similar results. However, technical grade methane gas is to be used in case of question.
- e) Mounting Block – A block capable of positioning the burner at an angle of 20 degrees from the vertical.
- f) Stopwatch or other timing device.
- g) Desiccator containing anhydrous calcium chloride.
- h) Conditioning room or chamber capable of being maintained at $23 \pm 2^\circ\text{C}$ ($73 \pm 3.6^\circ\text{F}$) and a relative humidity of 50 ± 5 percent.
- i) Conditioning Ovens – A full draft circulating-air oven capable of being maintained at $70 \pm 1^\circ\text{C}$ ($158 \pm 1.5^\circ\text{F}$).
- j) A supply of dry absorbent surgical cotton.

55.1.2 Test plaques approximately 152×152 mm (6×6 inch) are to be tested in the minimum and maximum thicknesses covering the thickness range to be considered, with the minimum coating thickness. Plaques tested by this method are limited to a maximum thickness of 12.7 mm (0.50 inch). Plaques in intermediate thicknesses are also to be provided and may be tested if the results obtained on the minimum and/or maximum thickness indicate a need. Intermediate thicknesses should not exceed increments of 3.17 mm (0.125 inch).

55.2 Plaque conditioning

55.2.1 Sets of five test plaques are to be conditioned as follows:

- a) Sets are to be conditioned for at least 48 hours at a temperature of $23 \pm 2^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and a relative humidity of 50 ± 5 percent prior to testing.
- b) Sets are to be conditioned in a circulating-air oven for 168 hours at $70 \pm 1^{\circ}\text{C}$ ($158 \pm 1.8^{\circ}\text{F}$) and then cooled in a desiccator over anhydrous calcium chloride for at least 4 hours at room temperature prior to testing.

55.2.2 The burning test is to be conducted in a chamber, enclosure, or laboratory hood that is free of induced or forced draft. An enclosed laboratory hood, with a heat resistant glass window, and an exhaust fan for removing the products of combustion after the test, is recommended.

55.2.3 The burner is to be placed remote from the specimen, ignited, and in a darkened room, adjusted so that when the burner is in a vertical position, the overall height of the flame is 127 mm (5 inches), and the height of the inner blue cone is 38 mm (1-1/2 inches).

55.2.4 The test plaque is to be supported by a clamp on the ring stand in the vertical position, so that the plaque is 305 mm (12 inches) above a horizontal layer of dry absorbent surgical cotton. The burner is to be supported on the inclined plane of a mounting block so that the burner tube may be positioned at 20 degrees from the vertical.


55.2.5 The flame is then to be applied to the center of the coated side of the plaque at an angle of 20 degrees from the vertical, so that the tip of the blue cone touches the surface of the plaque. See Figure 55.1.

55.2.6 The flame is to be applied for 60 seconds and removed.

55.2.7 After the removal of the test flame, the following are to be observed and recorded:

- a) Duration of flaming plus glowing.
- b) Whether or not plaques dripped flaming particles which ignite cotton.
- c) Whether or not the flame burned through the plaque.

Figure 55.1

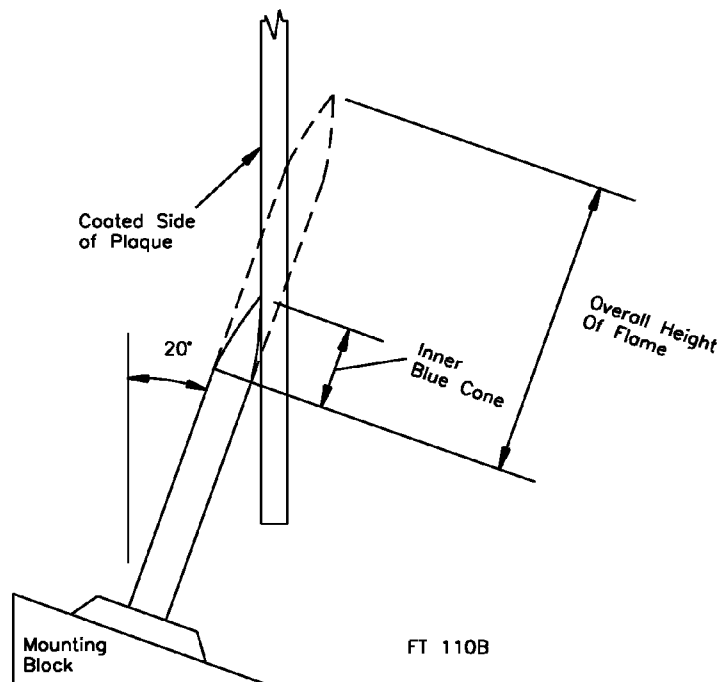

56 Flame-Retardant Coatings Test

56.1 Specimen conditioning

56.1.1 Effects of temperature

56.1.1.1 For flammability testing, 20 coated specimens, measuring 150 ± 5 mm by 150 ± 5 mm and provided in the use thickness shall be conditioned in a full-draft circulating oven for 800 hours at $90.0 \pm 2.0^\circ\text{C}$ ($194 \pm 3.6^\circ\text{F}$). An additional 20 specimens shall be conditioned in a full-draft circulating oven for 1500 hours at $80.0 \pm 2.0^\circ\text{C}$ ($176.0 \pm 3.6^\circ\text{F}$). Following the specified conditioning periods, the specimens are to be removed and conditioned for a minimum of 40 hours at $23.0 \pm 2.0^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and 50 ± 5 percent relative humidity prior to testing.

56.1.1.2 For adhesion testing 20 coated specimens, measuring 127 by 12.7 mm and provided in the use thickness shall be conditioned in a full-draft circulating oven for 800 hours at $90.0 \pm 2.0^\circ\text{C}$ ($194 \pm 3.6^\circ\text{F}$). An additional 20 specimens shall be conditioned in a full-draft circulating oven for 1500 hours at $80.0 \pm 2.0^\circ\text{C}$ ($176.0 \pm 3.6^\circ\text{F}$). Following the specified conditioning periods, the specimens are to be removed and conditioned for a minimum of 40 hours at $23.0 \pm 2.0^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) and 50 ± 5 percent relative humidity prior to testing.

56.1.1.3 For izod impact and/or flexural strength testing, 20 coated specimens, measuring 50.8 x 12.7 x 3.2 mm for izod impact and 127 by 12.7 by 3.2 mm for flexural strength, shall be conditioned in a full-draft circulating oven for 800 hours at $90.0 \pm 2.0^{\circ}\text{C}$ ($194 \pm 3.6^{\circ}\text{F}$). An additional 20 specimens shall be conditioned in a full-draft circulating oven for 1500 hours at $80.0 \pm 2.0^{\circ}\text{C}$ ($176.0 \pm 3.6^{\circ}\text{F}$). Following the specified conditioning periods, the specimens are to be removed and conditioned for a minimum of 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 \pm 5 percent relative humidity prior to testing.

56.1.2 Effects of humidity

56.1.2.1 For flammability and adhesion testing, 5 specimens of the dimensions noted above are to be conditioned for 108 ± 12 hours at $35.0 \pm 3.0^{\circ}\text{C}$ ($95.0 \pm 5.4^{\circ}\text{F}$) and 90 \pm 5 percent relative humidity. The specimens are to be tested immediately following the humidity exposure and shall comply with 22.2.1 and 22.2.2.

56.1.2.2 For surface resistivity testing, 3 specimens measuring 100 by 100 mm and provided in the use thickness, shall be subjected to each of the following:

- a) 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 \pm 5 percent relative humidity,
- b) 168 hours at $35.0 \pm 3.0^{\circ}\text{C}$ ($95.0 \pm 5.4^{\circ}\text{F}$) with 90 \pm 5 percent relative humidity,

The specimens are to be tested immediately following the humidity exposure and shall comply with 22.2.4.

56.1.3 Effects of environmental cycling

56.1.3.1 For flammability and adhesion testing, 5 specimens, of the dimensions noted above are to be subjected to three cycles of the following:

- a) 48 hours in a full-draft circulating air oven operating at $70.0 \pm 1.0^{\circ}\text{C}$ ($158.0 \pm 1.8^{\circ}\text{F}$),
- b) 48 hours at $35.0 \pm 3.0^{\circ}\text{C}$ ($95.0 \pm 5.4^{\circ}\text{F}$) with 90 \pm 5 percent relative humidity,
- c) 8 hours at $0.0 \pm 2.0^{\circ}\text{C}$ ($32.0 \pm 3.6^{\circ}\text{F}$),
- d) 4 hours of vibration at room temperature [approximately 25°C (75°F)], consisting of simple harmonic oscillating motion at right angles to the longitudinal plane of the specimen. The simple harmonic oscillating motion is to be 55 \pm 5 Hz with the peak deflection adjusted to result in a 1.5g acceleration.

56.2 Test methods

56.2.1 Flammability tests are to be conducted in accordance with Sections 18 – 20 of this standard, using the method most applicable for the application (refer to Section 4).

Note: Hardboard materials intended to be used as backing covers in television applications must comply with the requirements in Section 20, in accordance with the Standard for Audio/Video and Musical Instrument Apparatus for Household, Commercial and Similar General Use, UL 6500, Table 14.

56.2.2 Izod impact and flexural strength tests are to be conducted in accordance with Sections 12 and 14, respectively, of the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

56.2.3 The test method for the adhesion test is as follows. A set of 5 adhesion specimens are to be horizontally mounted and rigidly clamped 12.5 mm (0.5 inch) from one end. A load is to be applied at a rate of 12.3 – 50.8 mm per min (0.5 – 2.0 inches per min) 115 mm (4.5 inches) from the clamped end. The load is to be applied to cause a 25.4 mm (1.0 inch) vertical deflection upward, a 50.8 mm (2 in) vertical deflection downward, and a 25.4 (1 inch) vertical deflection upward, completing a cycle. Each test specimen is to be flexed for five complete cycles.

56.2.4 The surface resistivity is to be obtained using the test method in Section 20 of the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

56.3 Other considerations

56.3.1 Analytical tests are to be performed to determine the general composition of the material. The analytical tests may include but are not limited to:


- a) Percent Solids at 105°C (216°F) – Weighed samples (approximately 5 grams) of the coating in porcelain evaporating dishes are to be heated to constant weight at 105.0 ±1.0°C (221.0 ±1.8°F) in an electrical oven, cooled in a desiccator, and weighed. The percent solids can be calculated from the weight of the original samples and the weight of the residue after heating.
- b) Percent Ash (Dry-Basis) – The dried specimens of the coating remaining from the percent-solids test are to be used to determine the ash content as described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A. The dry-basis percent ash can be calculated from the weight of the dry sample after heating at 105.0 ±1.0°C (221.0 ±1.8°F) and the weight of the residue after ignition.
- c) Weight per Gallon – The weight per gallon of the coating is to be determined by means of a Baltimore weight-per-gallon cup.
- d) Qualitative Infrared Analysis – An infrared spectrum of the material is to be obtained as outlined in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.
- e) Qualitative X-Ray Analysis – The specimen is to be analyzed by X-ray for the presence of known fire-retardant elements (chlorine, bromine, phosphorus, and antimony).

57 Crushing Resistance Test

57.1 Three samples of equipment are to be supported on the mounting side by a fixed rigid supporting surface, in the position that is recommended by the manufacturer. Crushing force is to be applied to the exposed surfaces of the enclosure. The compression force is to be applied by flat surfaces each 102 by 254 mm (4 by 10 inches). Each force applicator is to exert 45.4 kg (100 lb) on the sample. As many applicators are to be applied as the sample can accommodate, up to a maximum of 8, based upon an arrangement of applicators as indicated in Figure 57.1.

Figure 57.1

Location of applicators for crush-resistance test

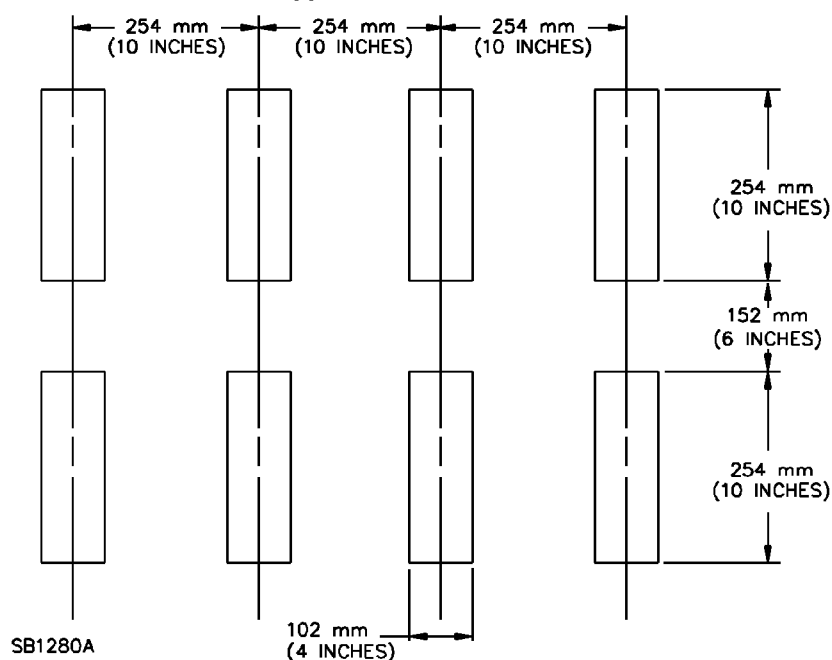

58 Resistance to Impact Test

58.1 Hand-supported equipment shall be subjected to the drop impact test described in (a) and (b).

a) Each of three samples of the equipment is to be dropped through 0.91 m (3 ft) to strike a hardwood surface in the position most likely to produce adverse results. The hardwood surface is to consist of a layer of nominal 25 mm (1 inch) tongue-and-groove oak flooring (actual size 18 by 57 mm or 3/4 by 2-1/4 inch) mounted on two layers of nominal 19 mm (3/4 inch) plywood. The assembly is to rest on a concrete floor or an equivalent nonresilient floor during the test.

b) Each sample is to be dropped three times so that, in each drop, the sample strikes the surface in a position different from those in the other two drops. Three samples shall be employed for the test; however, if the manufacturer so elects, fewer samples may be used in accordance with Figure 58.1. The overall performance is acceptable upon completion of any one of the procedures represented in that figure. If any sample does not comply on its first series of three drops, the results of the test are unacceptable.

58.2 Permanently wired equipment, or floor-supported equipment or equipment not likely to be dropped during intended use – such as counter-supported equipment – shall be subjected to the ball impact test described in 58.3.

58.3 Each of three samples of the appliance shall be subjected to a single impact of the value shown in Table 58.1 for the applicable equipment type, on any surface that can be exposed to a blow during intended use. This impact is to be produced by dropping a steel sphere, 50.8 mm (2 inches) in diameter, and weighing 0.535 kg (1.18 lb) mass from the height necessary to produce the specified impact as shown in Figure 58.2. The steel sphere shall strike the surface in a location different from those in the other two impacts. For surfaces other than the top on an enclosure, either the sample could be supported on the side and subjected to the ball impact mentioned above, or the steel sphere is to be suspended by a cord and swung as a pendulum, dropping through the vertical distance necessary to cause it to strike the surface with the specified impact as shown in Figure 58.2. Three samples shall be employed for the tests in the equipment restrained mode. However, if the manufacturer so elects, fewer samples may be used in accordance with Figure 58.1. The overall performance is acceptable upon completion of any one of the sequences represented in Figure 58.1.

58.4 In lieu of conducting the room temperature test described in 58.3, three specimens of equipment intended for outdoor use shall be cooled to a temperature of $\text{minus } 35.0 \pm 2.0^{\circ}\text{C}$ ($\text{minus } 31.0 \pm 3.6^{\circ}\text{F}$) and maintained at this temperature for 3 hours. Three specimens of indoor equipment intended for use in locations where the temperature may be less than actual room conditions, such as unheated warehouses or garages, – approximately 23°C (73°F) – shall be cooled to a temperature of $0.0 \pm 2.0^{\circ}\text{C}$ ($32.0 \pm 3.6^{\circ}\text{F}$) and maintained at this temperature for 3 hours. While the unit is still cold, the specimens shall be subjected to the impact described in 58.1 or 58.3 as applicable. The conditions for acceptable results are as indicated in 24.1.

Table 58.1
Ball impact requirements for equipment joules (foot-pounds)

Easily moved equipment		All other equipment
Counter-supported ^{a,b}	Floor-supported ^c	
1.02 (0.75)	6.8 (5.0)	6.8 (5.0)
^a Individual product requirements may require a higher level of impact resistance. ^b Counter-supported equipment is that which is typically supported by a counter, table, or bench during the performance of its intended electrically operated functions. Reference is to be made to the specific equipment's Use and Care Literature in establishing the intended electrically operated functions of the equipment. ^c Floor-supported equipment is that which is typically supported by the floor during the performance of its intended electrically operated functions. Reference is to be made to the specific equipment's Use and Care Literature in establishing the intended electrically operated functions of the equipment.		

Figure 58.1
Procedures for impact tests

Each series consists of three drops or one ball impact on each sample as applicable

Series Num- ber	Sample Number								
	1	2	3	1	2	3	1	2	3
1	↓ A	N	N	↓ A	N	N	↓ A	N	N
2	↓ A	N	N	↓ A	N	N	↓ U	↓ A	N
3	↓ A	N	N	↓ U	↓ A	N	↓ A	N	↓ U

Arrows indicate sequence of test procedure



A – Acceptable results from drop

U – Unacceptable results from drop

N – No test necessary

SA1162

Figure 58.2
Ball impact tests

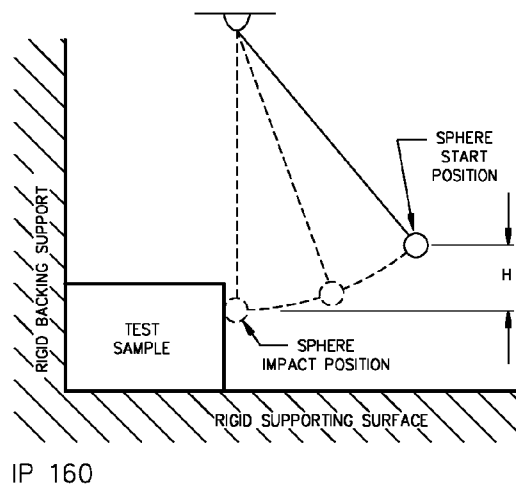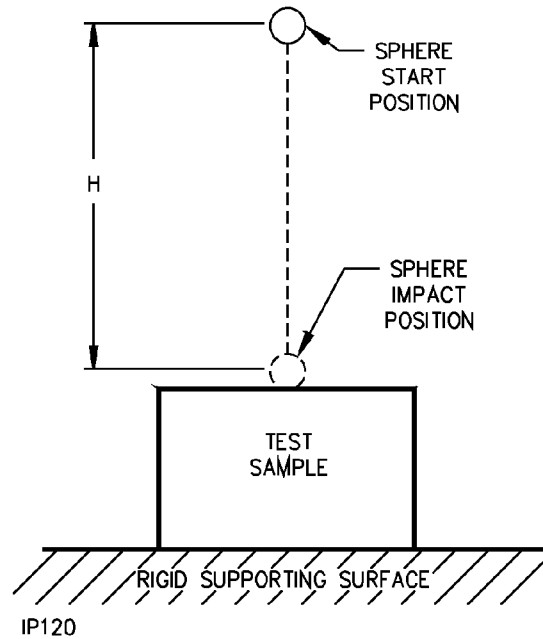

- 1 – H in Figure 58.2 indicates the vertical distance the sphere must travel to produce the desired impact.
- 2 – For the ball-pendulum impact test the sphere is to contact the test sample when the string is in the vertical position as shown.
- 3 – The backing surface is to consist of 19 mm (3/4 inch) plywood over arigid surface of concrete. An equivalent nonresilient backing surface may be used.

59 Ultraviolet Light Exposure Test

59.1 Apparatus

59.1.1 Specimens are to be exposed to ultraviolet light and water spray by using either of the following apparatus:

- a) Twin enclosed carbon-arc lamp in accordance with the Standard Practice for Exposing Nonmetallic Materials in Accelerated Test Devices That Use Laboratory Light Sources, ASTM G151, and the Standard Practice for Operating Enclosed Carbon Arc Light Apparatus for Exposure of Nonmetallic Materials, ASTM G153. The spectral power distribution of the enclosed carbon-arc shall conform to the requirements in ASTM G153 for enclosed carbon-arc lamp with borosilicate glass globes. A programmed cycle of 20 minutes consisting of a 17-minute light exposure and a 3-minute exposure to water spray with light shall be used. The apparatus shall operate with a black-panel temperature of $63 \pm 3^{\circ}\text{C}$ ($145 \pm 5^{\circ}\text{F}$), or
- b) Xenon-arc lamp in accordance with the Standard Practice for Exposing Nonmetallic Materials in Accelerated Test Devices That Use Laboratory Light Sources, ASTM G151, and the Standard Practice for Operating Xenon Arc Light Apparatus for Exposure of Nonmetallic Materials, ASTM G155. The spectral power distribution of the xenon lamp shall conform to the requirement in Table 1 in ASTM G155 for a xenon lamp with daylight filters. A programmed cycle of 120 minutes consisting of a 102-minute light exposure and an 18-minute exposure to water spray with light shall be used. The apparatus shall operate with a spectral irradiance of $0.35 \text{ W/m}^2 \text{ nm}$ at 340 nm and a black-panel temperature of $63 \pm 3^{\circ}\text{C}$ ($145.4 \pm 5.4^{\circ}\text{F}$).

Exception: Indoor enclosures that are subjected to UV radiation sources (such as, high intensity discharge lamps), may be conditioned without exposure to water.

59.2 Method

59.2.1 The specimens as indicated in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A, are to be mounted vertically on the inside of the cylinder in the ultraviolet-light apparatus, with the width of the specimens facing the arcs, and so that they do not touch each other.

Exception No. 1: For flexural strength specimens the ultraviolet-exposed side is to be in contact with the two points when using the three-point loading method.

Exception No. 2: Izod impact specimens are to be notched prior to UV conditioning with the direction of UV exposure towards the notch.

59.2.2 Two sets of specimens are to be exposed. For twin enclosed carbon-arc, one set is to be exposed for a total of 360 hours and the second set for a total of 720 hours. For xenon-arc, one set is to be exposed for a total of 500 hours and the second set for a total of 1000 hours. After the test exposure, the specimens are to be removed from the test apparatus, examined for signs of deterioration such as crazing or cracking, and retained under conditions of ambient room temperature and atmospheric pressure for not less than 16, nor more than 96 hours, before being subjected to flammability and physical tests. For comparative purposes, specimens that have not been exposed to ultraviolet light and water are to be subjected to these tests at the same time that the final exposed specimens are tested.

59.2.3 The flammability classification of base samples described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94, of the material in the thinnest part thickness under consideration, shall not be reduced as a result of the UV conditioning. Except as noted in 59.2.6, the average physical property values after 720 hours of twin enclosed carbon-arc exposure in accordance with ASTM G151 and G153 or 1000 hours xenon-arc exposure in accordance with ASTM G151 and G155, weatherometer conditioning shall not be less than 70 percent of the unconditioned value when the standardized small-scale physical tests shown in Table 59.1 are performed as described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

Table 59.1
Physical-property test methods

Physical-property consideration	Material test method
Functional support	Tensile strength or Flexural strength ^a
Impact resistance	Tensile impact, Izod impact, or Charpy impact
^a The ultraviolet-exposed side is to be in contact with the two loading points when using the three-point loading method.	

59.2.4 Tensile or flexural strength tests are to be conducted on specimens no thicker than the corresponding application. The results of Tensile, Charpy or Izod Impact testing of standard specimens in the nominal 4 mm thickness, can be considered representative of the testing of a reduced thickness not less than 0.75 mm, provided the non-impact testing of the reduced thickness complies with the requirements of Table 27.1.

59.2.5 If a material is to be considered in a range of colors, specimens representing these ranges are also to be provided. Specimens in the natural (if used in this color) and in the most heavily pigmented light and dark colors are to be provided and considered representative of the color range, if the test results are essentially the same. An additional set of specimens is to be provided in the heaviest organic pigment loading, unless the most heavily pigmented light and dark colors include the highest organic pigment level. When certain color pigments (for example, red, yellow, or the like) are known to have particularly critical effects, they are also to be provided.

59.2.6 Where it is not practical to conduct tests using the standardized small-scale impact-test specimens, the procedure of 59.2.7 – 59.2.11 and the impact equipment of Figures 59.1 and 59.2 may be used on representative sections of the enclosure as an alternative for tests conducted on tensile or izod impact specimens.

59.2.7 Referring to Figures 59.1 and 59.2, the equipment for impact is to consist of the following: a cast aluminum base, two steel-rod impact weights weighing 0.91 kg (2 lb) and 1.82 kg (4 lb); a hardened-steel round-nose impactor weighing 3.64 kg (8 lb) and with a radius of 8 mm (0.312 inch); a slotted guide tube 1.0 m (39.3 inches) in length, where the impact weights slide and also having inch-pound (joule) graduations in 0.23 J (2 inch-lb) increments. A bracket fixes the tube in vertical position by attaching it to the base and also holds the hand knob, that is a pivot-arm alignment for the impactor approximately 50 mm (2 inches) under the tube. This instrument is to be mounted firmly to a rigid table or bench. The specimen support plate as shown in Figure 59.2 is to be removed, leaving the specimen support-diameter of 31.8 mm (1.25 inch).

59.2.8 Each determination of impact resistance is to be made using 20 specimens. One at a time the specimens are to be placed so that they are centered over the opening in the specimen support. All specimens for a given material must be of the same thickness. The impactor foot is to be lowered to come in contact with the top surface of the specimen. To conduct the test, the weight, either 0.91 or 1.82 kg (2 or 4 lb), as needed, is to be raised to the height to give the desired impact value and released so that it drops on the impactor. The sample is then to be examined for a crack, break, or split appearing on the side opposite the contact area. If the first sample results in a crack, split, or break, the next is to be impacted at a level one increment lower. This increment may be 0.5 to 2.0 times the estimated standard deviation(s) described in 59.2.10. If the sample passes this test, the next sample is to be tested at an equal increment higher than the first sample.

59.2.9 Data is to be analyzed using the Up-and-Down Design (Staircase) Method described in the National Bureau of Standards Handbook 91, "Experimental Statistics", to estimate the mean value before and after the UV exposure. Reference to Figure 59.3 provides sample calculations and data record. The result of the test procedure shows a variation of impact values for the 20 samples that alternately increases and decreases as shown. The summaries at the end of the data table show the number that resulted in unacceptable results (n_x), the number that resulted in acceptable results (n_o), a constant (i) that varies from 0 for the lowest impact where unacceptable results were obtained to 1, 2, 3, and so forth for the next higher values that are used, the number of events that occurred at each test value (n_i), a value for the product of the preceding two columns (in_i), and a value for the product of this column and the i -column ($i^2 n_i$) in the remaining calculations, the totals for all columns except the i -column are used and are designated as (N_x), (N_o), (N), (A), (B).

59.2.10 The Estimated Standard Deviation shall be calculated to determine if the chosen increments are within the proper range. An increment equal to the standard deviation is the most desirable. This deviation is determined from the formula:

$$S = 1.6 \times d [B/N - (A/N)^2] + 0.47 d$$

in which:

d is the increment of height in mm.

59.2.11 The Mean Failure Height (h) is determined using the formula:

$$h = h_o + d (A/N) \pm 0.5d$$

in which:

h_o is the lowest height that impact failure occurred.

The Mean Failure Energy (MFE) is determined from the formula:

$$MFE = hwf$$

in which:

w is the value of the weight in kilograms

f is 9.80665×10^{-3} a factor for conversion to joules.

The value of MFE before and after UV exposure is used to determine compliance with 59.2.5 or 59.2.7, as appropriate.

Figure 59.1
Impact tester



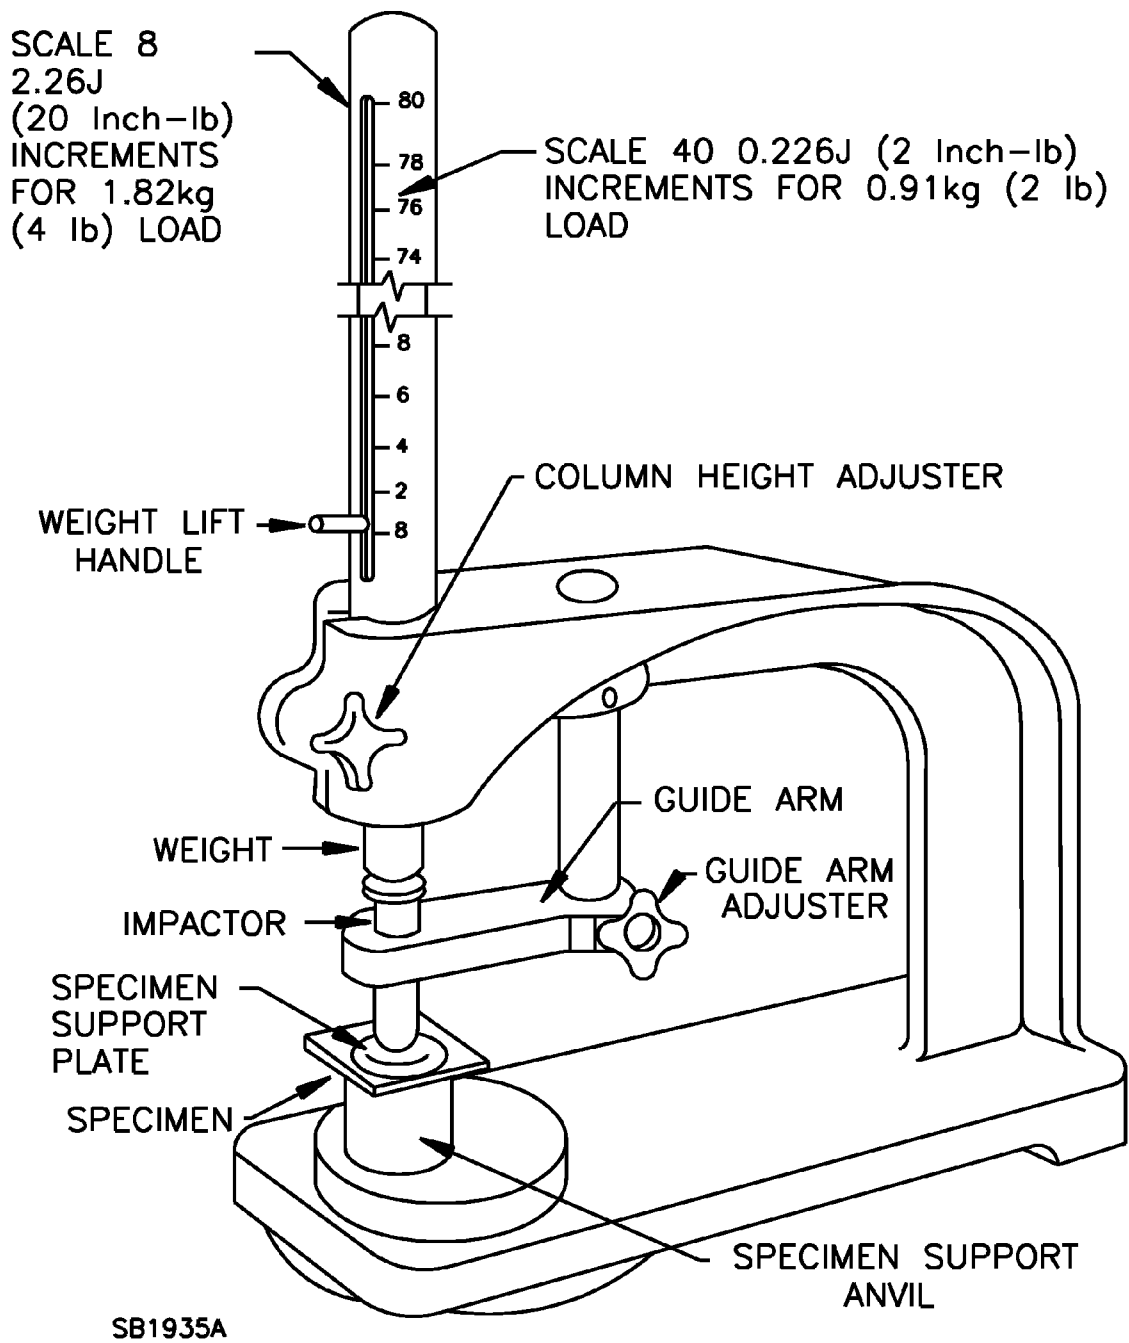


Figure 59.2
Impact tester parts in contact with specimen

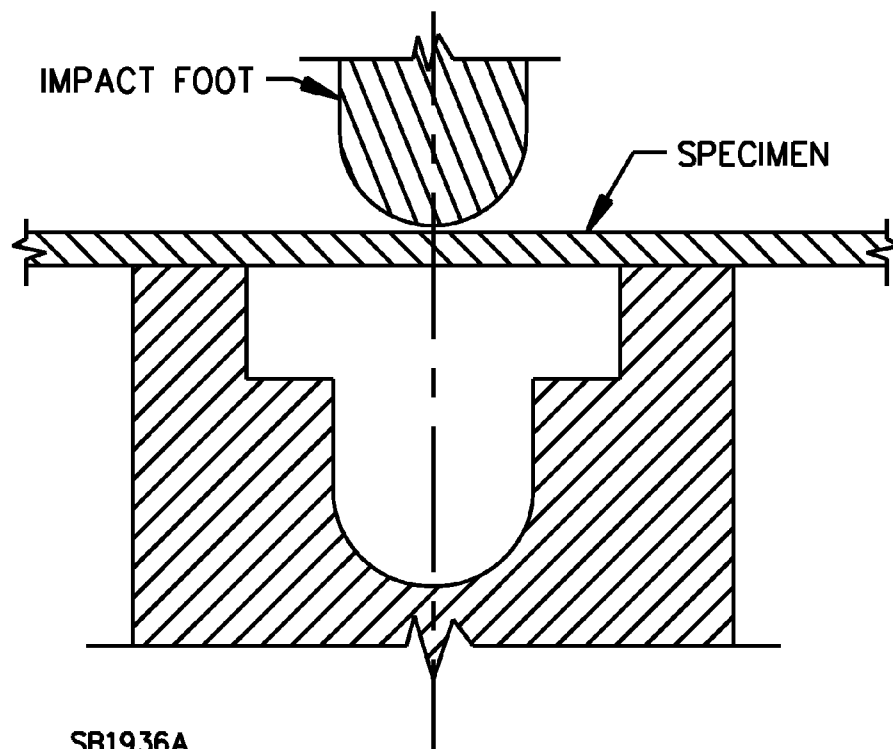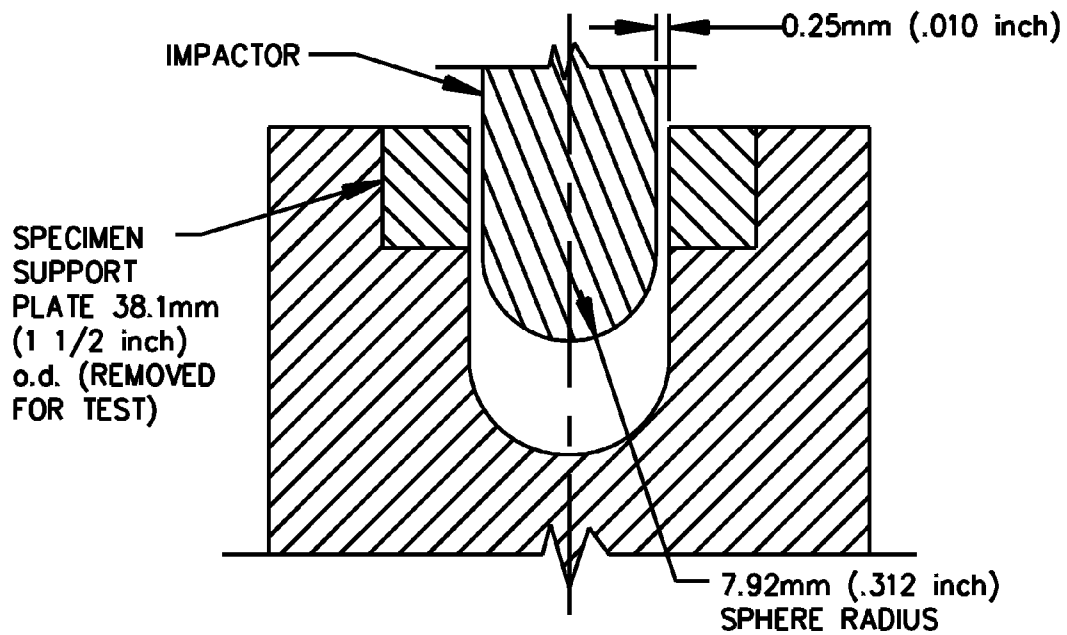

SB1936A

Figure 59.3 Sample calculations

Drop height mm	Outcome of test (X – failure; 0 – nonfailure)																				n_x	n_o	i	n_i	in_i	i^2n_i
	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20						
900						X															1	0	2	1	2	4
800					0		X		X				X		X						4	1	1	4	4	4
700		X		0				0		X		0		0		X		X		0	4	5	0	4	0	0
600	0		0								0						0		0		0	5				
		Totals																			9	11		9	6	8
																					(N_x)	(N_o)		(N)	(A)	(B)

$$h_o = 700; N_x = 9; d = 100$$

$$h = h_0 d (A/N) - 0.5d$$

$$= 700 + 100 (6/9) - 0.5 (100)$$

$$= 717 \text{ mm}$$

$$s = 1.6d [B/N - (A/N)^2] + 0.0668d$$

$$= 1.6 \times 100 \times [2/9 - (6/9)^2] + 0.0668 \times 100$$

$$= 77.8 \text{ mm}$$

$$MFE = hwf \quad w = 0.907 \text{ Kg}$$

$$= 717 \times 0.907 \times 9.80665 \times 10^{-3}$$

$$= 6.37 \text{ J}$$

60 Water Exposure and Immersion Test

60.1 Using standard test procedures, property values for the material are to be determined both before and after the conditioning described below:

- a) Specimens of the material shall be immersed in distilled or deionized water at $70.0 \pm 1.0^{\circ}\text{C}$ ($158.0 \pm 1.8^{\circ}\text{F}$) for 7 days. A complete change of water is to be made on each of the first 5 days. Following the water conditioning, those specimens that are to be subjected to physical-property tests are to be immersed in distilled or deionized water at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) for 1/2 hour immediately prior to testing. Following the immersions, those specimens to be subjected to flammability tests are to be conditioned in air at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 \pm 5 percent relative humidity for 2 weeks. Physical property tests conducted on the 3.2 mm (1/8 inch) thick specimens are considered representative of other thicknesses, down to 1.6 mm (1/16 inch).

Exception: For materials classed 5VA or 5VB or materials that are evaluated by Enclosure Flammability – 5 inch Flame Test, Section 54, the specimens shall be immersed in distilled or deionized water at $82 \pm 1^{\circ}\text{C}$ ($180 \pm 1.8^{\circ}\text{F}$) rather than $70 \pm 1^{\circ}\text{C}$.

60.2 The following properties shall be included in the evaluation (See Table 59.1):

- a) For Functional Support, either
 - 1) Tensile Strength, or
 - 2) Flexural Strength
- b) For Impact Resistance, either
 - 1) Tensile Impact, or
 - 2) Izod Impact, or
 - 3) Charpy Impact.
- c) Flammability, as described in the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94. See 59.2.3 – 59.2.7, and Table 59.1.

60.3 Tensile Strength Tests conducted on 3.2 mm (1/8 inch nominal) or 4.0 mm thick specimens are considered representative of other thicknesses, down to 0.8 mm (1/32 inch).

61 Abnormal Operation Test

61.1 The equipment is to be operated under the conditions of abnormal operation, that are appropriate for the product, such as stalled-rotor operation, air inlet blocked, and operation with live parts short-circuited. During the test, the equipment is to rest on white tissue paper on a softwood surface. A single layer of cheesecloth is to be draped over the entire equipment and the equipment is to be operated continuously until the ultimate results have been determined. In most cases, continuous operation for 7 hours may be necessary to obtain the ultimate results. Only one of the simulated abnormal conditions described above is to be imposed at one time. A new sample may be used to evaluate any or all conditions of abnormal use.

62 Severe Conditions Test

62.1 The equipment is to be operated in accordance with the conditions indicated below. During the test, the equipment is to rest on white tissue paper on a softwood surface. A single layer of cheesecloth is to be draped over the entire equipment and the equipment is to be operated as described in (a) – (c) until ultimate results have been determined. The maximum temperature of the enclosure material, during the conditioning shall be recorded unless burnout occurs.

- a) Unless the equipment is provided with a momentary-contact line switch (one that requires constant pressure to hold it in the on position) and no means for locking the switch in the on position, a sample of the equipment shall be operated at no-load and rated voltage (see 65.1 for 7 hours).
- b) A sample of the equipment shall be operated at 106 percent of rated voltage (see 65.1 under the same conditions of use as for the normal-temperature test for 7 hours).
- c) A sample of the equipment shall be operated at 94 percent of rated voltage (see 65.1) under the same conditions of use as for the normal-temperature test for 7 hours).

Exception: A manufacturer may elect to use the same sample for each conditioning provided that acceptable results are obtained.

62.2 For each of the conditioning methods mentioned in 62.1, an overload protective device provided with the equipment is to be bypassed.

Exception: User-serviceable or resettable overcurrent or overtemperature protectors can be maintained in the circuit during the conduct of the test provided that they have been shown by a separate investigation to reliably clear the circuit at the voltage, current, and power-factor levels involved.

63 Mold Stress-Relief Distortion Test

63.1 One sample of the equipment shall be conditioned in accordance with either (a) or (b) below:

a) One sample of the complete equipment (in the case of an enclosure) or the part under consideration, is to be placed in a full draft circulating air oven maintained at a uniform temperature at least 10°C (18°F) higher than the maximum temperature of the material measured under actual operating conditions, but not less than 70°C (158°F) in any case. The sample is to remain in the oven for 7 hours. After its careful removal from the oven and return to room temperature, the sample is to be investigated for compliance with 31.1.

b) One sample of the complete equipment is to be placed in a test cell. The circulation of air within the cell is to simulate actual room conditions. The air temperature within the cell, as measured at the supporting surface of the equipment, is to be maintained at 60°C (140°F). The equipment is to be operated in the same way as for the temperature test except for equipment that is not loaded or is not continuously loaded during the normal temperature test. Such equipment, although unloaded, shall be connected to 106 percent or 94 percent of normal rated voltage, whichever results in higher temperatures. In any case, the equipment is to be operated for 7 hours. After its careful removal from the test cell, the sample is to be investigated for compliance with 31.1.

63.2 One sample of the complete equipment, or enclosure thereof, is to be placed in a full draft circulating air oven maintained at a uniform temperature at least 10°C (18°F) higher than the maximum temperature of the material measured during the equipment conditioning described in 62.1, but not less than 70°C (158°F) in any case. The sample is to remain in the oven for 7 hours. After its careful removal from the oven and return to room temperature, the sample is to be investigated for compliance with 31.1.

Exception: If the equipment electrically burns-out as a result of the conditioning of 62.1, the oven test temperature is to be 10°C (18°F) higher than the maximum enclosure temperature measured under actual operating conditions or the highest temperature obtained under the conditions of 62.1 without burnout.

64 Ball Pressure Test on End-Product

64.1 This test method determines the value of temperature at which a standard force applied through a spherical shape, causes a defined value of penetration. The test method is described in IEC 695-10-2.

64.2 Enclosures and other external parts of insulating material (other than those of ceramic material) are to be tested, as indicated. The test is to be conducted at several temperatures so that the specific temperature can be determined at which the diameter of the impression, after the specified conditioning, is 2.0 ± 0.1 mm (0.079 ± 0.004 inch).

65 Input to Motors Test

65.1 Unless otherwise indicated or if primary-circuit adjustments are not provided, the test is to be conducted with the equipment connected to a supply circuit of maximum rated voltage and rated frequency except that, if the marked voltage is in the 105 – 120 V range, the potential of the supply circuit is to be 120 V and, if the marked voltage is in the 210 – 240 V range, the potential of the supply circuit is to be 240 V. If primary-circuit adjustments are provided, they are to be set for the minimum voltage in the 105 – 120 V range, or in the 210– 240 V range, and the potential of the supply circuit is to be 120 V, or 240 V, whichever is applicable. See 32.1.

66 Relative Thermal Capability

66.1 Computation of the Relative Thermal Capability (RTC) (see Section 38) requires definition of the following:

- a) RTI (from the UL 746B procedure)
- b) Life Equation Parameter (B)
- c) Excess Performance Factor (P)
- d) Property-Time Degradation characteristics for one or more aging temperatures

The factor, P, associated with a critical property is the ratio of the actual performance level measured in the finished part to the minimum normally acceptable level. For example, consider an enclosure material where the minimum level of impact strength is defined by the end-product standard to be 6.75 J (5 ft-lb). Testing reveals that, due to increased material thickness or other strengthening design features, the enclosure will consistently survive impacts of up to 13.5 J (10 ft-lb). Therefore, the excess performance factor, $P = 10 / 5 = 2$.

66.2 A reduced end-of-life performance (percent) is calculated as $f = 50/P$. Property-Time degradation characteristics at one or more aging temperatures, from the original aging program for the RTI, are then used to determine the time t_1 required for the property to degrade to the reduced "f" percent level. The ratio $F = t_1/t_0$ is calculated, where t_0 is the end-of-life time corresponding to 50 percent degradation. If data is available at more than one temperature, then the minimum resulting F is to be used for the RTC calculation.

66.3 If a material has an RTI of 130°C, where impact properties are essential in some minimum thickness equal to less than the application, the life equation parameter, $B = 3423$, and the minimum value of F determined from Property-Time degradation characteristics is 1.5, then the RTC is computed as follows. (See Temperature Considerations – Illustrative Example, Section 69).

$$RTC = [1 / (RTI + 273.16) - (\log F) / B]^{-1} - 273.16$$

$$RTC = [1 / (130 + 273.16) - (\log 1.5)/3423]^{-1} - 273.16$$

$$RTC = (0.0024804 - 0.00005144)^{-1} - 273.16$$

$$RTC = 138.5^{\circ}\text{C}$$

67 Relative Thermal Capability (Alternate)

67.1 Except as indicated below, samples of the part in question may be aged for 1000 hours at the corresponding part aging (see 39.6) temperature determined from the generated relative thermal capability profile line and the part aging temperature shall not exceed the aging temperature used in the original material thermal aging investigation. At the completion of the aging, the samples are to be cooled to room temperature and then subjected to the end-product tests that stress the functional usage of the material. Polymeric parts that are subjected to any type of long-term loading (for example, bending, compression, or tensile loading) shall comply with the creep analysis described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A.

Exception No. 1: A shorter or longer time at a higher or lower part aging temperature, respectively, may be employed if agreeable to all concerned; however, a period of time not less than 300 hours is to be used.

Exception No. 2: The part aging temperature may exceed the aging temperatures used in the original thermal aging investigation for the material providing that thermal analysis techniques, such as Differential Scanning Calorimetry (DSC) and Thermogravimetry (TG), show the absence of transitions in the temperature region beyond the material aging temperature that affects the Activation Energy of the material.

67.2 Samples of the part may be aged by either of the two methods indicated below:

- a) The samples of the product are to be connected to a supply circuit and the input voltage is to be adjusted so that the hot spot aging temperature is achieved on the part in question. It may be necessary to bypass safety circuits or to conduct the test in a room or test chamber with an elevated ambient temperature in order to achieve the aging temperature of the part. If the test terminates before the aging time is reached (heating element opens), the test is to be repeated on another sample at a lower temperature and for a longer time selected from the generated thermal endurance profile line (Figure 39.1).
- b) In lieu of the operational test described above, samples of the part may be aged in a circulating-air oven for the required aging time.

68 Temperature Excursions Beyond the Maximum Use Temperature

68.1 For the purpose of illustration consider the following example (Figure 68.1). A steam flatiron contains a leaf type thermostat that regulates temperatures on the sole plate. After three minutes of operation thermal equilibrium is achieved and the thermostat functions in a cyclic fashion in accordance with the measured time-temperature characteristic (Figure 68.1). During the cycle, the highest temperature measured was 180°C (356°F) and the lowest temperature measured was 130°C (266°F). The phenolic thermostat material was subjected to long term thermal aging tests (Relative Thermal Index, Section 37), and relative thermal indices of 170°C (338°F) for all properties have been assigned. The activation energy constant of the Arrhenius relationship ($L = A \times \text{Exp}(B/T)$) for the mechanical without impact and electrical properties has been determined as: $B = 16425.3$. Since the thermostat is located within the appliance enclosure, the mechanical with impact relative thermal index is not considered critical to the application.

68.2 A graphical "step" function is constructed and superimposed to approximate, but always exceed, the actual measured data curve. The temperatures and corresponding fractions of cycle time are then easily obtained from the step function. (Table 68.1)

68.3 Substituting this information into 68.4 equation will yield a continuous use temperature for the thermostat material of 162.12°C (323.82°F).

68.4 A more precise mathematical solution for (T_{eq}) when the temperature is defined continuously as $[T(t)]$ over a time interval (t_{1-2}) is given by the expression:

$$T_{eq} = B / \ln \left[\left(1 / (t_2 - t_1) \right) \int_{t_1}^{t_2} \text{Exp} (-B/T(t)) dt \right]$$

68.5 Since the equivalent continuous use temperature 162.12°C (323.82°F) is less than the assigned relative thermal index (170°C (338°F)), the phenolic material is considered acceptable for use in this thermostat application.

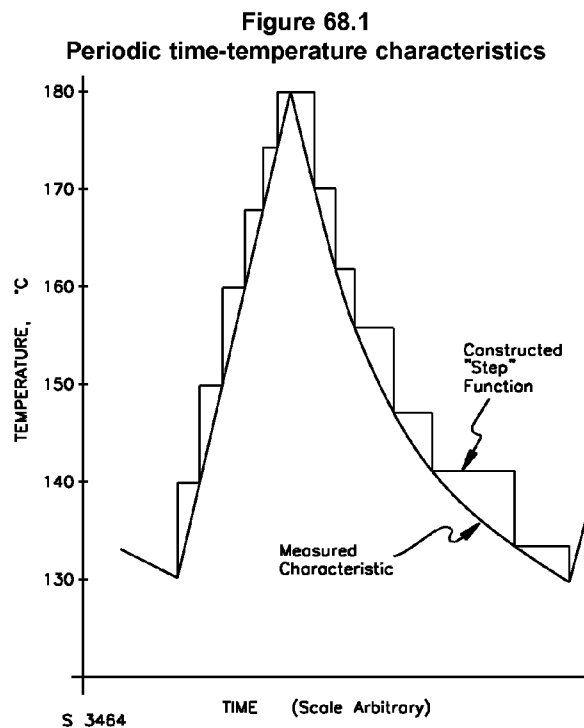


Table 68.1
Periodic time-temperature data

Fraction of cycle time	Temperature degrees C
.05	140
.05	150
.05	160
.05	168
.05	174
.10	180
.05	170
.05	162
.10	156
.10	147.2
.20	141.2
.15	134

69 Temperature Considerations – Illustrative Example

69.1 For the purpose of illustration, refer to Relative Thermal Capability, Section 38, and consider the following example. The enclosure of a cord connected household-use hair dryer, that contains uninsulated live parts, is exposed to a maximum intended use temperature of 137.0°C (278.6°F). The polybutylene terephthalate (PBTP) material used has been assigned a mechanical relative thermal index for impact properties of 130°C (266°F). The electrical and mechanical without impact relative thermal index of 140°C (284°F) has been assigned and was based upon thermal aging data generated at 200, 190, 180 and 170°C. Differential Scanning Calorimetry (DSC) and Thermogravimetry (TG) information is not available for the material.

69.2 The material would not be acceptable using the requirements for the functional-use thermal indices, since the part temperature is 137°C (278.6°F) and the allowable temperature for an attended, intermittent duty, cord connected household appliance enclosure is a maximum of 80°C (176°F).

69.3 The material would not be acceptable using the requirements for the Generic Thermal Indices, since the part temperature is 137°C (278.6°F) and the allowable generic temperature for a PBTP material is a maximum of 75°C (167°F).

69.4 The material would not be acceptable using the requirements for the Relative Thermal Indices, since the part temperature is 137°C (278.6°F) and the specific material's relative thermal index for impact properties is 130°C (266°F).

69.5 The material would be acceptable when used as an enclosure operating at 137°C (278.6°F) for a specific hair dryer model providing that it complies with the requirements for the Relative Thermal Capability (Section 38).

69.6 For this application, it has been judged that electrical (prevention of dielectric breakdown and excessive leakage current), mechanical without impact (functional support of electrical conductors and supporting members), mechanical with impact (for prevention of accessibility to live parts and for continued maintenance of electrical spacings) and retention of flammability characteristics are required enclosure properties for the satisfactory functioning of the part in the application. For this material, the impact property has the highest rate of degradation (lowest relative thermal index) and would therefore be most critical in the application.

69.7 The following data is a summary of the long term heat aging test results on the impact property of the material.

Aging temperature		Time to 50 percent degradation, hours
0°C	0°F	
180	356	2010
170	338	3360
160	320	4530
150	302	7170

A relative thermal index for impact of 130°C (266°F) was assigned to the PBTP material corresponding to a 18,132 hour correlation factor (life).

Using the procedures described in Polymeric Materials – Long Term Property Evaluation, UL 746B, linear regression analysis on the material data resulted in the relationship:

$$\log_{10} (\text{hours}) = A + B / (^\circ\text{C} + 273.16)$$


in which:

A is -4.232

B is 3423

69.8 The minimum acceptable impact resistance as defined by the end-product standard is that the hair dryer must survive a 3 foot drop. Tests reveal that the enclosure will consistently survive a drop from 6 feet. The excess performance factor, P, is therefore $P = 6/3 = 2$, and the reduced end-of-life performance (percent) is $f = 50/2 = 25$ percent. From existing Property-Time degradation characteristics (See Figure 69.1), the minimum ratio $F = t_1/t_0$ determined for one or more temperatures is $F = 1500 / 1000 = 1.5$, and the computed RTC = 138.5°C (281.3°F) (Relative Thermal Capability, Section 66).

Figure 69.1
Property degradation characteristic curve

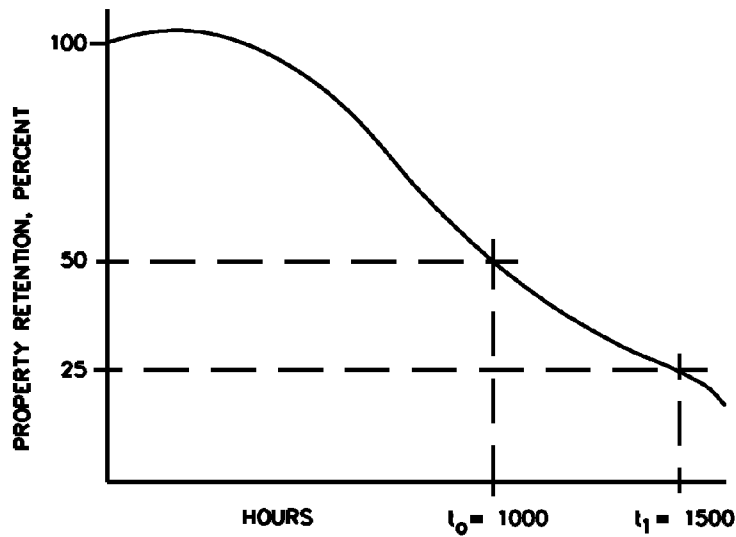

S3552

70 Temperature Considerations – Illustrative Example (Alternate RTC)

70.1 For the purpose of illustration, refer to Relative Thermal Capability (Alternate), Section 39, and consider the following example. The enclosure of a cord connected household-use hair dryer, that contains uninsulated live parts, is exposed to a maximum intended use temperature of 154.0°C (309.2°F). The polybutylene terephthalate (PBTP) material used has been assigned a mechanical relative thermal index for impact properties of 130°C (266°F). The electrical and mechanical without impact relative thermal index of 140°C (284°F) has been assigned and was based upon thermal aging data generated at 200, 190, 180 and 170°C (392, 374, 356, and 338°F). Differential Scanning Calorimetry (DSC) and Thermogravimetry (TG) information is not available for the material.

70.2 The material would not be acceptable using the requirements for the functional-use thermal indices, since the part temperature is 154°C (309.2°F) and the allowable temperature for an attended, intermittent duty, cord connected household appliance enclosure is a maximum of 80°C (176°F).

70.3 The material would not be acceptable using the requirements for the Generic Thermal Indices, since the part temperature is 154°C (309.2°F) and the allowable generic temperature for a PBTP material is a maximum of 75°C (167°F).

70.4 The material would not be acceptable using the requirements for the Relative Thermal Indices, since the part temperature is 154°C (309°F) and the specific material's relative thermal index for impact properties is 130°C (266°F).

70.5 The material would be acceptable when used as an enclosure operating at 154°C (309.2°F) for a specific hair dryer model providing that it complies with the requirements for the Relative Thermal Capability (Alternate), (Section 39).

70.6 For this application, it has been judged that electrical (prevention of dielectric breakdown and excessive leakage current), mechanical without impact (functional support of electrical conductors and supporting members), mechanical with impact (for prevention of accessibility to live parts and for continued maintenance of electrical spacings) and retention of flammability characteristics are required enclosure properties for the satisfactory functioning of the part in the application. For this material, the impact property has the highest rate of degradation (lowest relative thermal index) and would therefore be most critical in the application.

70.7 The following data is a summary of the long term heat aging test results on the impact property of the material.

Aging temperature°C	Time to 50% degradation, hours
180	390
170	848
150	7651
140	14286

A relative thermal index for impact of 130°C was assigned to the PBTP material corresponding to a 73,969 hour correlation factor (life), Line A of Figure 39.1.

Using the procedures described in Polymeric Materials – Long Term Property Evaluations, UL 746B, linear regression analysis on the material data resulted in the relationship:

$$t = Ae^{B/T}, \text{ or}$$

$$\log_{10}(t) = A_1 + \frac{B}{T} \log_{10}e = A_1 + \frac{B_1}{T}$$

in which:

A1 is the log10 (A) = -20.7519297

B1 is B log10e = 10329.35299

T is the absolute temperature, °K (°C + 273.16)

log10 (t) is the logarithm to the base 10 of time in hours.

70.8 The equation for determining the relative thermal capability is obtained by substituting the known maximum application temperature (154°C) and correlation time (73,969 hours). Therefore, the equation for the relative thermal capability for the impact may be expressed as:

$$\log_{10}(73,969) = A_2 + \frac{10329.35299}{154 + 273.16}$$

$$\text{Therefore, } A_2 = -19.31241151$$

$$\text{Hence, } \log_{10}(t) = -19.31241151 + \frac{10329.35299}{^{\circ}\text{C} + 273.16}$$

Substituting the 1000 hour time from 67.1 into this equation yields an oven aging temperature for the part of 190°C (374°F). However, 67.1 will permit a maximum aging temperature of 200°C (392°F), since the electrical and mechanical, without impact, relative thermal indices were determined using data obtained at the highest material aging temperature of 200°C (392°F). Substituting 200°C into the formula will yield a part aging time of 330 hours, line B of Figure 39.1. The part aging temperature of 200°C for 330 hours complies with the minimum 300 hour exposure time (as specified in Exception No. 1 of 67.1).

70.9 Three samples of the product having its safety circuits bypassed, are to be connected to a supply circuit and the input voltage is to be adjusted so that the aging temperature is achieved on the part in question.

70.10 After the 330 hour exposure at 200°C (392°F), the samples would be cooled to room temperature, and then dropped from a 0.91 m (3 foot) height onto a hard wood surface as described in Resistance to Impact Test, Section 58. The samples would then be subjected to dielectric withstand and flammability test as appropriate for the product. Acceptable results would be required if the material is to be considered acceptable for use at temperatures up to 154°C (309.2°F) in this particular application.

71 Adhesives – Specialized Applications

71.1 General

71.1.1 Unless otherwise specified, all testing shall be conducted in a standard laboratory atmosphere at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 ± 5 percent relative humidity.

71.1.2 Specimens shall be of the type described in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A. Specimen preparations shall be in accordance with the manufacturer's specification for fabrication. Surface preparation shall remove all contaminating substances (mold releases on polymeric surfaces; paint, rust, oxide films, oil, and dust from metal surfaces). Freshly cleaned surfaces shall be protected by a primer if the adhesive cannot be applied immediately. The adhesive can be applied by spray, brush, knife, or film. The temperature and pressure application during bonding shall be in accordance with the adhesive manufacturer's specifications.

71.2 As-received test

71.2.1 For each primary property to be evaluated, 20 specimens shall be conditioned for 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.0 \pm 3.6^{\circ}\text{F}$) and a relative humidity of 50 ± 5 percent prior to testing.

71.2.2 The specimens are to be subjected to applicable tests to determine the value of the critical properties in the as-received condition. In the case of bond-strength evaluation, specimens that break at an obvious flaw remote from the adhesive line shall be discarded and a retest made. The average value of the property is to be computed. This value is to be used for comparison with values of the same property after the environmental conditioning described in 71.1.1 – 71.5.1.

71.3 Effect of temperature


71.3.1 For each primary property to be evaluated, ten specimens shall be conditioned for 1000 hours at the oven temperature taken from the respective thermal-endurance-profile line in Figure 71.1, where the temperature index T is the measured normal operating temperature of the adhesive, but not less than 60°C (140°F).

Exception No. 1: The effect-of-temperature test need not be conducted on joints bonded by fusion techniques, such as solvent or ultrasonic welding, and the like.

Exception No. 2: On the same thermal-endurance-profile line in Figure 71.1, a shorter or longer time at a higher or lower temperature respectively may be employed if agreeable to all concerned, but a period no less than 300 hours is to be used.

71.3.2 After the conditioning, the specimens shall be brought to and tested at room temperature to determine the critical property values. The average conditioned value for each property is to be at least 50 percent of the unconditioned value.

Figure 71.1
Conditioning time versus oven temperature for temperature index of adhesives

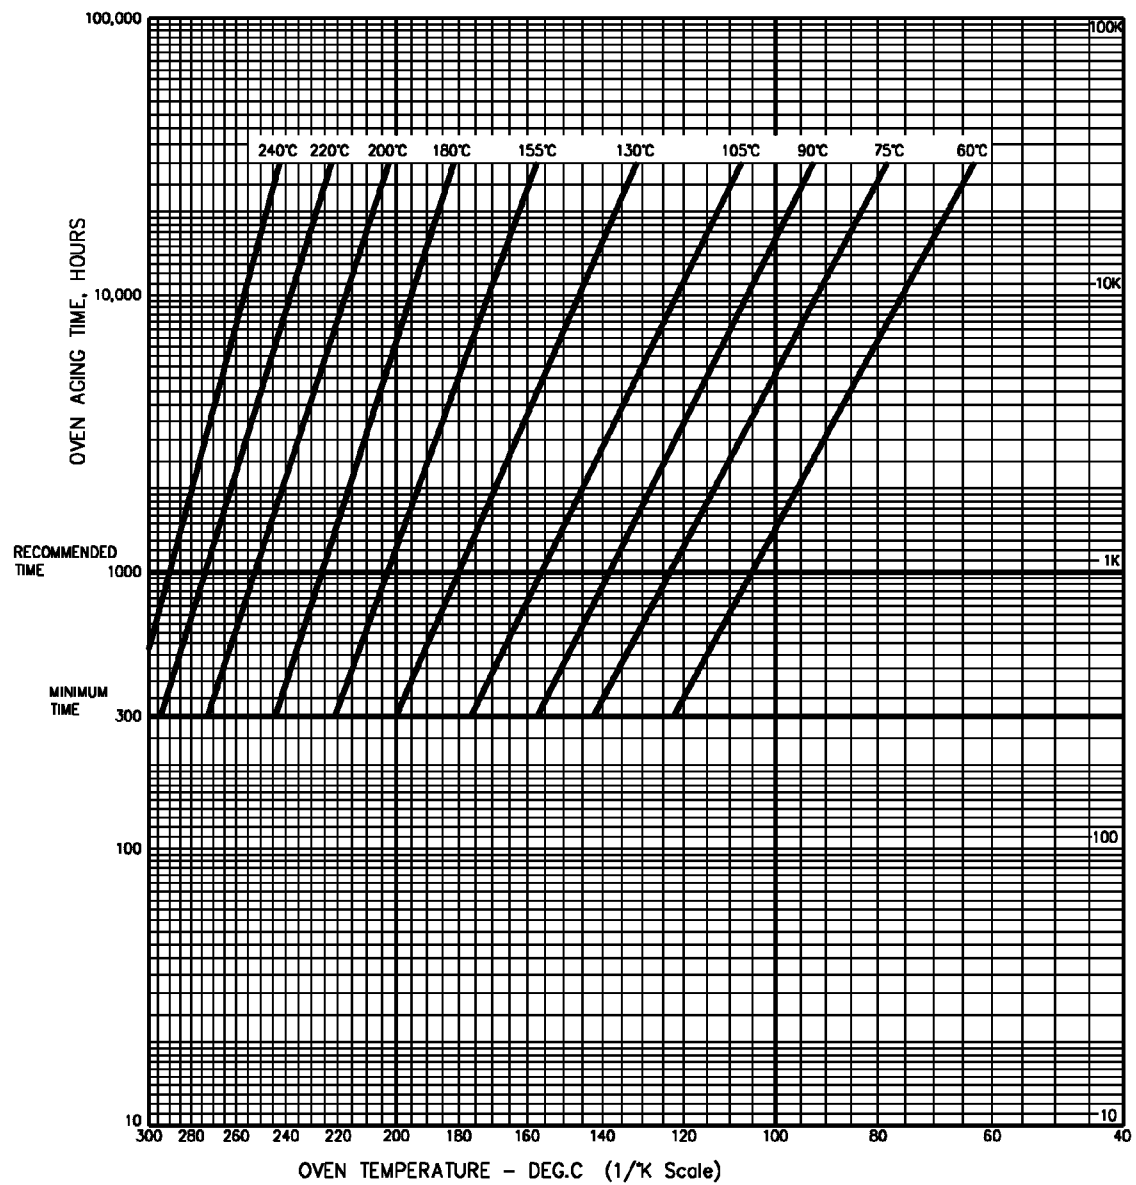

71.4 Effect of humidity

71.4.1 For each primary property to be evaluated, ten specimens shall be conditioned for 7 days at 95 – 100 percent relative humidity at $60.0 \pm 1.0^{\circ}\text{C}$ ($140.0 \pm 1.8^{\circ}\text{F}$).

Exception: The effect-of-humidity test need not be conducted on joints bonded by fusion techniques, such as solvent or ultrasonic welding, and the like.

71.4.2 After the conditioning, the specimens shall be brought to and tested at room temperature to determine the critical property values. The average conditioned value for each critical property is to be at least 50 percent of the unconditioned value.

71.5 Effect of cold

71.5.1 There shall be no visual signs of cracking or chipping of the bond between the two adhered parts of the specimens after conditioning for 24 hours at $\text{minus } 35.0 \pm 1.0^{\circ}\text{C}$ ($\text{minus } 31 \pm 1.8^{\circ}\text{F}$) for outdoor-use applications and at $0.0 \pm 1.0^{\circ}\text{C}$ ($32.0 \pm 1.8^{\circ}\text{F}$) for indoor-use applications. At least six specimens are to be subjected to the cold conditioning.

Exception: The effect-of-cold test need not be conducted on joints bonded by fusion techniques, such as solvent or ultrasonic welding, etc.

71.6 Effect of cyclic conditions

71.6.1 For each primary property to be evaluated, ten specimens shall be subjected to three complete cycles of the conditioning indicated in Table 71.1.

71.6.2 After the conditioning, the specimens shall be brought to and tested at room temperature to determine the critical property values. The average conditioned value of each property shall not be less than 50 percent of the unconditioned average value.

Table 71.1
Cycling conditions

For indoor end-use application	For outdoor end-use applications
24 hours at T followed immediately by at least 96 hours at $35.0 \pm 2.0^{\circ}\text{C}$ ($95.0 \pm 3.6^{\circ}\text{F}$), 90 percent relative humidity, followed by 8 hours at $0.0 \pm 2.0^{\circ}\text{C}$ ($32.0 \pm 3.6^{\circ}\text{F}$)	A minimum of 24 hours immersed in $25.0 \pm 2.0^{\circ}\text{C}$ ($77.0 \pm 3.6^{\circ}\text{F}$) water; followed immediately by 24 hours at T followed immediately by at least 96 hours at $35.0 \pm 2.0^{\circ}\text{C}$ ($95.0 \pm 3.6^{\circ}\text{F}$), 90 percent relative humidity; followed by 8 hours at $-35.0 \pm 2.0^{\circ}\text{C}$ ($-31.0 \pm 3.6^{\circ}\text{F}$).
Note: T is the rated temperature, but not less than 60°C (140°F).	

71.7 Other test considerations

71.7.1 If the parts joined by the adhesive are subjected to periodic forces during intended operation, the assembly shall be subjected to an endurance test as applicable to the equipment, following exposure to the effect-of-temperature test described in 71.3.1 and 71.3.2.

71.7.2 In some applications, the parts joined by the adhesive may be subjected to other environmental conditions. The resistance of adhesive-bonded joints to various corrosive media, chemical reagents, oils, fuels, etc. can be determined by subjecting the joined parts to the applicable tests described in the Standard for Polymeric Materials— Short Term Property Evaluations, (UL 746A).

71.7.3 If agreeable to those concerned, as an option, a reduced number of samples may be used, as follows:

- a) As-received – 8 specimens,
- b) Effect of Temperature – 5 specimens,
- c) Effect of Humidity – 5 specimens,
- d) Effect of Cold – 3 specimens, and
- e) Effect of Cycle Conditioning – 5 specimens.

COIL FORMS

72 Conformal Coating Test

72.1 General

72.1.1 Twenty specimens are to be provided with the minimum electrical spacing, and minimum coating thickness using the test pattern shown in Figure 72.1. The specimens are to be prepared by normal production means employing any primer or cleaner recommended by the coating manufacturer if this feature is to be considered. Lead wires are to be attached that are considered acceptable for the voltage stress and temperatures involved. See Table 72.1 for a description of the required specimens.

72.1.2 Specimens are to be prepared for the Voltage Transient and Dielectric Withstand and Breakdown tests in accordance with Table 72.1. Immediately prior to voltage transient testing, the specimens are to be wrapped with a tight-fitting aluminum foil (representing an electrically conductive contaminate deposit along the surface of the coating) that covers the test pattern but does not cover the insulated test lead wire and solder points.

Table 72.1
Test specimens


Test	Quantity of each coating thickness	Dimensions, mm (inch)	Coating thickness	
			Min	Max
Voltage Transient, Dielectric Withstand and Breakdown after:				
A As received (unconditioned)	5	a	X	—
A Environmental conditioning	5	a	X	—
B Humidity conditioning	5	a	X	—
C Thermal conditioning	5	a	X	—
Flammability	20	127x12.7x0.8	X	X
		(5x1/2x1/32)		
		127x12.7x0.8	X	X
		(5x1/2x1/16)		
^a See 72.1.1.				

72.1.3 VOLTAGE TRANSIENT TEST – A 50 – 60 Hz voltage source is to be applied on the specimens between opposite legs of the test pattern, namely leads A, B, C connected together and lead D in Figure 72.1. Each sample is to be subjected to ten (10) randomly triggered (with respect to the 60 Hz supply waveform) applications of a 6 kilovolt surge impulse superimposed on the supply source at 60 second intervals. The surge generator is to have a source impedance of 50 ohms. With no load on the generator, the surge waveform shall have the following characteristics:

- a) Initial rise time of 0.5 microsecond between 10 percent and 90 percent of peak amplitude;
- b) The period of the ensuing oscillatory wave is to be 10 microseconds; and
- c) Each successive peak of alternating polarity is to be 60 percent of the preceding peak.


Refer to Figures 72.2 and 72.3 for a typical surge generation and control relay circuit. All specimens, unconditioned and conditioned, shall be subjected to the voltage transient test. There shall not be any ignition, dielectric breakdown through the coating or evidence of a carbon path being created on the surface of the coating material.

72.1.4 DIELECTRIC WITHSTAND AND BREAKDOWN TEST – The specimens subjected to the voltage Transient Test shall withstand a 1000 V potential difference for one minute without breakdown. The voltage stress is to be applied between leads A, B, C connected together and the foil covering connected to lead D. After one minute, the voltage stress is to be increased until breakdown occurs. Conditioned specimens (see 72.2.1 – 72.2.3 shall withstand the dielectric stress for one minute without breakdown and have a dielectric breakdown value at least fifty percent of the unconditioned samples.

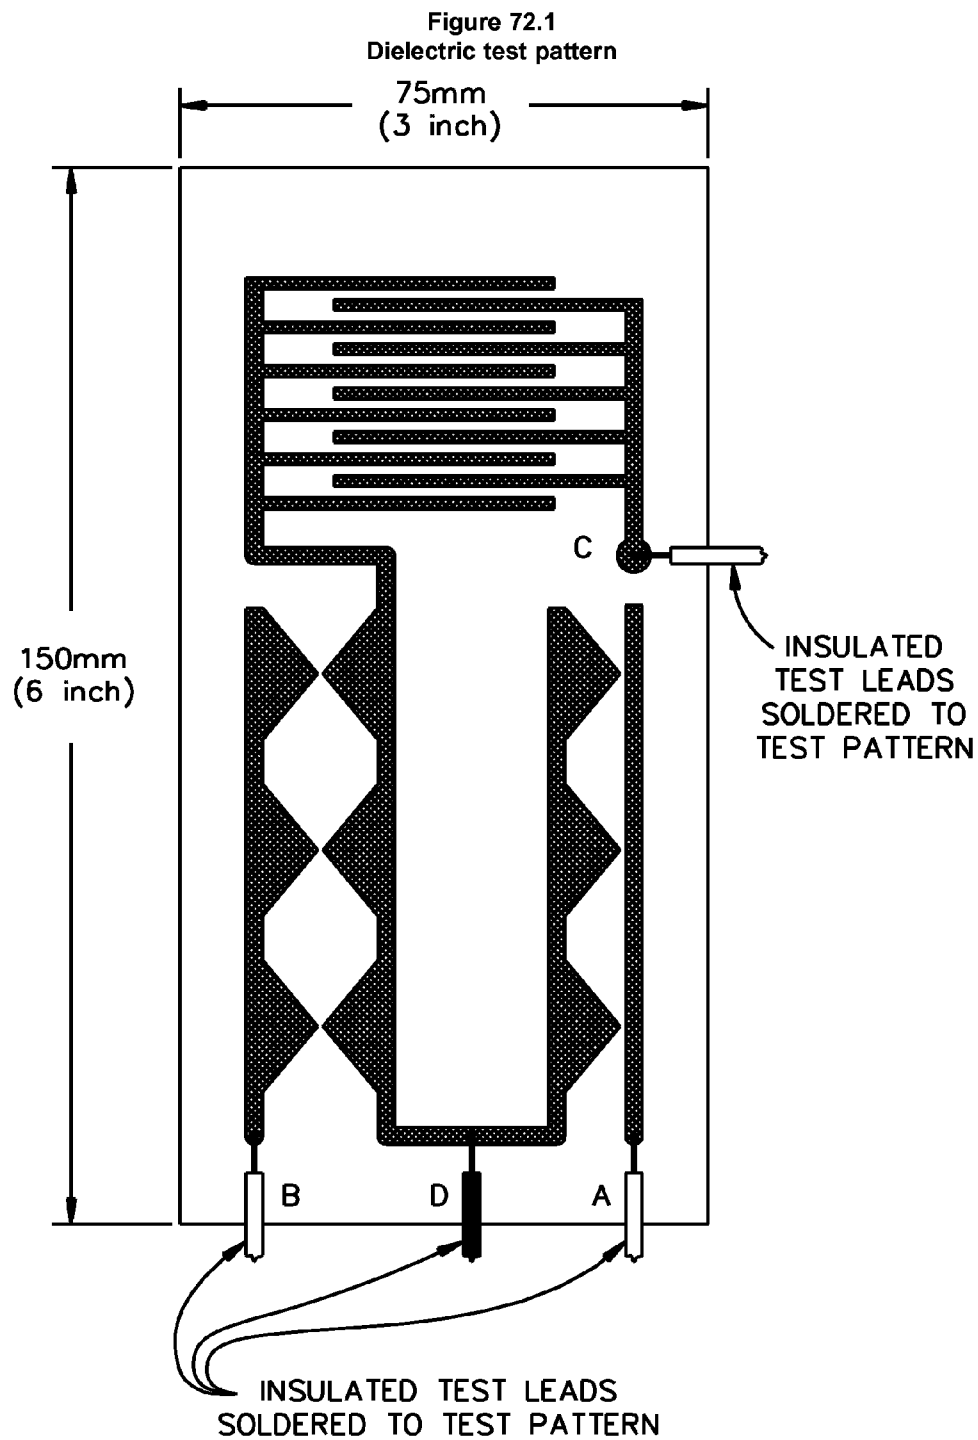

S2005B

Figure 72.2
Surge generator circuit

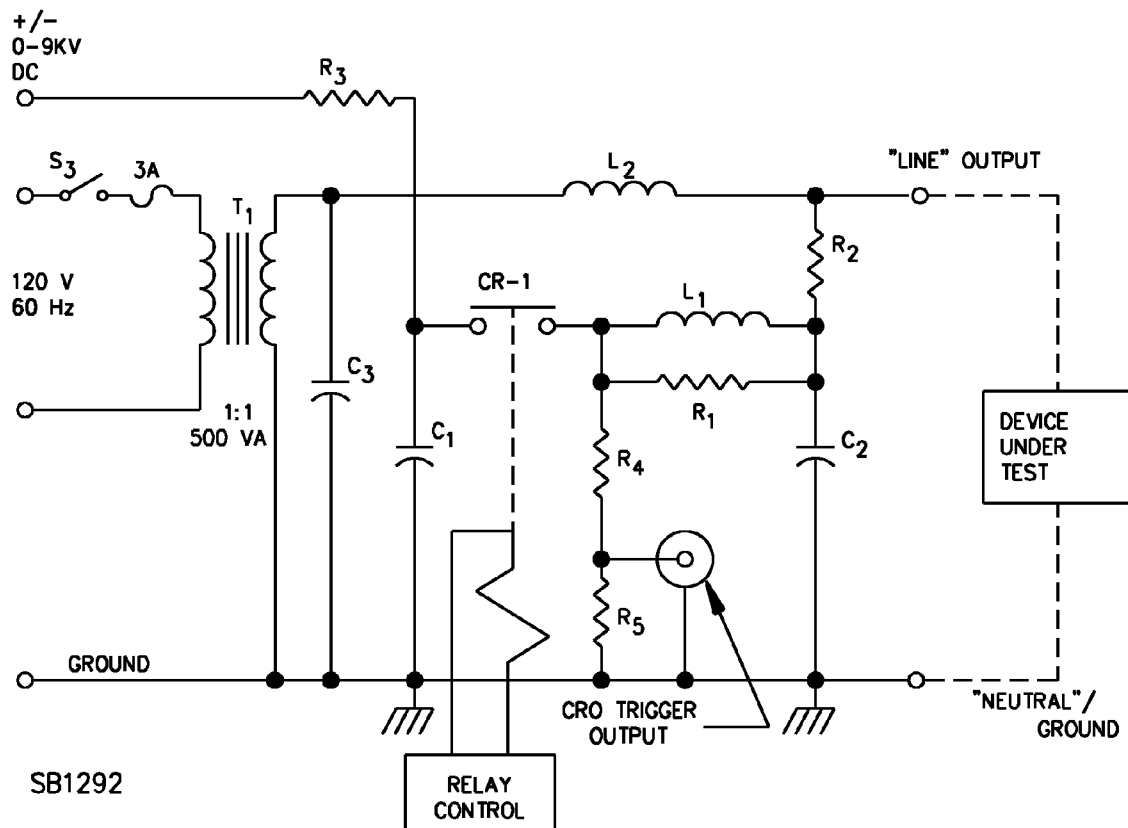

$C_1 = 0.025 \mu\text{F}$, 10kV

$C_2 = 0.01 \mu\text{F}$, 10kV

$C_3 = 4 \mu\text{F}$, 400 V

$R_1 = 22 \text{ Ohms}$, 1W, composition

$R_2 = 12 \text{ Ohms}$, 1W, composition


$R_3 = 1.3\text{M Ohms}$ ($12 \times 110\text{K Ohms}$, 1/2W)

$R_4 = 47\text{K Ohms}$ ($10 \times 4.7\text{K Ohms}$, 1/2W)

$L_1 = 14 \mu\text{H}$ (33 turns, No. 23 AWG wire, 0.7 inch diameter air core)

$L_2 = 70 \mu\text{H}$ (44 turns, No. 14 AWG wire, 2.6 inch diameter air core) $CR-1 = \text{Relay}$ – See Figure 72.3

Figure 72.3
Relay control circuit for surge generator

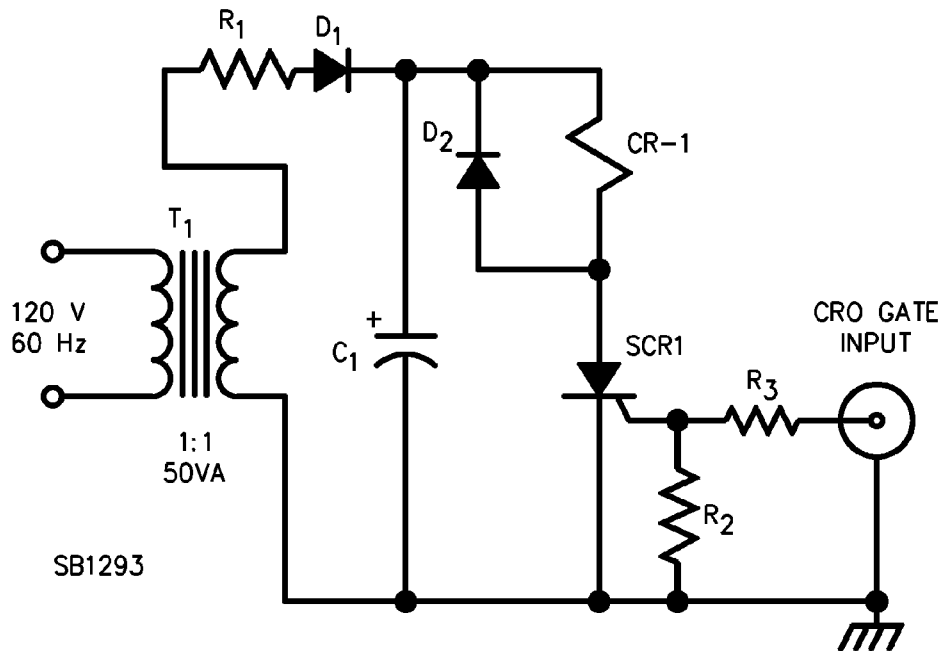

72.2 Sample conditioning

72.2.1 ENVIRONMENTAL CYCLING CONDITIONING— Specimens are to be subjected to three complete cycles of environmental conditioning as described in Table 72.2 and then subjected to the Voltage Transient and Dielectric Voltage-Withstand and Breakdown-Voltage Test.

Table 72.2
Cycling conditions

For indoor end-use applications	For outdoor end-use applications
24 hours at T ^a followed immediately by a minimum 96 hours exposure at 35.0 ±2.0°C (95.0 ±3.6°F), 90 percent relative humidity, followed by 8 hours at 0.0 ±2.0°C (32.0 ±3.6°F).	A minimum of 24 hours immersed in 25.0 ±2.0°C (77.0 ±3.6°F) water; followed immediately by 24 hours at T ^a followed immediately at least 96 hours at 35.0 ±2.0°C (95.0 ±3.6°F), 90 percent relative humidity; followed by 8 hours at -35.0 ±2.0°C (-31.0 ±3.6°F).
^a T is the normal operating temperature, but not less than 60°C (140°F).	

72.2.2 HUMIDITY CONDITIONING – Specimens are to be conditioned for 7 days at 90 – 95 percent relative humidity at 35.0 ±1.0°C (95.0 ±1.8°F). Within two minutes of removal from the test chamber or sealed transporting container, the specimens are to be subjected to the Voltage Transient and Dielectric Voltage-Withstand and Breakdown-Voltage Test described in 72.1.3 and 72.1.4.

72.2.3 THERMAL CONDITIONING – Specimens are to be conditioned for 1000 hours in a full draft circulating air oven maintained at the oven temperature taken from the appropriate thermal-endurance-profile line in Figure 72.1. The thermal-endurance-profile lines for ANSI Types FR2, FR3, FR4, XXXPC, and GPO-2 industrial laminates may be representative of other laminates. After conditioning, the specimens are to be cooled for a minimum of 40 hours at $23.0 \pm 2.0^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and a 50 ± 5 percent relative humidity and then be subjected to the Voltage Transient and Dielectric Voltage-Withstand and Breakdown-Voltage Test described in 72.1.3 and 72.1.4.

Exception: On the same thermal endurance profile line in Figure 72.4, a shorter or longer time at a higher or lower temperature, respectively, may be employed if agreeable to all concerned, but a period of not less than 300 hours is to be used.

73 Tape Adhesion Test

73.1 General

73.1.1 The test method for conducting the Tape Adhesion Test shall be in accordance with ASTM D3359. This test method is applicable to the brittle coatings of metallized parts that are described in Section 48.

73.1.2 Test panels shall be selected as shown in Table 73.1 for a full and short program of test. A full program is performed when the combination of the coating and substrate have not been previously tested by the coating or substrate supplier. A short program is performed when the coating and substrate have been previously tested by the coating or substrate supplier.


Exception: No testing is required for a substrate which is generically equivalent and which is similar to a substrate from the same manufacturer which has been tested with the same coating of that manufacturer.

Table 73.1

Program	Number of Panels	Conditioning
Full	12	73.5(a), (b), (c) and (d)
Short	6	73.5(a) and (b)

73.1.3 The tape used to measure adhesion by ASTM D3359 shall have a Tape Adhesion Strength as determined per ASTM D1000 of 36 ± 2.5 oz/

Figure 72.4
Conditioning time versus oven temperature for normal operating temperature of conformal coatings

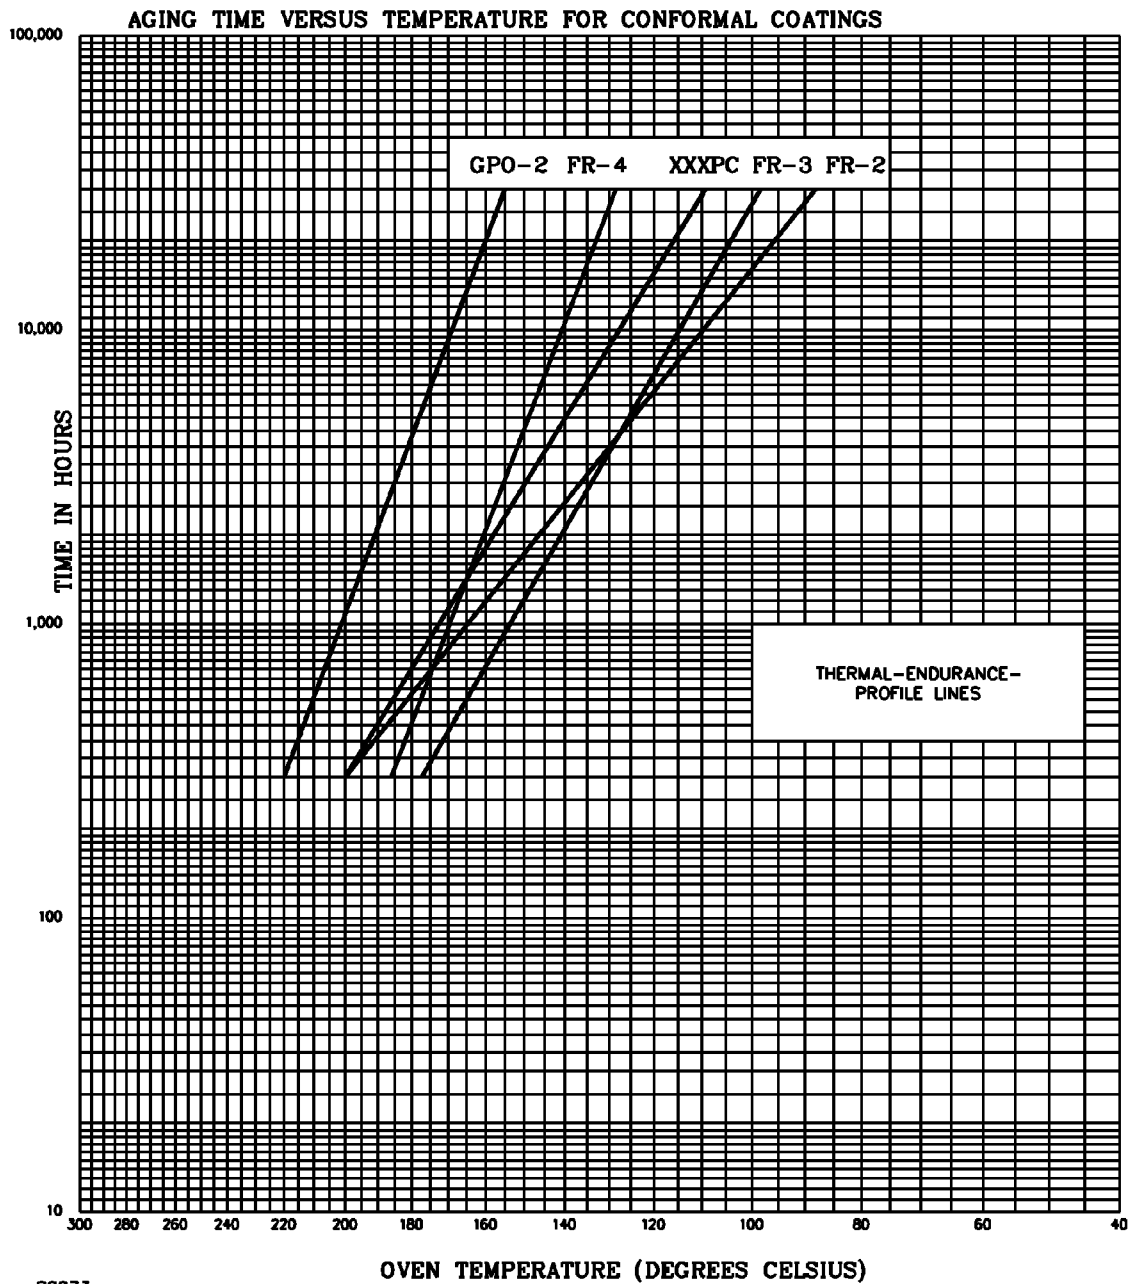

S2273

73.2 Samples

73.2.1 Test panels shall be approximately 76 x 127 mm (3 by 5 inches), rigid, flat and with no obstructions (e.g. ridges, bosses, and ventilation openings).

73.2.2 Each test panel shall be coated with the minimum thickness of coating being investigated.

73.3 Coating Thickness Measurement

73.3.1 Prior to environmental conditioning, the coating thickness for each panel is to be measured. The thickness shall be determined by a mechanical device such as a micrometer, an optical device, or a radioactive device which shall render an actual coating thickness at any given point.

73.4 Sample Preparation

73.4.1 For coating thicknesses up to 0.051 mm (2 mils), an 11 cross-cut is to be made. For coating thicknesses between 0.051 to 0.127 mm (2 to 5 mils), a 6 cross-cut is to be made. For coatings of greater than 0.127 mm (5 mils) an X cut is to be made. The cuts are to be made in accordance with ASTM D3359-95a, Test Method A or B.

73.4.2 Cuts are to be made to all panels prior to conditioning. They are to be made on a flat surface by using a sharp blade to cut through the coating to the substrate in one steady motion. If the blades are not sharp, excess coating and substrate will be removed by the rough cut. Blades should be examined for sharpness after 50 cuts or if rough cuts are observed.

73.4.3 After cutting, brush lightly over the surface to remove excess flakes and ribbons.

73.5 Conditioning

a) As-Received – Three specimens are to be conditioned for at least 40 hours at a temperature of $23.0 \pm 2.0^{\circ}\text{C}$ ($73.0 \pm 3.6^{\circ}\text{F}$) and a relative humidity of 50 ± 5 percent prior to testing.

b) Thermal Cycling Evaluation

- 1) Three specimens are to be conditioned for 1 hour at 10.0 ± 0.0 , minus 1.0°C (18.0 ± 0.0 , minus 1.8°F) higher than the normal-use temperature of the plastic, but not less than 70°C (158°F) in any case, followed by
- 2) One hour at $23.0 \pm 2^{\circ}\text{C}$ ($73.0 \pm 3.6^{\circ}\text{F}$) and a relative humidity of 50 ± 5 percent, followed by
- 3) One hour at minus $29.0 \pm 2.0^{\circ}\text{C}$ (minus $20.2 \pm 3.6^{\circ}\text{F}$) followed by
- 4) One hour at $23.0 \pm 2^{\circ}\text{C}$ ($73.0 \pm 3.6^{\circ}\text{F}$) and a relative humidity of 50 ± 5 percent, followed by
- 5) Steps 1 – 4 repeated two more times.

c) Oven - Three specimens are to be conditioned for 14 days at 10.0 ± 0.0 , minus 1.0°C (18.0 ± 0.0 , minus 1.8°F) higher than the normal-use temperature of the plastic (minimum 70°C), with testing at the end of 14 days.

- d) Humidity - A second set of three specimens is to be conditioned for 14 days at $35.0 \pm 0^\circ\text{C}$ ($95.0 \pm 3.6^\circ\text{F}$) and 90 ± 5 percent relative humidity with testing at the end of 14 days.

73.6 Results

73.6.1 The test specimens shall be examined, both as received and after conditioning, as follows:

- a) Examine the grid area and the tape for removal of coating from the substrate (for adhesion failure) or separation of the coating from itself (cohesion failure).
- b) Record the percentage of coating removal from the substrate for each specimen. If the removal is cohesive, record the percentage of coating removal, using the tape as a reference.

Note: Removal due to cutting is not counted as part of the adhesive and cohesive bond removal. Removal due to cutting is evident as a pattern of traces that follow the edges of the cross hatch lattice typically seen on the tape. These are micro fractures caused by blades pressing through the coated substrate. These fractures are strong enough to resist the brushing-off of flakes and ribbons yet weak enough to be pulled up by the Tape Test.

Note: Unlike adhesive removal where the substrate becomes exposed cohesive removal is indicated by the tape containing a layer or a dusting of coating.

73.6.2 If 5% or more of the coating is removed in Method B of ASTM D-3359 and if more than 0.8 mm (1/32 inch) of the coating is removed along the incision of the "X" cut in Method A of ASTM D-3359, the results are not acceptable.

74 Leakage Current Test

74.1 All exposed conductive surfaces are to be tested for leakage currents. The leakage currents from these surfaces are to be measured to the grounded supply conductor individually as well as collectively where simultaneously accessible, and from one surface to another where simultaneously accessible. Parts are considered to be exposed surfaces unless guarded by an enclosure considered to provide protection against electric shock. Surfaces are considered to be simultaneously accessible when they can be readily contacted by one or both hands of a person at the same time. These measurements do not apply to terminals operating at voltages which are not considered to involve electric shock.

74.2 If a conductive surface other than metal is used for the enclosure or of the enclosure, the leakage current is to be measured using a metal foil with an area of $10\text{ cm} \times 20\text{ cm}$ in contact with the surface. Where the surface is less than $10\text{ cm} \times 20\text{ cm}$, the metal foil is to be the same size as the surface. The metal foil is not to remain in place long enough to affect the temperature of the appliance.

74.3 The measurement circuit for leakage current is to be as shown in Figure 74.1. The ideal instrument is defined in (a) – (d). The meter which is actually used for a measurement need only indicate the same numerical value for a particular measurement as would the defined instrument. The meter used need not have all the attributes of the defined instrument.

- a) The meter is to have an input impedance of 1500 ohms resistive shunted by a capacitance of 0.15 microfarad.
- b) The meter is to indicate 1.11 times the average of the full-wave rectified composite waveform of voltage across the resistor or current through the resistor.

c) Over a frequency range of 0 – 100 KHz, the measurement circuitry is to have a frequency response (ratio of indicated to actual value of current) equal to the ratio of the impedance of a 1500 ohm resistor shunted by a 0.15 microfarad capacitor to 1500 ohms. At an indication of 0.5 or 0.75 mA, the measurement is to have an error of not more than 5 percent at 60 Hz.

d) Unless the meter is being used to measure leakage from one part of an appliance to another, the meter is to be connected between the accessible parts and the grounded supply conductor.

74.4 A sample of the appliance is to be tested for leakage current starting with the as-received condition but with its grounded conductor, if any, open at the attachment plug. The as-received condition is without prior energization except as may occur as part of the production-line testing. The supply voltage is to be adjusted to 120 V. The test sequence, with reference to the measuring circuit, (Figure 74.1) is to be as follows:


a) With switch S1 open, the appliance is to be connected to the measuring circuit. Leakage current is to be measured using both positions of switch S2 and with the appliance switching devices in all their normal operating positions.

b) Switch S1 is then to be closed energizing the appliance, and within a period of 5 seconds, the leakage current is to be measured using both positions of switch S2, and with the appliance switching device in all their normal operating positions.


c) The leakage current is to be monitored until thermal stabilization. Both positions of switch S2 are to be used in determining this measurement. Thermal stabilization is to be obtained by operation as in the temperature test.

74.5 Normally a sample will be carried through the complete leakage current test program as covered by 74.4, without interruption for other tests. With the concurrence of those concerned, the leakage current tests may be interrupted for the purpose of conducting other non-destructive tests.


Figure 74.1
Leakage-current measurement circuit

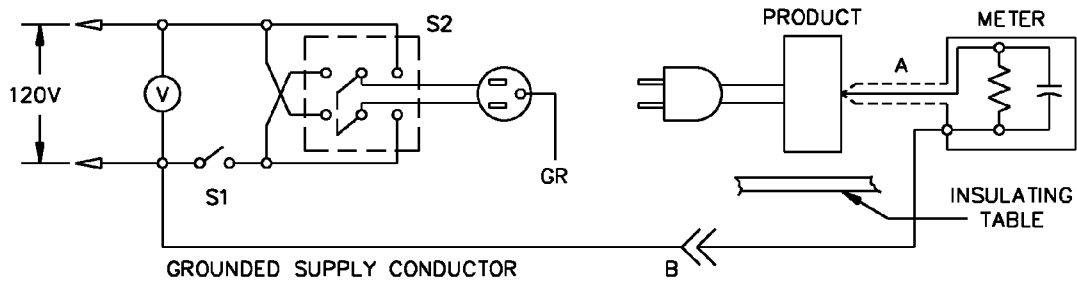

Appliance intended for connection to a 120 V power supply.

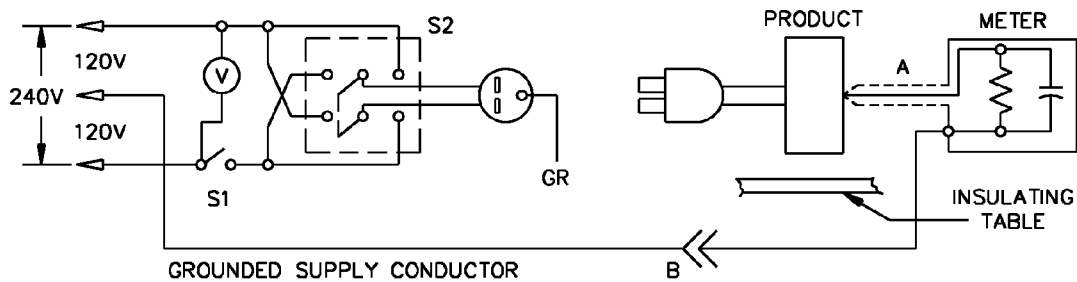

Appliance intended for connection to a 3-wire, grounded neutral power supply, as illustrated above.

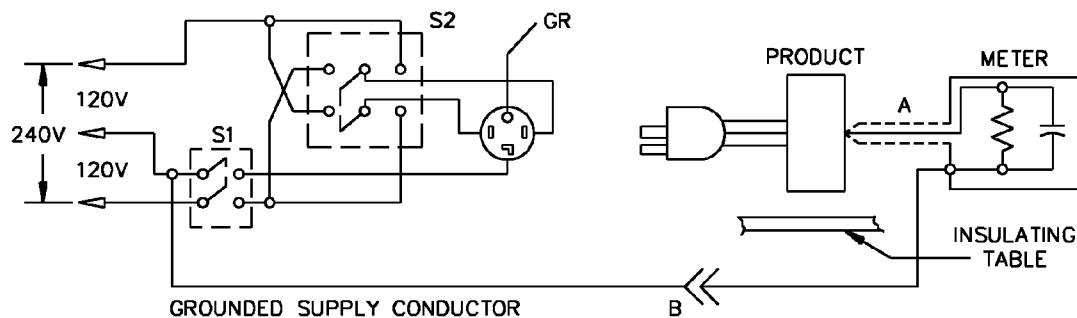

Appliance intended for connection to a 3-wire, grounded neutral power supply, as illustrated above.

A PROBE WITH SHIELDED LEAD.

B SEPARATED AND USED AS CLIP WHEN MEASURING CURRENTS FROM ONE PART OF APPLIANCE TO ANOTHER.

LC100N

75 Glow-Wire End-Product Test

75.1 General

75.1.1 This method is intended to determine compliance of an end-product to satisfactorily withstand the effects of an electrically heated wire as described in The Method for Glow-Wire End-Product Test, IEC 695-2-1/1.

75.2 Significance

75.2.1 Either during normal operation, under unusual conditions, or as a result of malfunctions, some components of an electrical apparatus, such as wires or other conductors may become abnormally hot. When these overheated parts are in intimate contact with the insulating material, ignition may occur. This test is intended to determine compliance, under these conditions, of an insulating material incorporated in and end-product.

75.3 Apparatus

75.3.1 The basic components of the test apparatus as follows:

- a) Glow-Wire – Nichrome wire (nominal 80 percent nickel /20 percent chromium) with a nominal 4.0 mm (0.16 inch) diameter formed to the dimensions shown in Figure 75.1.
- b) Thermocouple – A sheathed fine-wire thermocouple, having an overall nominal diameter of 0.5 mm (0.02 inch) and wires (type K) of, for example, NiCr and NiAl suitable for continuous operation at temperatures up to 960°C (1760°F) with the welded point located inside the sheath. The thermocouple is arranged in a pocket hole, drilled in the tip of the glow-wire, as shown in the detail of Figure 75.1. Maintain the thermal contact between the tip of the thermocouple and the end and sides of the bored hole.
- c) Temperature Indicator – A temperature indicator for Type K thermocouples capable of reading to 1000°C (1832°F) and with an accuracy of 1°C (1.8°F).
- d) Supply Circuit – current transformer with a 2.1 V open circuit, secondary voltage. The transformer having sufficient kVA to supply from 0 to 115 A to the test circuit. There must also be a means for smooth and continuous adjustment of the power level to achieve the desired glow-wire tip temperature.
- e) Test Fixture – Designed so that the glow-wire is kept in a horizontal plane and applies a force of 1.0 ± 0.2 N to the specimen. Maintain the force as the glow-wire is moved horizontally towards the specimen or visa versa over a distance of at least 7mm (0.28 inch).
- f) Flaming Particle Indicator – A piece of flat smooth white pinewood board, approximately 10 mm (0.39 inch) thick, and in close contact with a single layer of tissue paper, located a distance of 200 ± 5 mm (7.87 ± 0.20 inch) below the glow-wire tip. Use undyed, soft, strong, lightweight tissue paper weighing between 12 and 30 g/m².

Note: If known, replace the white pinewood board and tissue paper with the materials normally situated around and underneath the end-product during normal operation. Also, adjust the distances of these materials from the end-product to the distances usually encountered during normal operation.

75.4 Specimens

75.4.1 The specimen should be the complete equipment, sub-assembly or component under investigation. If this is not possible, cut off a piece of the equipment containing the part under investigation.

75.5 Conditioning

75.5.1 The specimen is to be conditioned at $23 \pm 2^{\circ}\text{C}$ ($73.4 \pm 3.6^{\circ}\text{F}$) and 50 ± 5 percent relative humidity for at least 40 hours prior to testing.

75.6 Procedure

75.6.1 The tip of the glow-wire is to be applied to the thinnest portion of the specimen that is likely to be subjected to thermal stresses during normal use (but preferably not less than 15 mm (0.59 inch) from any edge). Mount the specimen in the test fixture so that the surface coming in contact with the tip of the glow-wire is vertical. Electrically heat the clean glow-wire to a temperature determined from Table 75.1. Keep this temperature (and the heating current) constant for at least 60 s prior to testing. The tip of the glow-wire is then brought into contact with the specimen with an applied force of 1.0 ± 0.2 N for 30 ± 1 s. Maintain the glow-wire current constant during this period and mechanically limit the movement of the glow-wire tip into the specimen to 7 mm (0.28 inch).

75.6.2 If ignition occurs, note the time from the beginning of the glow-wire application to the time at which the specimen, the parts surrounding the specimen, or the flaming particle indicator ignites. For the purposes of this method, ignition is defined as either a visible flame on the specimen (or parts surrounding the specimen) for more than 5 seconds, or ignition of the flaming particle indicator due to particles falling from the specimen.

75.6.3 After the 30 ± 1 s application period, remove the glow-wire from the specimen at a rate which limits any further heating of the specimen, but slowly enough so as to avoid any movement of air which might affect the results of the test. Continue observation of the specimen, the parts surrounding the specimen, and the flaming particle indicator, for an additional 30 ± 1 s. Disregard ignition of the flaming particle indicator due to flaming particles falling from the glow-wire. If ignition occurred during the application of the glow-wire, note whether or not all flaming and glowing ceased within 30 ± 1 s after removal of the glow-wire.


75.6.4 The specimen is considered to have satisfactorily withstood the glow-wire end-product test if either:

- a) There is no ignition, or
- b) All flaming and glowing of the specimen, the parts surrounding the specimen, and (if a material was used other than the tissue paper/pinewood board) the flaming particle indicator, ceases within 30 ± 1 s after removal of the glow-wire. The results are not acceptable if the specimen, the parts surrounding the specimen, or the flaming particle indicator are completely consumed.

Table 75.1
Glow-wire temperature requirements based upon a products functional end-use application

Application type	Glow-wire temperature
Portable, attended, intermittent duty, household use equipment	650°C
All other portable equipment	750°C
Fixed or stationary equipment	750°C

Figure 75.1
Glow-wire configuration

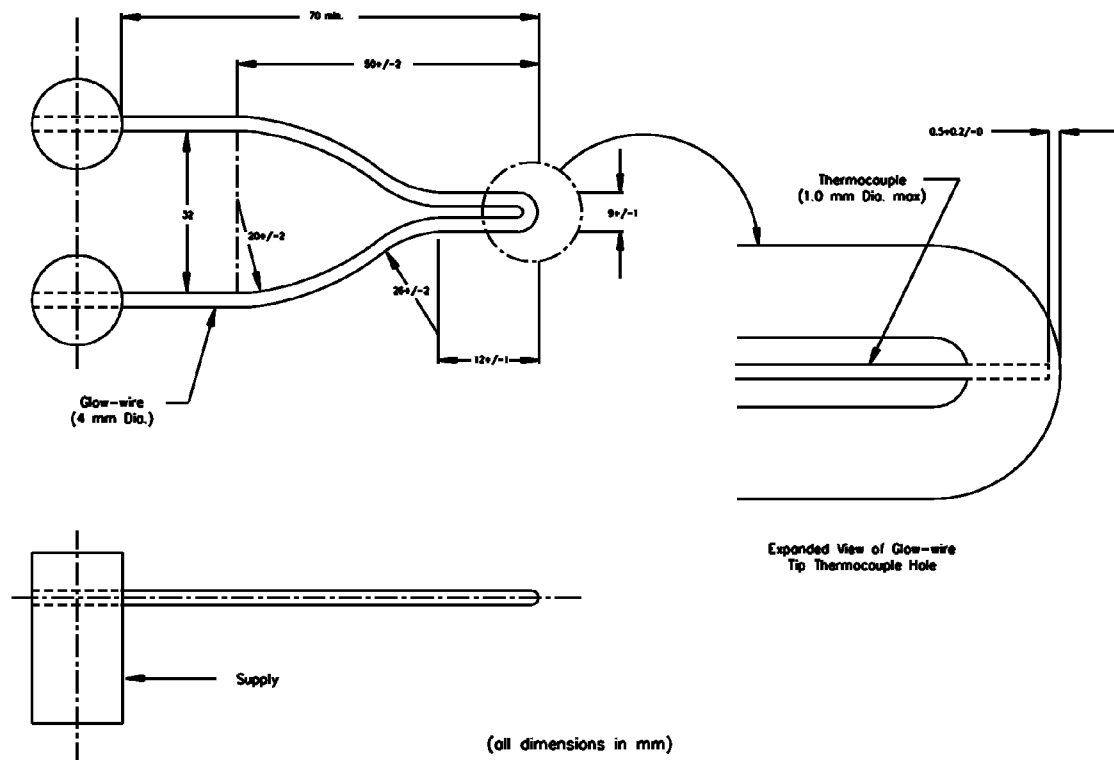

SM1224

MARKING**76 General**

76.1 Material containers shall be marked with the following:

- a) The manufacturer's or private labeler's name or identifying symbol.
- b) A distinctive material designation.

76.2 If a manufacturer produces the material at more than one factory, each material container shall have a distinctive marking to identify it as the product of a particular factory.

No Text on This Page

APPENDIX A

Guidelines for Evaluation of Substitute Polymeric Materials

A Alternate Enclosure Material Considerations

A.1 From time-to-time, it may be necessary to select alternative or substitute materials for use. These considerations apply only to alternate materials for a given part. Changes in part dimensions and, in particular, reductions in material thickness, generally require an evaluation using all the end-product tests.

A.2 It may not be necessary that a complete series of end-product tests be required, provided that equivalent or better material properties can be demonstrated by standardized small-scale tests on the candidate material when compared to the properties of a material having acceptable application performance.

Exception: A candidate material that does not provide equivalent material properties to the properties of a material having acceptable application performance, may be acceptable providing that the candidate material possesses the minimum performance level required in Table 4.1 and/or Table 8.1 for the application.

Revised A.2 effective June 1, 2004

A.3 Table A.1 indicates general guidelines that can be used to evaluate alternate or substitute materials if small-scale test data is available. It should be noted that these guidelines apply to substitutions within the same class of materials (thermoplastic to thermoplastic and thermoset to thermoset).

A.4 Except as indicated in Table A.1, if the originally tested material was considered acceptable based upon special tests (for example, determining the resistance of the material to ultraviolet light for an outdoor application or tests required by the end-product standard such as resistance to creep, endurance, and overload), these tests are to be conducted on the candidate material to determine acceptability.

A.5 In Table A.1, the material property parameters are tabulated in column 1. Acceptance guidelines for those situations where the candidate material properties are equivalent to or better than the characteristics of the original material are tabulated in column 2.

A.6 For those properties where the candidate material is not equal to or better than those for the original material, column 3 of Table A.1 indicates the considerations that should be given to the original requirements for the specific application.

A.7 Column 4 of Table A.1 indicates the required end-product tests needed if the candidate materials' properties are not equivalent to the original material's properties nor meet the requirements for the application.

A.8 As an example, if the original enclosure material was a Type 66 nylon (PA66) and the candidate material is a polycarbonate (PC), then for each property parameter tabulated in column 1, the end-product test in column 4 would be required if the candidate material properties are not equivalent to the original material properties (column 2) or does not meet the original requirements for the specific application (column 3).

Table A.1
Alternative material consideration

Revised Table A.1 effective June 1, 2004

Material property parameters (Column 1)	Candidate material characteristics, equivalent or better than characteristics of the original material considered acceptable for the application (Column 2)	Candidate material characteristics, equivalent or better than those required for the application (Column 3)	Candidate material characteristics not equivalent to original material characteristics nor meets those required for the application (Column 4)
FLAMMABILITY (flammability classification at use thickness and color)	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct flame test on part or enclosure (See Flammability – 12 mm Flame, Section 17, Flammability – 127 mm (5 inch) Flame, Section 19, Enclosure Flammability – Large Mass Considerations, Section 21)
ELECTRIC STRENGTH (1) Volume resistivity (2) Dielectric Strength	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product (1) leakage current tests or insulation resistance complying with 16.3 (2) dielectric withstand complying 12.1
TRACKING RESISTANCE (1) Comparative tracking index or (2) Inclined Plane Tracking	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	(1) Increase spacings to $\geq \frac{1}{2}$ inch (2) Increase spacings to: Refer to applicable end-product considerations.
WATER RESISTANCE (1) Dimensional change after water exposure (2) Properties after water immersion (Outdoor use only) Also see A.4	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product Humidity/immersion tests per 28.2 Material is not suitable for prolonged exposure to water
ULTRA-VIOLET RESISTANCE Properties after ultra-violet exposure. (Outdoor use only) Also see A.4	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Material is not suitable for exposure to weather
RESISTANCE TO ELECTRICAL IGNITION (1) Hot- wire ignition and flame classification combination, (2) High current arc resistance and flame classification combination	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product: Abnormal Overload Test or Glow Wire Test per section 14 Arc-Resistance Test per par. 13.3 – 13.5
MECHANICAL (See note b)	Candidate Material Considered Acceptable ^a	NA	Conduct end-product

Table A.1 Continued on Next Page

Table A.1 Continued

Material property parameters (Column 1)	Candidate material characteristics, equivalent or better than characteristics of the original material considered acceptable for the application (Column 2)	Candidate material characteristics, equivalent or better than those required for the application (Column 3)	Candidate material characteristics not equivalent to original material characteristics nor meets those required for the application (Column 4)
(1) Tensile or Flexural Strength (2) Tensile or Izod impact or Charpy			(1) Crushing Resistance per 23.1 and Strain Relief per 33.1 or Conduit tests per UL 50 or UL 508 (2) Impact Resistance per Sec. 24 and Strain Relief per 33.1 or Conduit tests per UL 50 or UL 508
DEFORMATION (See notes a) (1) Heat Deflection (2) Creep	Candidate Material Considered Acceptable ^a	NA	Conduct end-product Mold Stress-Relief test. Test is not required for thermoset materials.
	All alternative or substitute materials are to be subjected to end product creep tests (see Section 25) unless: a) The candidate material is of the same composition b) The candidate has equivalent of higher small-scale heat deflection, vicat softening, or ball pressure temperature indices. c) The candidate has equivalent creepage characteristics based on tests and/or test data (Note – the test results being compared must have the same test parameters) Creep evaluations are not required for rigid thermoset materials.		
MAXIMUM USE TEMPERATURE	Refer to Sections 34 – 40		
SPECIAL END-USE CONSIDERATIONS^b	If indicated by the applicable path in Table 4.1 all alternative or substitute materials are to be subjected to the abnormal operation (29.1) and severe conditions tests (30.1), unless the candidate is of the same generic type with the same percentage and type of fillers, reinforcements, heat stabilizers and flame retardants.		

^a All alternative or substitute materials are to be subjected to end-product impact, crush, conduit, strain relief and mold stress-relief tests unless:

1) The candidate material is of the same generic type with the same percentage and type of fillers and reinforcements, and

2) The candidate material has equivalent or higher small-scale tensile or flexural strength, tensile or izod impact and heat deflection ratings indicated above.

^b See A.4

No Text on This Page

November 29, 2001
Superseded requirements for
the Standard for
Polymeric Materials – Use in Electrical Equipment Evaluations
UL 746C, Fifth Edition

The requirements shown are the current requirements that have been superseded by requirements in this edition. To retain the current requirements, do not discard the following requirements until the future effective dates are reached.

3.3 ATTENDED INTERMITTENT-DUTY HOUSEHOLD APPLIANCE – An appliance intended for infrequent and short-time use in residences and used only while attended, such as an electric knife, electric can opener, hair dryer and the like.

3.3 effective until June 1, 2004

4.1 The requirements for polymeric enclosures, or parts of enclosures of appliances and equipment are contained in Sections 6 – 8.

4.1 effective until June 1, 2004

6 Portable Appliances

6.1 Portable appliances having an enclosure of polymeric material shall comply with the applicable requirements in Figure 6.1. The use of Figure 6.1 is explained in 6.7 – 6.11.

6.1 effective until June 1, 2004

6.2 The requirements in Portable Appliances, Section 6, do not cover the additional considerations that must be given to enclosures employing large masses of polymeric materials. Whether or not such enclosures reduce the risk of electric shock or fire, or both, consideration should be given to the probability of ignition of the material by sources within the equipment or by external sources.

6.2 effective until June 1, 2004

6.3 A polymeric material which can contact electrically live parts, or is within 0.79 mm (1/32 inch) of uninsulated live parts, shall comply with the requirements indicated in Table 8.1.

6.3 effective until June 1, 2004

6.4 The requirements in Portable Appliances, Section 6, do not cover the additional considerations that must be given to enclosure materials exposed to oils, acids, solvents, cleaning agents, and the like in use. The performance of the material shall not be adversely affected by such environments (if encountered in the end-use application) as determined by applicable tests as detailed in the Standard for Polymeric Materials – Short Term Property Evaluation, UL 746A.


6.4 effective until June 1, 2004

6.5 The thermal endurance of a polymeric material shall be considered with respect to the requirements in Sections 34 – 39.

6.5 effective until June 1, 2004

Figure 2.1
Flowchart of UL 746C procedures to evaluate polymeric parts

Figure 2.1 effective until June 1, 2004

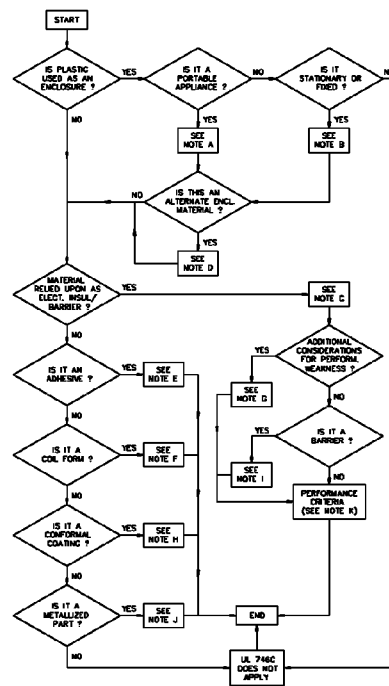

S3553

- A. Section 6
- B. Section 7
- C. Sections 8, 9, Table 8.1
- D. Appendix A
- E. Sections 41 – 43, 71
- F. Section 44
- G. Table 8.2
- H. Sections 45, 72
- I. Table 9.1
- J. Sections 46 – 48, 73
- K. Sections 10 – 40

6.6 Polymeric material used to enclose a metal housing that encloses insulated or uninsulated live parts or as a decorative part, shall be classed either 5VA, 5VB, V-0, V-1, V-2, or HB by the burning tests described in the Standard for Tests for Flammability of Plastic Materials, UL 94.

Exception No. 1: Decorative parts are not required to be made of a material classed 5VA, 5VB, V-0, V-1, V-2, or HB, providing the part: does not occupy a volume greater than 2 cubic centimeters (0.122 cubic inch), does not have any dimension greater than 3 cm (1.18 inch), and is located so it cannot propagate flame from one area to another or bridge between a possible source of ignition and other ignitable parts.


Exception No. 2: A material is to be considered equivalent if it complies with the requirements in 17.1, 52.1 – 52.5, 19.1, 54.1 – 54.5, when flame tested as used in the equipment. The use of a flame-retardant coating applied to the inside of a polymeric enclosure is not acceptable unless the coating/material interface is found to be acceptable by separate investigation (see Flame-Retardant Coatings, Section 22).

6.6 effective until June 1, 2004

Figure 6.1
Enclosure requirements for portable appliances

Figure 6.1 effective until June 1, 2004

Part 1 – Conditions of use

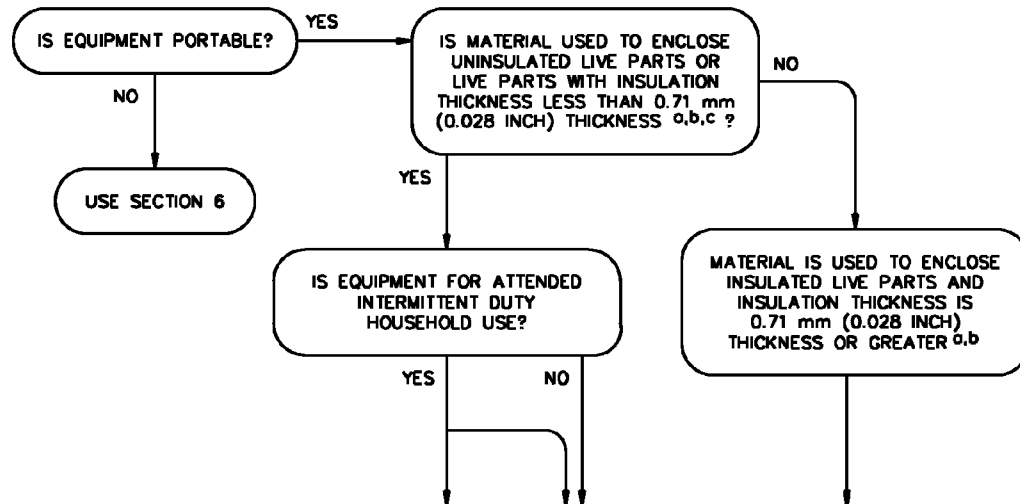

Part 2 – Applicable requirements

Minimum flammability rating	HB	v e,f	HB or v e,f
Electrical/Mechanical Properties per Table 8.1	Yes	Yes	Yes
Hot-Wire Ignition per Hot-Wire Ignition (HWI) – Abnormal Overload Test, Section 14	Max PLC of 4	Max PLC of 4 ^g	No
Impact Test per Resistance to Impact, Section 24	Yes	Yes	Yes
Abnormal Operation Test per 29.1	Yes	Yes	Yes
Severe Conditions Test per 30.1	Yes	No	No
Mold-Stress Relief Distortion per:			
A. 63.1	No	Yes	Yes
B. 63.2	Yes	No	No
Input after Mold-Stress Relief Distortion per 32.2	Yes	No	No
Creep per Section 25 ^h	Yes	Yes	Yes
Strain Relief Test per 33.1 ^d	Yes	Yes	Yes
Thermal Endurance per Sections 34 – 40	Yes	Yes	Yes
Volume Resistivity per Volume Resistivity, Section 16	Yes	Yes	No

S3468G

(Continued)

Figure 6.1 (Cont.)

- ^a The insulation thickness of the component parts is considered to be equivalent to 0.71 mm (0.028 inch) if the component complies with the requirements for the component.
- ^b 0.71 mm (0.028 inch) thickness is generally required for internal insulation. However, if insulation or wire insulated with less than 0.71 mm (0.028 inch) insulation thickness (light duty) is provided that is restricted for use in chassis, channels or other internal areas where contact during user servicing or user operation of the equipment is unlikely, the insulation is considered to be equivalent to 0.71 mm (0.028 inch).
- ^c Enamel insulated magnet wire is to be considered as an uninsulated live part.
- ^d This test is required only if the strain-relief means is secured to the enclosure or is an integral part of the polymeric enclosure.
- ^e V = V-0, V-1, V-2 classed material, or enclosure material complies with the 12 mm end-product flame test described in Flammability – 12 mm Flame, Section 17.
- ^f As an alternative to the 12 mm end-product flame test, the 3/4 inch end-product flame test may be used.
- ^g The Hot-Wire Ignition criteria is applied only for materials used to enclose uninsulated live parts.
- ^h This test is only required if the equipment enclosure is subject to mechanical stresses from internal or external sources (such as bending, compression, or tensile loading) and the material used is not a rigid thermoset.

S3468F

6.7 The path shown on Part 1 of Figure 6.1 that matches the conditions of use for the polymeric material under consideration determines the requirements to be met.

6.7 effective until June 1, 2004

6.8 Following the path in Part 1 of Figure 6.1 (selected using 6.7) leads to Part 2 and the applicable material requirements. It may be necessary to determine whether the equipment is of an attended, intermittent-duty, household-use type before the applicable material requirements can be selected.

6.8 effective until June 1, 2004

6.9 Part 2 of Figure 6.1 indicates the required tests (marked with a "yes" and with a footnote reference if necessary) under the applicable path determined in Part 1 of Figure 6.1.

6.9 effective until June 1, 2004

6.10 For example, a polymeric material used to enclose uninsulated live parts, such as a heating element, of an unattended household-use electric toaster, shall only be made from a V-rated material (second path from the left of Figure 6.1), specifically either V-0, V-1, V-2 or a material that complies with the requirements in 17.1, and 52.5 – 52.5.

6.10 effective until June 1, 2004

6.11 Using this example, the material shall comply with the applicable requirements for:

- a) Hot-wire ignition per Section 14,
- b) Resistance to impact per 24.1 and 58.3,
- c) Mold stress-relief distortion per 63.1,

- d) Creep per Section 25,
- e) Strain relief per 33.1,
- f) Abnormal operation per 29.1,
- g) Enclosure flammability per Section 17 or 18.
- h) Mechanical/electrical properties per Table 8.1, and
- i) Thermal endurance per Sections 34 – 40.

6.11 effective until June 1, 2004

7 Fixed or Stationary Equipment

7.1 Electrical equipment that is fixed or stationary and not easily carried or conveyed by hand and that has an enclosure of polymeric material shall comply with the applicable requirements in Table 8.1 and Figure 7.1. The use of Figure 7.1 is explained in 7.7 – 7.11.

7.1 effective until June 1, 2004

7.2 The requirements in Fixed or Stationary Equipment, Section 7, do not cover the additional considerations that must be given to enclosures employing large masses of polymeric materials. Whether or not such enclosures protect against electric shock and/or the likelihood of fire, consideration should be given to the probability of ignition of the material by sources within the equipment or by external sources. See 21.1 for large mass flammability considerations.

7.2 effective until June 1, 2004

7.3 A polymeric material used for the support of electrically live parts, shall comply with the requirements indicated in Table 8.1.

7.3 effective until June 1, 2004

7.4 The requirements in Fixed or Stationary Equipment, Section 7, do not cover the additional considerations that must be given to enclosure materials exposed to oils, acids, solvents, cleaning agents, and the like in production equipment. The performance of the material shall not be adversely affected by such environments (if encountered in the end-use application) as determined by applicable tests as detailed in the Standard for Polymeric Materials – Short Term Property Evaluation, UL 746A.

7.4 effective until June 1, 2004

7.5 See Sections 34 – 40 for considerations of thermal endurance and Mechanical/Electrical Property Considerations, Section 8, for additional considerations of the mechanical/electrical properties of enclosure materials.

7.5 effective until June 1, 2004

7.6 Polymeric material used to enclose a metal housing that encloses insulated or uninsulated live parts or as a decorative part, shall be classed either 5VA, 5VB, V-0, V-1, V-2, or HB by the burning tests described in the requirements for tests for flammability of plastic materials, UL 94.

Exception No. 1: Decorative parts are not required to be made of a material classed 5VA, 5VB, V-0, V-1, V-2, or HB, providing the part: does not occupy a volume greater than 4000 cubic millimeters (0.24 cubic inch), does not have any dimension greater than 60 mm (2.4 inch) and is located so it cannot propagate flame from one area to another or bridge between a possible source of ignition and other ignitable parts.

Exception No. 2: A material is to be considered equivalent if it complies with the requirements in 17.1, 52.1 – 52.6 or 19.1, 54.1 – 54.5, when flame tested as used in the equipment. The use of a flame-retardant coating applied to the inside of a polymeric enclosure is not acceptable unless the coating/material interface is found to be acceptable by separate investigation (see Flame-Retardant Coatings, Section 22).

7.6 effective until June 1, 2004

7.7 The path shown on Part 1 of Figure 7.1 that matches the conditions of use for the polymeric material under consideration determines the requirements to be met.

7.7 effective until June 1, 2004

7.8 Following the path in Part 1 of Figure 7.1 (selected using 7.7) leads to the applicable requirements and the test considerations to be considered in Part 2 of Figure 7.1.

7.8 effective until June 1, 2004


7.9 Part 2 of Figure 7.1 indicates the required tests (marked with a “yes” and with a footnote reference if necessary) under the applicable path determined in Part 1 of Figure 7.1.

7.9 effective until June 1, 2004

Figure 7.1
Enclosure requirements for fixed or stationary equipment

Figure 7.1 effective until June 1, 2004

Part 1 – Conditions of use

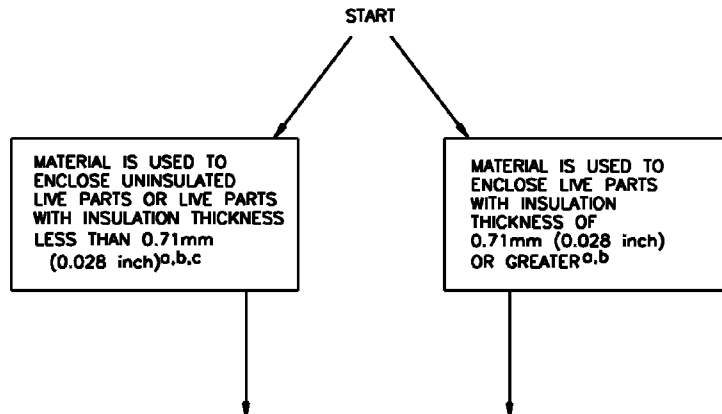

Part 2 – Applicable requirements

Minimum flammability rating	5V ⁱ	5V ⁱ
ELECTRICAL/MECHANICAL PROP. PER TABLE 8.1	YES	YES
DIELECTRIC WITHSTAND PER 12.1	YES	NO
LARGE MASS FLAMMABILITY PER SECTION 21	YES	YES
CRUSHING RESISTANCE PER 23.1	YES	NO
RESISTANCE TO IMPACT PER SECTION 24	YES	YES
UV RESISTANCE PER 27.1	YES ^f	YES ^f
WATER EXPOSURE AND IMMERSION		
A. PROPERTIES PER 28.1	YES ^f	YES ^f
B. DIMENSION PER 28.2	YES	NO
ABNORMAL OPERATION PER 29.1	YES	YES
SEVERE CONDITIONS PER 30.1	YES	YES ^g
MOLD STRESS–RELIEF DISTORTION PER 63.1	YES	YES ^d
INPUT AFTER MOLD STRESS–RELIEF DISTORTION PER 32.1	YES	YES ^g
CREEP PER SECTION 25	YES ^j	YES ^j
CONDUIT CONNECTIONS	YES ^h	YES ^h
STRAIN RELIEF PER 33.1	YES ^e	YES ^e
THERMAL ENDURANCE PER SECTIONS 34 – 40	YES	YES
VOLUME RESISTIVITY PER SECTION 16	YES	NO

S3467G

(Continued)

Figure 7.1 (Cont.)

- ^a The insulation thickness of the component parts is considered to be equivalent to 0.71 mm (0.028 inch) if the component complies with the requirements for the component.
- ^b 0.71 mm (0.028 inch) thickness is generally required for internal insulation. However, if insulation or wire insulated with less than 0.71 mm (0.028 inch) insulation thickness (light duty) is provided that is restricted for use in chassis, channels or other internal areas where contact during user servicing or user operation of the equipment is unlikely, the insulation is considered to be equivalent to 0.71 mm (0.028 inch).
- ^c Enamel insulated magnet wire is to be considered as an uninsulated live part.
- ^d This test is required only if failure of the material causes a stress on the junction between a lead and a terminal of a component. If the strain-relief test is acceptably performed for components with integral leads either as a separate test or as part of the regular test procedure for the component, it shall be considered that the material does not cause a stress on the junction between the lead and a terminal of the component.
- ^e This test is required only if the strain-relief means is mounted to the enclosure or is a polymeric part of the enclosure.
- ^f This test is required only if the equipment may be exposed to outdoor weather conditions.
- ^g This test is required only if the equipment may be used unattended.
- ^h This test is required only if the equipment is permanently connected electrically to the wiring system. The continuity of the conduit system shall be a metal-to-metal contact. If the integrity of the polymeric enclosure is relied upon to provide for bonding between the parts of the conduit system at any location where conduit may be connected, the bonding shall be evaluated by the requirements contained in the Standard for Enclosures for Electrical Equipment, UL 50. If the polymeric enclosure is intended for connection to a rigid conduit system, it shall acceptably perform when tested using the pullout, torque and bending tests as described in the Standard for Industrial Control Equipment, UL 508.
- ⁱ 5V = 5VA or enclosure material complies with the 5 inch End-Product Flame Test described in Flammability – 127 mm (5 inch) Flame, Section 19.
- ^j This test is only required if the equipment enclosure is subject to mechanical stresses from internal or external sources (such as bending, compression, or tensile loading) and the material used is not a rigid thermoset.

S3467E

7.10 For example, a polymeric material used to enclose uninsulated live parts (such as the motor windings) of a permanently wired, indoor-use ceiling fan shall be made from a 5VA classed material or a material that complies with the requirements in 19.1, 54.1 – 54.5.

7.10 effective until June 1, 2004

7.11 Using the above example, the material shall also comply with the applicable requirements for:

- a) Electrical/mechanical properties per Table 8.1,
- b) Dielectric strength per 12.1,
- c) Flammability testing per Flammability– 127 mm (5 inch) Flame, Section 19 and Enclosure Flammability – Large Mass Considerations, Section 21,
- d) Crushing resistance per 23.1,
- e) Resistance to impact per 24.1 and 24.3,
- f) Dimensional change per 28.3,
- g) Abnormal operation per 29.1,
- h) Severe conditions per 30.1,
- i) Mold stress-relief distortion per 63.1,
- j) Input after mold stress-relief distortion per 32.1,
- k) Creep per Section 25.
- l) Conduit connections per footnote h of Figure 7.1, and
- m) Thermal endurance per Sections 34 – 40.

7.11 effective until June 1, 2004

8 Mechanical/Electrical Property Considerations

Title effective until June 1, 2004

8.1 General

8.1.1 Mechanical and electrical properties of materials are to be judged with respect to the particular “end use” application. The requirements in Mechanical/Electrical Property Considerations, Section 8, are intended to establish general minimum acceptable requirements for those applications where the polymeric material is relied upon to reduce the risks of fire and electric shock. In the case where the material’s characteristics do not meet the minimum performance levels specified, recommended engineering considerations will be made.

8.1.1 effective until June 1, 2004

8.1.2 These requirements do not cover the additional considerations that must be given to applications employing large masses of polymeric materials. Whether or not such materials protect against electric shock or injury to persons, consideration is to be given to the likelihood of ignition of the material by sources inside the product or by sources outside the product. See 21.1 for large mass flammability considerations.

8.1.2 effective until June 1, 2004

8.1.3 These requirements alone do not cover enclosures that provide mechanical support of electrically live parts. For evaluation of such enclosures, Figure 6.1 or 7.1 is to be used in addition to the requirements in Mechanical/Electrical Property Considerations, Section 8.

8.1.3 effective until June 1, 2004

8.1.4 Using Figure 8.1 as a guide, the figurative examples that match the application of the material under consideration determine the applicable properties tabulated in Table 8.1. A material shall provide acceptable levels of performance for each of these applicable properties tabulated in Table 8.1.

Exception: End product tests may be used to determine if the material is acceptable in the application, as indicated in Table 8.2.

8.1.4 effective until June 1, 2004

8.1.5 For example, a polymeric material used in an application that most closely matches figurative example No. 6 of Figure 8.1, would be evaluated with respect to the distortion under load and mold-stress relief, creep, and maximum-use temperature properties indicated in Table 8.1.

8.1.5 effective until June 1, 2004

8.1.6 To determine a polymeric material's performance profile, certain tests are to be performed according to the methods contained in the Standard for Polymeric Materials – Short Term Property Evaluations, UL 746A and the Standard for Polymeric Materials – Long Term Property Evaluations, UL 746B. These tests, general engineering considerations, and minimum performance levels are tabulated in Table 8.1. Specific applications may require different limits than are shown in the general case. Refer to 8.2.1 and 8.2.2 for considerations to be used in determining the acceptability of an insulating material that does not meet with the requirements tabulated in Table 8.1.

8.1.6 effective until June 1, 2004

8.2 Performance weaknesses

8.2 effective until June 1, 2004

8.2.1 Some materials may have performance characteristics that are less than those tabulated in Table 8.1. In such cases, the application must be considered or special tests conducted to determine if the reduced value can be accepted without increasing the likelihood of risk for the particular end-product.

8.2.1 effective until June 1, 2004

8.2.2 Table 8.2 is intended to be used as a guide in determining the acceptability of a material where performance is less than the anticipated level.

8.2.2 effective until June 1, 2004

Table 8.1
Mechanical/electrical property considerations

Table 8.1 effective until June 1, 2004

Property	Test	Method	Units of PLC	Recommended levels related to flammability classification ^a				Applications ^b	Figurative examples from Fig. 8.1	Exceptions based upon engineering considerations
				V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB			
Electric strength	Volume – resistivity	UL 746A	Min Ohm-cm (dry)	50 x 10 ⁶	50 x 10 ⁶	50 x 10 ⁶	50 x 10 ⁶	Material serves as insulation between uninsulated live parts of opposite polarity or between uninsulated live parts and (1) dead metal parts that may be grounded in service or (2) any surface exposed to contact	(1), (2), (3), (8)	See Sec. 16
			Min Ohm-cm (after 90% humidity)	10 x 10 ⁶	10 x 10 ⁶	10 x 10 ⁶	10 x 10 ⁶			
	Dielectric strength	UL 746A	Min V (rms) (both dry & after 90% humidity)	5000	5000	5000	5000	Same as above	(1), (2), (3), (8)	See Sec. 12
Tracking resistance	Comparative tracking index (CTI)	UL 746A	Max ^c PLC					Material surface is in contact with or in close proximity (less than 1/32 inch (0.8mm)) to (a) uninsulated live parts of opposite polarity, or (b) uninsulated live parts and either (1) dead metal parts that may be grounded in service, or (2) any surface exposed to contact Higher CTI values are required where a greater degree of contamination is involved, as follows:	(2), (2), (4)	See Sec.11
				4	4	4	4	Indoor equipment exposed to relatively clean environment		
				3	3	3	3	Outdoor and indoor equipment exposed to moderate contaminate environments		
	CTI	UL 746A	Max ^c PLC	2	2	2	2	Outdoor and indoor equipment exposed to severe contaminate environments		

Table 8.1 Continued on Next Page

Table 8.1 Continued

Recommended levels related to flammability classification ^a								Figuiative examples from Fig. 8.1	Exceptions based upon engineering considerations	
Property	Test	Method	Units of PLC	V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB			Applications ^b
	Inclined-plane tracking	UL 746A	Min time (min) to track 25.4 mm at 2.5 kV excitation	60	60	60	60	Same as above for CTI except that the application voltage range is 601 V-5 kV	(2), (3), (4), (8)	See Sec. 15
				300	300	300	300	Same as above for CTI except that application voltage range 5,001 V-35 kV	(2), (3), (4), (8)	See Sec. 15
Permanence	Dimensional change after water exposure	UL 746A	Max percent change	2	2	2	2	Same as Volume Resistivity above but also includes applications where the material maintains the relative positioning of live parts and the parts could be subjected to high humidity or moisture	(1), (2), (3), (4), (7), (8)	See 28.2.1
Distortion under load	Heat deflection temperature under load or	UL 746A	Min °C at 66 psi	10°C (18°F) greater than the use temperature but not less than 90°C				All applications except decorative parts	(1), (2), (3), (4), (5), (6), (7), (8)	See Sec. 31
	Vicat softening point or			25°C greater than the use temperature but not less than 105°C (221°F)						
	Ball pressure temperature			Greater than the use temperature by the difference between 40°C and the ambient, but not less than 95°C						
Dimensional Change due to External Stresses	Resistance to Creep	UL 746C		Resistance to creep should be evaluated in the specific application				All applications with mechanical stresses due to external sources	(1), (2), (3), (4), (5), (6), (7), (8)	See Sec. 25
Resistance to Electrical Ignition Sources	High current arc resistance to ignition (HAI)	UL 746A	Max PLC ^d	3	2	2	1	Material is in contact with or in close proximity to uninsulated live parts 0.8 mm (1/32 inch) for nonarcing parts or 12.7 mm (1/2 inch) for arcing parts	(1), (2), (3), (4), (5), (8)	See Sec. 13
	Hot wire ignition HWI	UL 746A	Max PLC ^e	4	3	2	2	Material is in contact with or close proximity to uninsulated live parts [less than 0.8 mm (1/32 inch)]	(2), (3), (4), (8)	See Sec. 14

Table 8.1 Continued on Next Page

Table 8.1 Continued

Recommended levels related to flammability classification ^a									Figurative examples from Fig. 8.1	Exceptions based upon engineering considerations
Property	Test	Method	Units of PLC	V-0 VTM-0	V-1 VTM-1	V-2 VTM-2	HB	Applications ^b		
Mechanical	Tensile or flexural strength; tensile, Izod, or Charpy impact	UL 746A	MPa KJ/m ² or J/m notch	Mechanical strength is judged in the application				Material maintains the relative positioning of live parts or encloses live parts	(2), (4), (7), (8)	See Sec. 24
Maximum use temperature index (RTI)	Relative thermal	UL 746A	Minimum °C	The maximum operating temperature of the part shall not exceed materials' temperature limit determined by the method, indicated in Table 34.1 (See Sections 34 – 40)				All applications except decorative parts	(1), (2), (3), (4), (5), (6), (7), (8)	See Sec. 38 – 40
^a Materials classed as 5VA and 5VB only by the Vertical Burning Test described in the requirements for tests for flammability of plastic materials for parts in devices and appliances, UL 94, or a material when flame tested as used in the equipment, complies with the requirements in Flammability - 12 mm flame, Section 17, Flammability - 3/4-inch flame, Section 18, or Flammability - 127 mm (5 inch) flame, Section 19, shall be considered with respect to the recommended performance levels of a material classed as V-1										
^b Materials located in nonhazardous-energy circuitry, as defined in the appropriate end-product standard, shall only be considered with respect to their flammability, distortion under load and mold stress relief, mechanical and maximum use temperature properties except the resistance to electrical ignition sources properly may also be considered if the material is located less than 12.7 (1/2 inch) from arcing parts or sources of ignition.										
^c										
CT1 Range – Tracking Index (Volts)					Assigned PLC					
600 ≤ TI					0					
400 ≤ TI < 600					1					
250 ≤ TI < 400					2					
175 ≤ TI < 250					3					
100 ≤ TI < 175					4					
0 ≤ TI < 100					5					
^d During the HAI test, the electrodes are to be positioned as indicated in 13.2										
HAI Range – mean number of arcs to cause ignition					Assigned PLC					
120 ≤ NA					0					
60 ≤ NA < 120					1					
30 ≤ NA < 60					2					
15 ≤ NA < 30					3					
0 ≤ NA < 15					4					
^e										
HWI Range – mean ignition time					Assigned PLC					
120 ≤ IT					0					
60 ≤ IT < 120					1					
30 ≤ IT < 60					2					
15 ≤ IT < 30					3					
7 ≤ IT < 15					4					
0 ≤ IT < 7					5					

Table 8.2
Additional considerations for performance weaknesses


Table 8.2 effective until June 1, 2004

Test		Additional end product considerations
1.	Volume resistivity	Conduct end product leakage current test – see 16.1
2.	Dielectric strength	Use thicker material section – see 12.1
3.	Comparative tracking index (CTI)	Increase spacings
4.	Inclined Plane tracking	Increase spacings
5.	Permanence	Conduct end product conditioning test – see 28.2
6.	Distortion under load	Conduct end product mold stress-relief distortion test where stress is internal (i.e, results from molding or fabrication process) – see 31.1 Conduct end-product creep test where stress is due to externally applied forces – see Section 25
7.	High current arc ignition (HAI)	Conduct end product arc resistance test – see 13.3 and 13.4
8.	Hot wire ignition (HWI)	Conduct end product abnormal overload test, or end-product Glow-Wire Test – see Hot-Wire Ignition (HWI)) – Abnormal Overload Test, Section 14
9.	Maximum Use Temperature	Conduct end product thermal aging test – see Relative Thermal Index, Section 37, Relative Thermal Capability, Section 38, and Temperature Excursions Beyond the Maximum Use Temperature, Section 40

Figure 8.1
Figurative examples for Table 8.1


Figure 8.1 effective until June 1, 2004

1.

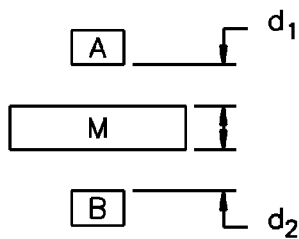


$d_1 + d_2 < S_a$
 WHERE d_1, d_2 = THROUGH AIR SPACING
 S_a = APPLICABLE THROUGH AIR
 SPACING REQUIREMENT

2.




$d < 12.7\text{mm}$
 WHERE d = OVER SURFACE SPACING

3.

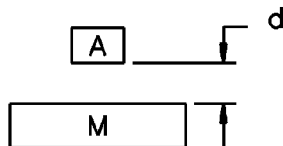

$0 \leq d < 0.8\text{mm}$
 WHERE d = THROUGH AIR SPACING





4.

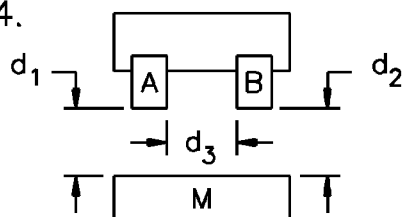

$d_1, d_2 < 0.8\text{mm}$
 $d_3 < 12.7\text{mm}$
 WHERE d_1, d_2 = THROUGH AIR SPACINGS
 d_3 = OVER SURFACE SPACING

S3463B-1

Figure 8.1 (Cont.)
Figurative examples for Table 8.1

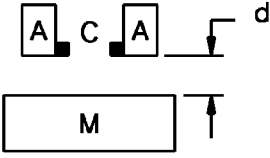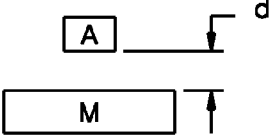5.  $d < 12.7\text{mm}$
WHERE d = THROUGH AIR SPACING
 C = ELECTRICAL CONTACTS, e.g.
SWITCH CONTACTS,
RELAY CONTACTS,
BRUSH/COMMUTATOR CONTACTS
6.  $0.8\text{mm} \leq d < 12.7\text{mm}$
WHERE d = THROUGH AIR SPACING
7.  D = ACCEPTABLE INSULATING MATERIAL
IN CONTACT WITH "A" AND MOUNTED
ON "M" BY SCREWS
8.  $d \geq 12.7\text{mm}$

A = UNINSULATED LIVE PART

B = (1) UNINSULATED LIVE PART HAVING DIFFERENCE IN POTENTIAL FROM A, OR
(2) DEAD METAL PART THAT MAY BE GROUNDED IN SERVICE OR IS EXPOSED TO CONTACT.

M = POLYMERIC MATERIAL UNDER CONSIDERATION

Note: (1) ALL SPACINGS ASSUMED TO BE RELIABLY MAINTAINED.
(2) UNLESS SHOWN IN CONTACT WITH "M", ALL LIVE PARTS ARE SUPPORTED BY STRUCTURES NOT DEPENDENT ON "M".

S3463B-2

9 Internal Barriers

9.1 A vulcanized fiber barrier or liner having a minimum 0.71 mm (0.028 inch) thickness may be an acceptable alternative to maintaining electrical spacing between live parts of opposite polarity or between uninsulated live parts and accessible metal parts where the maximum temperature does not exceed 90°C (194°F).

Exception No. 1: 0.33 mm (0.013 inch) thick vulcanized fiber is acceptable if used in conjunction with an air space of at least one-half of the required spacing.

9.1 effective until June 1, 2004

9.2 A barrier or liner of other than vulcanized fiber, employed where spacings are unacceptable between uninsulated live parts of opposite polarity or between uninsulated live parts and accessible metal parts, shall comply with all of the following:

- a) The barrier or liner shall be of insulating material that complies with Table 9.1
- b) The minimum thickness of the barrier or liner shall be at least 0.71 mm (0.028 inch), except that 0.33 mm (0.013 inch) is acceptable where used in conjunction with an air space of at least one-half of the required spacing.

Exception: The thickness of the barrier may be less than that specified in 9.1 providing that the results of a separate investigation indicate acceptable performance. For example, 0.18 mm (0.007 inch) thick polyethylene terephthalate (PETP) film is considered equivalent to 0.71 mm (0.028 inch) thick vulcanized fiber. Resin bonded mica 0.15 mm (0.006 inch) thick is considered electrically equivalent to 0.71 mm (0.028 inch) thick vulcanized fiber; however, its use is limited to applications where it is protected from mechanical abuse or movement.

- c) The barrier or liner shall be equivalent to vulcanized fiber in mechanical strength (tensile strength, tear resistance, puncture strength, creep, and the like) if likely to be subject to mechanical damage. See Polymeric Materials – Industrial Laminates, Filament Wound Tubing, Vulcanized Fibre, and Materials used in Printed Wiring Boards, UL 746E, Vulcanized Fibre, Section 9, for specific performance indexing data on vulcanized fiber.
- d) The maximum use temperature shall not exceed either the Functional-Use Temperature Indices, Section 35, Generic Thermal Indices, Section 36, or the Relative Thermal Index, Section 37, of the barrier material, unless an end-product relative thermal capability evaluation is conducted using the requirements of Relative Thermal Capability, Section 38.

9.2 effective until June 1, 2004

Table 9.1
Material requirements for internal barriers

Table 9.1 effective until June 1, 2004

Application	Properties				
	Resistance to ignition from		Flammability classification ^d	Comparative tracking index (CTI) max. PLC ^e	Other criteria ^f
	Hot-wire (HWI) max. PLC ^b	High-current arc (HAI) max. PLC ^c			
Used instead of spacings in contact with live parts	4 or g	3	V-0 or VTM-0	e, o	i, j, k, l, m, n
	3 or g	2	V-1 or VTM-1	e, o	i, j, k, l, m, n
	2 or g	2	V-2 or VTM-2	e, o	i, j, k, l, m, n
Used instead of spacings in conjunction with an air space	4 or g	3 ^h	V-0 or VTM-0	4	i, k
	3 or g	2 ^h	V-1 or VTM-1	4	i, k
	2 or g	2 ^h	V-2 or VTM-2	4	i, k
	2 or g	1 ^h	HB	4	i, k
Used as a physical barrier only	—	—	V-0 or VTM-0 or V-1 or VTM-1 or V-2 or VTM-2 or HB	—	k
	2 or g	1 ^h	HB	—	k
^a Deleted. ^b Hot-Wire Resistance to Ignition – See 3.19. ^c High-Current Arc Resistance to Ignition – See 3.18. ^d Flammability Classification – See 3.14. ^e Comparative Tracking Index – See 3.6 and Comparative Tracking Index (CTI), Section 11. ^f Other criteria; mechanical strength is to be judged in the application. Special consideration is to be given to cold flow or creep characteristics if the barrier material is subjected to any type of long-time mechanical loading (for example, bending, compressive, or tensile loading). See Section 25. ^g Abnormal Overload Test or End-Product Glow-wire Test described in Section 14. ^h Material evaluated with test electrodes positioned as indicated in 13.2. Test is not required if: <p>a) An arcing part is located 12.7 mm (1/2 inch) or more from the material, or</p> <p>b) A nonarcing live part (bus bar, terminal, and the like) is located 0.8 mm (1/32 inch) or more from the material.</p> ⁱ Dielectric Breakdown Strength – The barrier material shall comply with the dielectric strength criteria specified in 12.1. ^j Volume Resistivity – The barrier material shall comply with the volume resistivity criteria specified in Section 16. ^k Mold-Stress Relief – The barrier material shall comply with the mold-stress relief distortion criteria specified in Sections 31 and 63 upon completion of the test described in 63.1. This test is not required for rigid thermosetting material.					

Table 9.1 Continued on Next Page

Table 9.1 Continued

Application	Properties				
	Resistance to ignition from		Flammability classification ^d	Comparative tracking index (CTI) max. PLC ^e	Other criteria ^f
	Hot-wire (HWI) max. PLC ^b	High-current arc (HAI) max. PLC ^c			
^l Creep – Parts subject to mechanical stresses from internal or external sources (such as bending, compressive or tensile loading) are required to withstand the test described in Section 25. There is to be no warpage or distortion that: a) Interferes with normal operation or servicing, b) Results in accessibility of live parts, or c) Reduces electrical spacings below the level necessary to comply with the applicable requirements pertaining to dielectric strength and leakage current This test is not required for rigid thermosets. ^m UV Resistance – The barrier material shall comply with the applicable UV and water immersion requirements in Section 27. ⁿ Water Exposure and Immersion (For Equipment Intended for Outdoor Use) – The barrier material shall comply with the applicable water immersion and dimensional change criteria specified in Section 28. ^o For a barrier in contact with electrically live parts, a maximum CTI PLC of 4 is required for indoor equipment in a relatively clean environment. Higher CTI values would be required where a greater degree of contamination and/or potentials are involved, as indicated in Table 8.1 and Comparative Tracking Index (CTI), Section 11.					

9.3 A material, that is used as a physical barrier against contact with parts that can cause injury to persons during intended use, cleaning, servicing, or to restrict access to circuitry where there is an increased risk of electric shock, shall comply with the requirements in 9.2.

9.3 effective until June 1, 2004

10.1 Section 10 – 40 indicated the test methods and minimum performance levels specified in part 2 of Figures 6.1, 7.1 and Table 8.1. Some materials may not comply with all of the general properties required for the application. In such cases, the application must be further considered to determine if the material's characteristics are not acceptable, or if a reduced value can be accepted without increasing the likelihood of risk for the particular end-product.

10.1 effective until June 1, 2004

14.1.1 Materials that do not comply with the minimum hot-wire ignition levels shown in Table 8.1 may be evaluated by an abnormal overload test or the glow-wire end-product test. The abnormal overload test passes abnormal currents through current-carrying members as described in 14.2. Over-current values and times are shown in Table 51.1 as a function of the circuit over-current device rating. The glow-wire end-product test subjects the end-product to an electrically heated wire. Glow-wire test temperatures are shown in Table 75.1 and are determined by end-product use.

Exception No. 1: The abnormal overload test or the glow-wire end-product test need not be conducted if the electrically live parts are spaced 0.8 mm (1/32 inch) or more from the material.

Exception No. 2: The abnormal overload test or the glow-wire end-product test need not be conducted for non-hazardous energy circuits.

14.1.1 effective until June 1, 2004

14.3 Glow-wire end-product test

Title of 14.3 effective until June 1, 2004

31.1 Conditioning of the equipment as described in 63.1 or 63.2, whichever is applicable according to Figure 6.1 or 7.1 shall not cause softening of the material as determined by handling immediately after the conditioning, nor shall there be shrinkage, warpage, or other distortion as judged after cooling to room temperature, that results in any of the following:

- a) Reduction of spacings between uninsulated live parts of opposite polarity, uninsulated live parts and accessible dead or grounded metal, uninsulated live parts and the enclosure below the minimum acceptable values.
- b) Making uninsulated live parts or internal wiring accessible to contact, or defeating the integrity of the enclosure so that acceptable mechanical protection is not afforded to internal parts of the equipment.
- c) Causing a condition that results in the equipment not complying with the power-supply-cord strain-relief requirements, if applicable.
- d) Causing interference with the intended operation or servicing of the equipment.

Exception: The conditioning described in 63.1 and 63.2 is not required for rigid thermosetting materials or for low-pressure foamed molded parts.

31.1 effective until June 1, 2004

33.1 After the test samples have cooled to room temperature following the oven conditioning described in 63.1 or 63.2 (whichever is applicable according to Figure 6.1 or 7.1), the sample shall be subjected to the strain-relief test and shall comply with the requirements applicable to the equipment.

33.1 effective until June 1, 2004

A.2 It may not be necessary that a complete series of end-product tests be required, provided that equivalent or better material properties can be demonstrated by standardized small-scale tests on the candidate material when compared to the properties of a material having acceptable application performance.

Exception: A candidate material that does not provide equivalent material properties to the properties of a material having acceptable application performance, may be acceptable providing that the candidate material possesses the minimum performance level required in Figure 6.1 or 7.1 and/or Table 8.1 for the application.

A.2 effective until June 1, 2004

Table A.1
Alternative material consideration

Table A.1 effective until June 1, 2004

Material property parameters (Column 1)	Candidate material characteristics, equivalent or better than characteristics of the original material considered acceptable for the application (Column 2)	Candidate material characteristics, equivalent or better than those required for the application (Column 3)	Candidate material characteristics not equivalent to original material characteristics nor meets those required for the application (Column 4)
FLAMMABILITY (flammability classification at use thickness and color)	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct flame test on part or enclosure (See Flammability – 12 mm Flame, Section 17, Flammability – 127 mm (5 inch) Flame, Section 19, Enclosure Flammability – Large Mass Considerations, Section 21)
ELECTRIC STRENGTH (1) Volume resistivity (2) Dielectric Strength	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product (1) leakage current tests or insulation resistance complying with 16.3 (2) dielectric withstand complying 12.1
TRACKING RESISTANCE (1) Comparative tracking index or (2) Inclined Plane Tracking	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	(1) Increase spacings to $\geq \frac{1}{2}$ in. (2) Increase spacings to: Refer to applicable end-product considerations.
WATER RESISTANCE (1) Dimensional change after water exposure (2) Properties after water immersion (Outdoor use only) Also see A.4	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product Humidity/immersion tests per 28.2 Material is not suitable for prolonged exposure to water
ULTRA-VIOLET RESISTANCE Properties after ultra-violet exposure. (Outdoor use only) Also see A.4	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Material is not suitable for exposure to weather
RESISTANCE TO ELECTRICAL IGNITION (1) Hot- wire ignition and flame classification combination (2) High current arc resistance and flame classification combination	Candidate Material Considered Acceptable	Candidate Material Considered Acceptable	Conduct end-product: Abnormal Overload Test or Glow Wire Test per Section 14 Arc-Resistance Test per par. 13.3 – 13.5
MECHANICAL (See note b)	Candidate Material Considered Acceptable ^a	NA	Conduct end-product

Table A.1 Continued on Next Page

Table A.1 Continued

Material property parameters (Column 1)	Candidate material characteristics, equivalent or better than characteristics of the original material considered acceptable for the application (Column 2)	Candidate material characteristics, equivalent or better than those required for the application (Column 3)	Candidate material characteristics not equivalent to original material characteristics nor meets those required for the application (Column 4)
(1) Tensile or Flexural Strength (2) Tensile or Izod impact or Charpy			(1) Crushing Resistance per 23.1 and Strain Relief per 33.1 or Conduit tests per UL 50 or UL 508 (2) Impact Resistance per Sec. 24 and Strain Relief per 33.1 or Conduit tests per UL 50 or UL 508
DEFORMATION (See notes a) (1) Heat Deflection (2) Creep	Candidate Material Considered Acceptable ^a	NA	Conduct end-product Mold Stress-Relief test. Test is not required for thermoset materials.
	All alternative or substitute materials are to be subjected to end product creep tests (see Section 25) unless: a) The candidate material is of the same composition b) The candidate has equivalent of higher small-scale heat deflection, vicat softening, or ball pressure temperature indices c) The candidate has equivalent creepage characteristics based on tests and/or test data (Note - the test results being compared must have the same test parameters) Creep evaluations are not required for rigid thermoset materials.		
MAXIMUM USE TEMPERATURE	Refer to Sections 34 – 40		
SPECIAL END-USE CONSIDERATIONS^b	If indicated by the applicable path in Figure 6.1 or 7.1, all alternative or substitute materials are to be subjected to the abnormal operation (29.1) and severe conditions tests (30.1), unless the candidate is of the same generic type with the same percentage and type of fillers, reinforcements, heat stabilizers and flame retardants.		

^a All alternative or substitute materials are to be subjected to end-product impact, crush, conduit, strain relief and mold stress-relief tests unless:

1) The candidate material is of the same generic type with the same percentage and type of fillers and reinforcements, and

2) The candidate material has equivalent or higher small-scale tensile or flexural strength, tensile or izod impact and heat deflection ratings indicated above.

^b See A.4

No Text on This Page

Subject 746A (746B, 746C, 746D, 94, 588)
(In reply, refer to Subject 746.)

1285 Walt Whitman Road
Melville, NY 11747-3081
March 20, 2001

**TO: Industry Representatives on the Industry Advisory Group of UL for
Plastic Materials
Electrical Council of Underwriters Laboratories Inc.
Fire Council of Underwriters Laboratories Inc.
Subscribers to UL's Standards Service for:
Polymeric Materials – Short Term Property Evaluations, UL 746A
Polymeric Materials – Long Term Property Evaluations, UL 746B
Polymeric Materials – Use in Electrical Equipment Evaluations, UL 746C
Polymeric Materials – Fabricated Parts, UL 746D
Tests for Flammability of Plastic Materials, UL 94
Seasonal and Holiday Decorative Products, UL 588
Listing Service for
Decorative Lighting Strings, Category DGZZ**

**SUBJECT: New Recognition Service for Polymeric Materials For Use In Seasonal & Holiday
Decorative Products (QMT02)**

This bulletin replaces UL's Subject 746A (746B, 746C, 746D, 94, 588) bulletin dated March 8, 2001 referencing the same subject. The reference to Listing Service for Seasonal and Holiday Decorative Products, Category DGVF in the March 8, 2001 bulletin has been changed to Listing Service for Decorative Lighting Strings, Category DGZZ.

Underwriters Laboratories Inc., (UL) announces a willingness to accept submittals for Recognition under the newly established category of Polymeric Materials For Use In Seasonal & Holiday Decorative Products (QMT02). Effective January 2, 2003, the use of materials Recognized under this category will become a requirement for products Listed in accordance with the Standard for Seasonal & Holiday Decorative Products, UL 588.

The following are the minimum requirements for inclusion in QMT02;

1) Flammability

a) All materials shall attain a flammability rating of V-0 or V-1 (minimum thickness 0.8 mm or less) in accordance with the Standard for Tests for Flammability of Plastic Materials for Parts in Devices and Appliances, UL 94. Testing will be conducted at both the minimum thickness of the Recognized polymeric material as well as at 3.0 (+0.2) mm, and

b) All materials shall attain a flammability rating of SC-0 or SC-1 in accordance with the Standard for Tests for Flammability of Small Polymeric Component Materials, UL 1694. Testing will be performed on standardized flame bars of 55 (±5) x 13.0 (±0.5) mm at a thickness of 0.8 (±0.1) mm or less. No other sample dimensions will be applicable. (Note: These are standard UL 94 Vertical flame bars cut roughly in half.)

2) Resistance to Ignition

a) For materials which attain a flammability rating of SC-0, no minimum ratings are established with respect to Resistance to Ignition.

b) For materials which attain a flammability rating of SC-1, a minimum Performance Level Category (PLC) of 3 shall be established at the material's Recognized minimum thickness for Hot Wire Ignition (HWI) and High Current Arc Ignition (HAI) in accordance with the Standard for Polymeric Materials - Short Term Evaluations, UL 746A.

3) Relative Thermal Index (RTI)

A minimum RTI of 90 °C (established for all properties in accordance with the Standard for Polymeric Materials - Long Term Property Evaluations, UL 746B) will be required. This coincides with current requirements for the Standard for Seasonal & Holiday Decorative Products, UL 588, effective February 14, 2003.

4) Specific Gravity

The Specific Gravity, measured in accordance with the Standard for Polymeric Materials - Short Term Property Evaluations, UL 746A, will be verified to confirm that the material is within the declared normal tolerances (established by the manufacturer as part of the Recognition). The tolerance will be published on the Recognition ("Yellow") Card.

5) Identification Tests

In order to ensure continuity in the product's formulation, additional polymer identification testing (IR, TGA, DSC, SG, etc.) will be determined by UL and incorporated into the New Work testing and UL's Follow-Up Test Program.

Attached as Appendix A is a copy of the Guide Information. A sample Recognition Card is attached as Appendix B. The Guide Card/Recognition Card also has the provision for noting when a material has been investigated and found acceptable for "Suitability for Outdoor Use."

The UL Recognized Component Mark will be a MANDATORY part of the required Markings for products Recognized under this category. The Recognized Component Mark, along with the Recognized Company name and material designation, will be required on the smallest unit container.

Subscribers interested in submitting products under the QMTO2 Recognition Service should contact Mr. Dan O'Shea at UL's Melville office. His contact information is shown below. UL will then send you a Product Information Form for each material to be submitted which will convey additional information about sample requirements, etc., and will ask you the questions necessary for the UL staff to commence an investigation.

Questions regarding the new program requirements for Recognized Polymeric Materials For Use In Seasonal & Holiday Decorative Products (QMTO2), should be directed to Mr. Dan O'Shea. Questions regarding the Standard for Seasonal and Holiday Decorative Products, UL 588, should be directed to Mr. Anthony Tassone (631-271-6200, Ext. 22943).

UNDERWRITERS LABORATORIES INC.

DANIEL W. O'SHEA (Ext. 23070)
Project Engineer
Conformity Assessment Services 3016P
Phone (631) 271-6200
Fax: (631) 439-6046
E-mail: daniel.w.oshea@us.ul.com

01ST103_UL746

REVIEWED BY:

JOHN STIMITZ (Ext. 22214)
Associate Managing Engineer
Conformity Assessment Services 3016P
Phone (631) 271-6200
Fax: (631) 439-6046
E-mail: John.Stimitz@us.ul.com

APPENDIX A**PROPOSED GUIDE CARD****[Plastics – Component] Polymeric Materials for Use in Seasonal and Holiday Decorative Products – Component**

The materials covered under this category are incomplete in certain constructional features or restricted in performance capabilities and are intended for use as components of complete equipment submitted for investigation rather than for direct separate installation in the field. THE FINAL ACCEPTANCE OF THE COMPONENT IS DEPENDENT UPON ITS INSTALLATION AND USE IN COMPLETE EQUIPMENT SUBMITTED TO UNDERWRITERS LABORATORIES INC.

USE

This category covers polymeric materials intended for use in seasonal and holiday decorative products and accessories.

FLAMMABILITY

Materials have been classified based on burning tests conducted in accordance with "UL 1694, Tests for Flammability of Small Polymeric Component Materials." By small-scale tests on standardized samples, materials are classified as SC-0 or SC-1.

RELATIVE TEMPERATURE INDEX (RTI)

In accordance with UL 746B, "Polymeric Materials – Long Term Property Evaluations," RTI is the maximum service temperature for a material, where a class of critical property will not be unacceptably compromised through chemical thermal degradation, over the reasonable life of an electrical product, relative to a reference material having a confirmed, acceptable corresponding performance defined RTI.

SPECIFIC GRAVITY

The relative density range of the individual Recognition determined in accordance with UL 746A, "Polymeric Materials – Short Term Property Evaluations."

SUITABILITY FOR OUTDOOR USE (f1, f2)

Where indicated, the effect of exposure to ultraviolet light and water on property retention has been evaluated in accordance with UL 746C, "Polymeric Materials – Use in Electrical Equipment Evaluations."

PERFORMANCE LEVEL CATEGORIES (PLC)

In order to avoid an excessive level of implied precision and bias, material performances for several tests are recorded as Performance Level Categories (PLC), based on the mean test results (rather than recording the exact numerical results), as indicated in the table following the test description.

Hot Wire Ignition (HWI)

Performance is expressed as the mean number of seconds needed either to ignite standard specimens or to burn through the specimens without ignition. The specimens are wrapped with resistance wire that dissipates a specified level of electrical energy in accordance with UL 746A.

HWI Range Mean Ign Time (in sec)	Assigned PLC
120 and longer	0
60 through 119	1
30 through 59	2
15 through 29	3

High Current Arc Ignition (HAI)

Performance is expressed as the number of arc rupture exposures (standardized as to electrode type and shape and electric circuit) which are necessary to ignite a material when they are applied at a standard rate on the surface of the material in accordance with UL 746A.

HAI Range Mean No. of Arc to Cause Ign	Assigned PLC
120 and greater	0
60 through 119	1
30 through 59	2
15 through 29	3

REQUIREMENTS

Minimum requirements for products covered under this category are in accordance with UL 588, "Seasonal and Holiday Decorative Products."

UL MARKING

Products Recognized under UL's Component Program are identified by markings consisting of the manufacturer's identification and catalog, model or other product designation. In addition, component products which are produced under the UL Component Recognition Program will also bear the Recognized Component Mark*.

The Listing or Classification Mark of Underwriters Laboratories Inc. is not authorized for use on, or in connection with, Recognized Components. Only those components which actually bear the "Marking" should be considered as being covered under the Component Recognition Program.

* The actual symbol will be shown on the guidecard.

APPENDIX B**Proposed ModelCard (QMT02)**

Polymeric Materials For Use In Seasonal & Holiday Decorative Products – Component

UNDERWRITERS LABORATORIES INC
333 PFINGSTEN RD
NORTHBROOK, IL 60062

Date

E99999 (MEL)

RTI

Mech

Material Deg	Color	Min Thk (mm)	Flame Class	Elec	W/Imp	W/O Imp	HWI	HAI	Specific Gravity
Polypropylene (PP), furnished in the form of pellets or sheets.									
<i>(Report Date: 01/03/2001)</i>									
PP-ABC	All	0.75	SC-1	90	90	90	3	3	0.902 – 0.918
DEF-SC0 (f1)	GN	0.75	SC-0	105	105	105	–	–	0.980 – 0.996

Polyvinylchloride (PVC), furnished in the form of pellets*(Report Date: 01/04/2001)*

123-FR (f2)	GN, WT	0.5	SC-0	120	110	125	0	0	1.772 – 1.811
UV-456 (f1)	All	0.4	SC-1	120	95	115	2	3	1.320 – 1.359

(f1) Suitable for outdoor use with respect to exposure to Ultraviolet Light, Water Exposure and Immersion in accordance with UL 746C.

(f2) – Subjected to one or more of the following tests: Ultraviolet light, water exposure or immersion in accordance with UL 746C where the acceptability for outdoor use is to be determined by UL, Inc.

Marking: Company name or trade name, material designation, and the Recognition Mark, , on container, wrapper or molded on finished part.

Cutoff

See General Information Preceding These Recognitions

Small-scale flame test data is intended solely for determining the flammability of plastic materials used in the components and parts of end-product devices, sub-assemblies and equipment, where the acceptability of the combination is determined by ULI.